

Gelest

Hydrophobicity, Hydrophilicity and Silane Surface Modification



Materials for:

Water-Repellents

Anti-Stiction Coatings

Mineral Surface Treatments

Fillers for Composites

Pigment Dispersants

Dielectric Coatings

Release Coatings

Optical (LCD) Coatings

Bonded Phases

Self-Assembled Monolayers (SAMs)

Architectural Coatings

Crosslinkers for Silicones

Nanoparticle Synthesis



Gelest, Inc.

Telephone: General 215-547-1015
Order Entry 888-734-8344
FAX: 215-547-2484
Internet: www.gelest.com
Correspondence: 11 East Steel Rd.
Morrisville, PA 19067

For further information consult our web site at: www.gelest.com

In Europe:

For commercial quantities contact:

Gelest Ltd
46 Pickering Street
Maidstone
Kent ME15 9RR
United Kingdom
Tel: +44(0) 1622 741115
Fax: +44(0) 1622 741114
e-mail: europe@gelest.com

For research quantities contact:

ABCR GmbH & Co. KG
Im Schlehert
D-76187 Karlsruhe
Germany
Tel: +49 - 721 - 950610
Fax: +49 - 721 - 9506180
e-mail: info@abcr.de
on-line catalog: www.abcr.de

In Japan:

For commercial and research quantities contact:

AZmax Co. Ltd. Tokyo Office
Matsuda Yaesudori Bld F8
1-10-7 Hatchoubori, Chuo-Ku
Tokyo 104-0032
Tel: 81-3-5543-1630
Fax: 81-3-5543-0312
e-mail: sales@azmax.co.jp
on-line catalog: www.azmax.co.jp

In South-East Asia:

For commercial and research quantities contact:

Altus Technologies Pte Ltd
196 Pandan Loop #06-09
Pantech Industrial Complex
Singapore 128384
Tel: (65) 6779 7666
Fax: (65) 6779-7555
www.altus.com.sg

Front Cover Photos: Water rolls off a duck's back. Lotus leaves exhibit superhydrophobicity. Biological systems are dependent on water, but at the same time must control the interaction. In a sense, all living organisms exhibit behaviors that can be described as both hydrophobic and hydrophilic.

Sales of all products listed are subject to the published terms and conditions of Gelest, Inc.

Gelest **Hydrophobicity, Hydrophilicity and Silane Surface Modification**

TABLE OF CONTENTS

Silanes and Surface Modification	2
Water, Hydrophobicity and Hydrophilicity	3
Wettability and Contact Angle	4
Critical Surface Tension and Adhesion	5
How does a Silane Modify a Surface?	6
Selecting a Silane for Surface Modification	7
Hydrophobic Surface Treatments	8
Hydrophilic Surface Treatments	10
Range of Water Interaction with Surfaces	11
Reacting with the Substrate	12

Special Topics:

Dipodal Silanes	13
Linker Length	14
Partition, Orientation and Self-Assembly in Bonded Phases	15
Modification of Metal Substrates	16
Difficult Substrates	17
Applying a Silane Surface Treatment	18
Hydrophobic Silane Selection Guide	20

Silane Properties:

Hydrophobic Silanes	30
Hydrophobic Silanes - Dipodal	56
Hydrophobic Silanes - Polymeric	59
Hydrophilic Silanes - Polar	60
Hydrophilic Silanes - Hydrogen Bonding	62
Hydrophilic Silanes - Hydroxylic	66
Hydrophilic Silanes - Ionic / Charge Inducible	67
Hydrophilic Silanes - Polymeric	70
Hydrophilic Silanes - Epoxy / Masked	71
Silyl Hydrides	72

Hydrophobicity, Hydrophilicity and Silane Surface Modification

by Barry Arkles

©2006 Gelest, Inc.

Silanes and Surface Modification

Silanes are silicon chemicals that possess a hydrolytically sensitive center that can react with inorganic substrates such as glass to form stable covalent bonds and possess an organic substitution that alters the physical interactions of treated substrates.



organic substitution allows permanent property modification

hydrolyzeable alkoxy (alcohol) groups

Property modifications include:

- Hydrophobicity
- Release
- Dielectric
- Absorption
- Orientation
- Hydrophilicity
- Charge Conduction

Applications include:

- Architectural Coatings
- Water-Repellents
- Anti-stiction Coatings for MEMs
- Mineral Surface Treatments
- Fillers for Composites
- Pigment Dispersants
- Dielectric Coatings
- Anti-fog Coatings
- Release Coatings
- Optical (LCD) Coatings
- Bonded Phases
- Self-Assembled Monolayers (SAMs)
- Crosslinkers for Silicones
- Nanoparticle Synthesis

In contrast with silanes utilized as coupling agents in adhesive applications, silanes used to modify the surface energy or wettability of substrates under normal conditions do not impart chemical reactivity to the substrate. They are often referred to as non-functional silanes. The main classes of silanes utilized to effect surface energy modification without imparting reactivity are:

Hydrophobic Silanes

- Methyl
- Linear Alkyl
- Branched Alkyl
- Fluorinated Alkyl
- Aryl
- Dipodal

Hydrophilic Silanes

- Polar
- Hydroxylic
- Ionic
- Charge inducible /charge switchable
- Embedded Hydrophilicity
- Masked

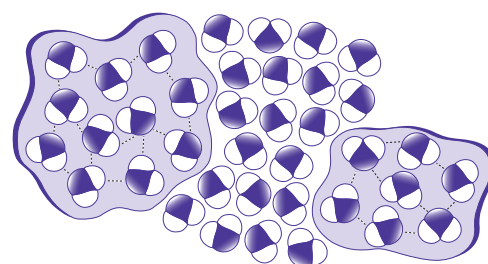
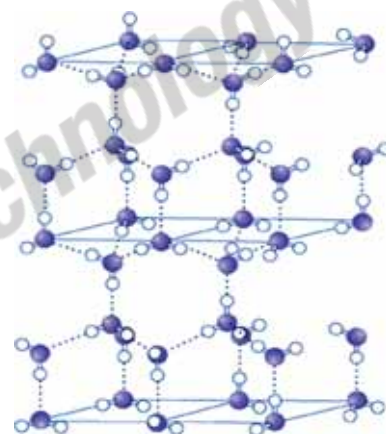
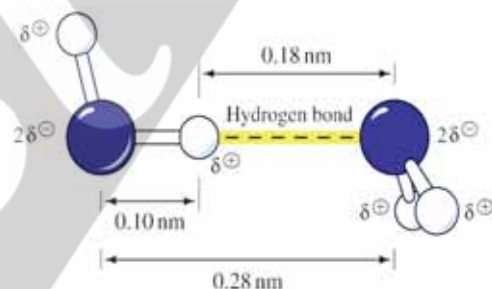
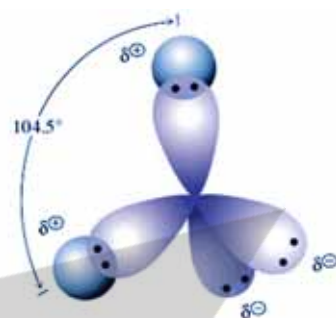
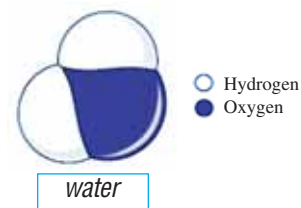
Water, Hydrophobicity and Hydrophilicity

Hydrophobic and **Hydrophilic** are frequently used descriptors of surfaces. A surface is hydrophobic if it tends *not to* adsorb water or be wetted by water. A surface is hydrophilic if it tends *to* adsorb water or be wetted by water. More particularly, the terms describe the interaction of the boundary layer of a solid phase with liquid or vapor water. Silanes can be used to modify the interaction of boundary layers of solids with water with a high degree of control, effecting variable degrees of hydrophobicity or hydrophilicity.

Since the interaction of water with surfaces is frequently used to define surface properties, a brief review of its structure and properties can be helpful. Although the structure of water is a subject of early discussion in the study of physical sciences, it is interesting to note that the structure of liquid water is still not solved and, even so, most technologists lose appreciation of what is known about its structure and properties.

The quantum calculation of the structure of an isolated H₂O molecule has evolved to the currently accepted model which demonstrates a strong dipole, but no lone electron pairs associated with sp³ hybridized orbitals of oxygen. This model of isolated H₂O conforms most closely to the vapor state and extrapolation often leads to the conclusion that water is a collection of individual molecules which associate with each other primarily through dipole interactions. The polar nature of water, with its partial positive and partial negative dipole, explains why bulk water readily dissolves many ionic species and interacts with ionic surfaces. The difference between isolated vapor phase water and bulk liquid water is much more extreme than can be accounted for by a model relying only on dipole interaction. The properties of bulk liquid water are strongly influenced by hydrogen bond interactions. In the liquid state, in spite of 80% of the electrons being concerned with bonding, the three atoms of a water molecule do not stay together as discrete molecules. The hydrogen atoms are constantly exchanging between water molecules in a protonation-deprotonation process. Both acids and bases catalyze hydrogen exchange and, even when at its slowest rate of exchange (at pH 7), the average residence time of a hydrogen atom is only about a millisecond. In the liquid state, water molecules are bound to each other by an average of three hydrogen bonds. Hydrogen bonds arise when a hydrogen that is covalently bound to an oxygen in one molecule of water nears another oxygen from another water molecule. The electrophilic oxygen atom “pulls” the hydrogen closer to itself. The end result is that the hydrogen is now shared (unequally) between the oxygen to which it is covalently bound and the electrophilic oxygen to which it is attracted (O-H...O). Each hydrogen bond has an average energy of 20 kJ/mol. This is much less than an O-H covalent bond, which is 460 kJ/mol. Even though an individual hydrogen bond is relatively weak, the large number of hydrogen bonds that exist in water which pull the molecules together have a significant role in giving water its special bulk properties. In ice, water molecules are highly organized with four hydrogen bonds. Liquid water is thought to be a combination of domains of molecules with 3-4 hydrogen bonds separated by domains with 2-3 hydrogen bonds, subject to constant turnover - the *flickering cluster model*.

This brief description of water is provided in order to give the insight that whenever a solid surface interacts with bulk water it is interacting with a soft matter structure, not simply a collection of individual molecules. Surface interactions with water must compete with a variety of internal interactions of liquid phase water: van der Waals forces, dipole interactions, hydrogen bonding and proton exchange.



Wettability and Contact Angle

A surface is said to be wetted if a liquid spreads over the surface evenly without the formation of droplets. When the liquid is water and it spreads over the surface without the formation of droplets, the surface is said to be hydrophilic. In terms of energetics, this implies that the forces associated with the interaction of water with the surface are greater than the cohesive forces associated with bulk liquid water. Water droplets form on hydrophobic surfaces, implying that cohesive forces associated with bulk water are greater than the forces associated with the interaction of water with the surface. Practically, hydrophobicity and hydrophilicity are relative terms. A simple quantitative method for defining the relative degree of interaction of a liquid with a solid surface is the contact angle of a liquid droplet on a solid substrate. If the contact angle of water is less than 30°, the surface is designated hydrophilic since the forces of interaction between water and the surface nearly equal the cohesive forces of bulk water and water does not cleanly drain from the surface. If water spreads over a surface and the contact angle at the spreading front edge of the water is less than 10°, the surface is often designated as superhydrophilic provided that the surface is not absorbing the water, dissolving in the water or reacting with the water. On a hydrophobic surface, water forms distinct droplets. As the hydrophobicity increases, the contact angle of the droplets with the surface increases. Surfaces with contact angles greater than 90° are designated as hydrophobic. The theoretical maximum contact angle for water on a smooth surface is 120°. Micro-textured or micro-patterned surfaces with hydrophobic asperities can exhibit apparent contact angles exceeding 150° and are associated with superhydrophobicity and the “lotus effect”.



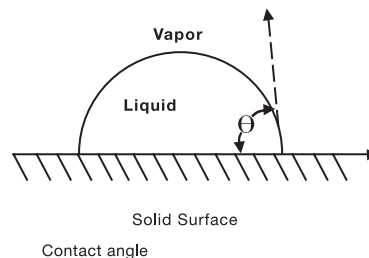
Ordinary Surface
“typical wetting”

Hydrophobic-
“poor wetting”



Hydrophilic-
“good wetting”

Contact Angle Defines Wettability



Contact Angle of Water on Smooth Surfaces

	θ
heptadecafluorodecyltrimethoxysilane*	115°
poly(tetrafluoroethylene)	108-112°
poly(propylene)	108°
octadecyldimethylchlorosilane*	110°
octadecyltrichlorosilane*	102-109°
tris(trimethylsiloxy)-silylethyldimethylchlorosilane	104°
octyldimethylchlorosilane*	104°
dimethyldichlorosilane*	95-105°
butyldimethylchlorosilane*	100°
trimethylchlorosilane*	90-100°
poly(ethylene)	88-103°
poly(styrene)	94°
poly(chlorotrifluoroethylene)	90°
human skin	75-90°
diamond	87°
graphite	86°
silicon (etched)	86-88°
talc	50-55°
chitosan	80-81°
steel	70-75°
methacryloxypropyltrimethoxysilane	70°
gold, typical (see gold, clean)	66°
intestinal mucosa	50-60°
glycidoxypropyltrimethoxysilane*	49°
kaolin	42-46°
platinum	40°
silicon nitride	28-30°
silver iodide	17°
soda-lime glass	<15°
gold, clean	<10°

* Note: Contact angles for silanes refer to smooth treated surfaces.

Critical Surface Tension and Adhesion

While the contact angle of water on a substrate is a good indicator of the relative hydrophobicity or hydrophilicity of a substrate, it is not a good indicator for the wettability of the substrate by other liquids. Critical surface tension is associated with the wettability or release properties of a solid. It serves as a better predictor of the behavior of a solid with a range of liquids.

Liquids with a surface tension below the critical surface tension (γ_c) of a substrate will wet the surface, i.e., show a contact angle of 0 ($\cos\theta_e = 1$). The critical surface tension is unique for any solid and is determined by plotting the cosine of the contact angles of liquids of different surface tensions and extrapolating to 1. The contact angle is given by Young's equation:

$$\gamma_{sv} - \gamma_{sl} = \gamma_{lv} \cdot \cos\theta_e$$

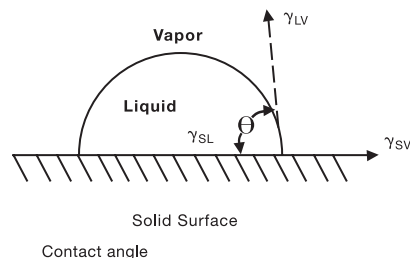
where γ_{sl} = interfacial surface tension, γ_{lv} = surface tension of liquid.

Hydrophilic behavior is generally observed by surfaces with critical surface tensions greater than 45 dynes/cm. As the critical surface tension increases, the expected decrease in contact angle is accompanied with stronger adsorptive behavior and with increased exotherms associated with the adsorption.

Hydrophobic behavior is generally observed by surfaces with critical surface tensions less than 35 dynes/cm. At first, the decrease in critical surface tension is associated with oleophilic behavior, i.e. the wetting of the surfaces by hydrocarbon oils. As the critical surface tensions decrease below 20 dynes/cm, the surfaces resist wetting by hydrocarbon oils and are considered oleophobic as well as hydrophobic.

Silane treatment has allowed control of thixotropic activity of silica and clays in paint and coating applications. In the reinforcement of thermosets and thermoplastics with glass fibers, one approach for optimizing reinforcement is to match the critical surface tension of the silylated glass surface to the surface tension of the polymer in its melt or uncured condition. This has been most helpful in resins with no obvious functionality such as polyethylene and polystyrene. Immobilization of cellular organelles, including mitochondria, chloroplasts, and microsomes, has been effected by treating silica with alkylsilanes of C₈ or greater substitution.

Contact Angle Defines Wettability



Critical surface tensions

	γ_c dynes/cm
heptadecafluorodecyltrichlorosilane	12.0
poly(tetrafluoroethylene)	18.5
octadecyltrichlorosilane	20-24
methyltrimethoxysilane	22.5
nonafluorohexyltrimethoxysilane	23.0
vinyltriethoxysilane	25
paraffin wax	25.5
ethyltrimethoxysilane	27.0
propyltrimethoxysilane	28.5
glass, soda-lime (wet)	30.0
poly(chlorotrifluoroethylene)	31.0
poly(propylene)	31.0
poly(propylene oxide)	32
polyethylene	33.0
trifluoropropyltrimethoxysilane	33.5
3-(2-aminoethyl)-aminopropyltrimethoxysilane	33.5
poly(styrene)	34
p-tolyltrimethoxysilane	34
cianoethyltrimethoxysilane	34
aminopropyltriethoxysilane	35
polymethylmethacrylate	39
polyvinylchloride	39
phenyltrimethoxysilane	40.0
chloropropyltrimethoxysilane	40.5
mercaptopropyltrimethoxysilane	41
glycidoxypropyltrimethoxysilane	42.5
poly(ethyleneterephthalate)	43
poly(ethylene oxide)	43-45
copper (dry)	44
aluminum (dry)	45
iron (dry)	46
nylon 6/6	45-6
glass, soda-lime (dry)	47
silica, fused	78
titanium dioxide (anatase)	91
ferric oxide	107
tin oxide	111

Note: Critical surface tensions for silanes refer to smooth treated surfaces.

How does a Silane Modify a Surface?

Most of the widely used organosilanes have one organic substituent and three hydrolyzable substituents. In the vast majority of surface treatment applications, the alkoxy groups of the trialkoxysilanes are hydrolyzed to form silanol-containing species. Reaction of these silanes involves four steps. Initially, hydrolysis of the three labile groups occurs. Condensation to oligomers follows. The oligomers then hydrogen bond with OH groups of the substrate. Finally, during drying or curing, a covalent linkage is formed with the substrate with concomitant loss of water. Although described sequentially, these reactions can occur simultaneously after the initial hydrolysis step. At the interface, there is usually only one bond from each silicon of the organosilane to the substrate surface. The two remaining silanol groups are present either in condensed or free form. The R group remains available for covalent reaction or physical interaction with other phases.

Silanes can modify surfaces under anhydrous conditions consistent with monolayer and vapor phase deposition requirements. Extended reaction times (4-12 hours) at elevated temperatures (50°-120°C) are typical. Of the alkoxy silanes, only methoxysilanes are effective without catalysis. The most effective silanes for vapor phase deposition are cyclic azasilanes.

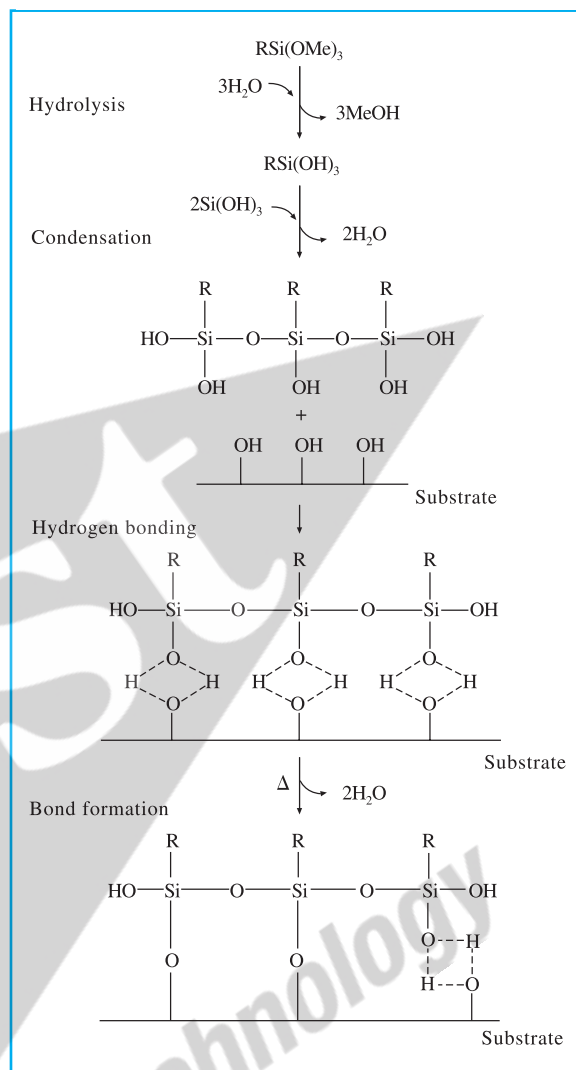
Hydrolysis Considerations

Water for hydrolysis may come from several sources. It may be added, it may be present on the substrate surface, or it may come from the atmosphere. The degree of polymerization of the silanes is determined by the amount of water available and the organic substituent. If the silane is added to water and has low solubility, a high degree of polymerization is favored. Multiple organic substitution, particularly if phenyl or tertiary butyl groups are involved, favors formation of stable monomeric silanols.

The thickness of a polysiloxane layer is also determined by the concentration of the siloxane solution. Although a monolayer is generally desired, multilayer adsorption results from solutions customarily used. It has been calculated that deposition from a 0.25% silane solution onto glass could result in three to eight molecular layers. These multilayers could be either interconnected through a loose network structure, or intermixed, or both, and are, in fact, formed by most deposition techniques. The orientation of functional groups is generally horizontal, but not necessarily planar, on the surface of the substrate.


The formation of covalent bonds to the surface proceeds with a certain amount of reversibility. As water is removed, generally by heating to 120°C for 30 to 90 minutes or evacuation for 2 to 6 hours, bonds may form, break, and reform to relieve internal stress.

Hydrolytic Deposition of Silanes



B. Arkles, CHEMTECH, 7, 766, 1977

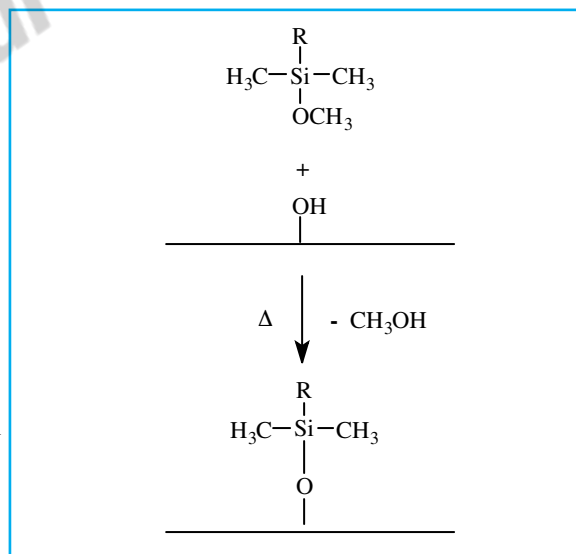Anhydrous Deposition of Silanes



Selecting A Silane for Surface Modification - Inorganic Substrate Perspective

Factors influencing silane surface modification selection include:

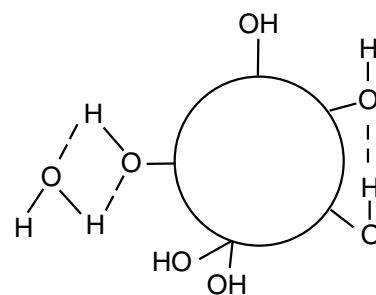
- Concentration of surface hydroxyl groups*
- Type of surface hydroxyl groups*
- Hydrolytic Stability of the bond formed*
- Physical dimensions of the substrate or substrate features*

Surface modification is maximized when silanes react with the substrate surface and present the maximum number of accessible sites with appropriate surface energies. An additional consideration is the physical and chemical properties of the interphase region. The interphase can promote or detract from total system properties depending on its physical properties such as modulus or chemical properties such as water/hydroxyl content.

Hydroxyl-containing substrates vary widely in concentration and type of hydroxyl groups present. Freshly fused substrates stored under neutral conditions have a minimum number of hydroxyls. Hydrolytically derived oxides aged in moist air have significant amounts of physically adsorbed water which can interfere with coupling. Hydrogen bonded vicinal silanols react more readily with silane coupling agents, while isolated or free hydroxyls react reluctantly.

Silanes with three alkoxy groups are the usual starting point for substrate modification. These materials tend to deposit as polymeric films, effecting total coverage and maximizing the introduction of organic functionality. They are the primary materials utilized in composites, adhesives, sealants, and coatings. Limitations intrinsic in the utilization of a polylayer deposition are significant for nano-particles or nano-composites where the interphase dimensions generated by polylayer deposition may approach those of the substrate. Residual (non-condensed) hydroxyl groups from alkoxy-silanes can also interfere in activity. Monoalkoxy-silanes provide a frequently used alternative for nano-featured substrates since deposition is limited to a monolayer.

If the hydrolytic stability of the oxane bond between the silane and the substrate is poor or the application is in an aggressive aqueous environment, dipodal silanes often exhibit substantial performance improvements. These materials form tighter networks and may offer up to 10⁵x greater hydrolysis resistance making them particularly appropriate for primer applications.



Water droplets on a (heptadecafluoro-1,1,2,2-tetrahydrodecyl)trimethoxysilane-treated silicon wafer exhibit high contact angles, indicative of the low surface energy. Surfaces are both hydrophobic and resist wetting by hydrocarbon oils. (water droplets contain dye for photographic purposes).

Silane Effectiveness on Inorganics

	SUBSTRATES
EXCELLENT	Silica
	Quartz
	Glass
	Aluminum (AlO(OH))
	Alumino-silicates (e.g. clays)
	Silicon
	Copper
	Tin (SnO)
	Talc
	Inorganic Oxides (e.g. Fe ₂ O ₃ , TiO ₂ , Cr ₂ O ₃)
GOOD	Steel, Iron
	Asbestos
	Nickel
	Zinc
	Lead
SLIGHT	Marble, Chalk (CaCO ₃)
	Gypsum (CaSO ₄)
	Barytes (BaSO ₄)
	Graphite
POOR	Carbon Black

Estimates for Silane Loading on Siliceous Fillers

Average Particle Size	Amount of Silane (minimum of monolayer coverage)
<1 micron	1.5%
1-10 microns	1.0%
10-20 microns	0.75%
>100 microns	0.1% or less

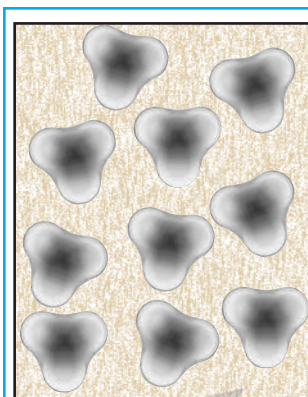
Hydrophobic Silane Surface Treatments

Factors which contribute to the ability of an organosilane to generate a hydrophobic surface are its organic substitution, the extent of surface coverage, residual unreacted groups (both from the silane and the surface) and the distribution of the silane on the surface.


Aliphatic hydrocarbon substituents or fluorinated hydrocarbon substituents are the hydrophobic entities which enable silanes to induce surface hydrophobicity. Beyond the simple attribute that in order to generate a hydrophobic surface the organic substitution of the silane must be non-polar, more subtle distinctions can be made. The hydrophobic effect of the organic substitution can be related to the free energy of transfer of hydrocarbon molecules from an aqueous phase to a homogeneous hydrocarbon phase. For non-polar entities, van der Waals interactions are predominant factors in interactions with water and such interactions compete with hydrogen bonding in ordering of water molecules. Van der Waals interactions for solid surfaces are primarily related to the instantaneous polarizability of the solid which is proportional to the dielectric constant or permittivity at the primary UV absorption frequency and the refractive index of the solid. Entities which present sterically closed structures that minimize van der Waals contact are more hydrophobic than open structures that allow van der Waals contact. Thus, in comparison to polyethylene, polypropylene and polytetrafluoroethylene are more hydrophobic. Similarly methyl-substituted alkylsilanes and fluorinated alkylsilanes provide better hydrophobic surface treatments than linear alkyl silanes.

Surfaces to be rendered hydrophobic usually are polar with a distribution of hydrogen bonding sites. A successful hydrophobic coating must eliminate or mitigate hydrogen bonding and shield polar surfaces from interaction with water by creating a non-polar interphase. Hydroxyl groups are the most common sites for hydrogen bonding. The hydrogens of hydroxyl groups can be eliminated by oxane bond formation with an organosilane. The effectiveness of a silane in reacting with hydroxyls impacts hydrophobic behavior not only by eliminating the hydroxyls as water adsorbing sites, but also by providing anchor points for the non-polar organic substitution of the silane which shields the polar substrates from interaction with water.


Strategies for silane surface treatment depend on the population of hydroxyl groups and their accessibility for bonding. A simple conceptual case is the reaction of organosilanes to form a monolayer. If all hydroxyl groups are capped by the silanes and the surface is effectively shielded, a hydrophobic surface is achieved. Practically, not all of the hydroxyl groups may react leaving residual sites for hydrogen bonding. Further, there may not be enough anchor points on the surface to allow the organic substituents to effectively shield the substrate. Thus the substrate reactive groups of the silane, the conditions of deposition, the ability of the silane to form monomeric or polymeric layers and the nature of the organic substitution all play a role in rendering a surface hydrophobic. The minimum requirements of hydrophobicity and economic restrictions for different applications further complicate selection.




complete coverage

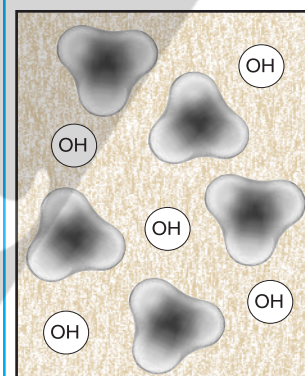

incomplete hydroxyl reaction

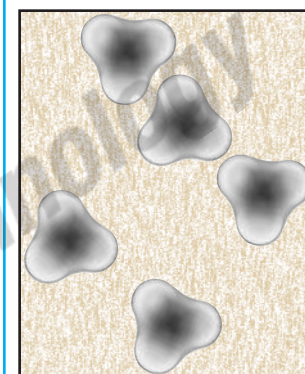

few bonding opportunities



Hypothetical Trimethylsilylated Surfaces

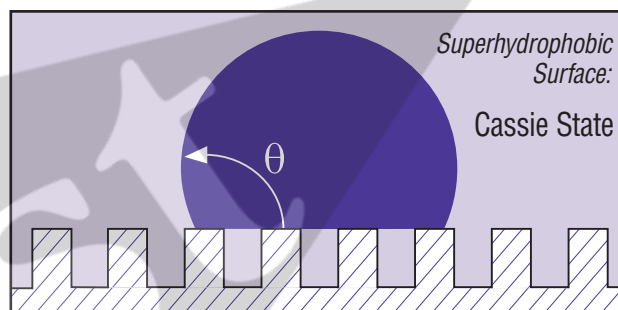
Pyrogenic silica has 4.4-4.6 OH/nm². Typically less than 50% are reacted. Other substrates have fewer opportunities for reaction.

Hydrophobicity is frequently associated with oleophilicity, the affinity of a substance for oils, since non-polar organic substitution is often hydrocarbon in nature and shares structural similarities with many oils. The hydrophobic and oleophilic effect can be differentiated and controlled. At critical surface tensions of 20-30, surfaces are wetted by hydrocarbon oils and are water repellent. At critical surface tensions below 20, hydrocarbon oils no longer spread and the surfaces are both hydrophobic and oleophobic. The most oleophobic silane surface treatments have fluorinated long-chain alkyl silanes and methylated medium chain alkyl silanes.

Superhydrophobic surfaces are those surfaces that present apparent contact angles that exceed the theoretical limit for smooth surfaces, i.e. $>120^\circ$. The most common examples of super-hydrophobicity are associated with surfaces that are rough on a sub-micron scale and contact angle measurements are composites of solid surface asperities and air denoted the *Cassie state*. Perfectly hydrophobic surfaces (contact angles of 180°) have been prepared by hydrolytic deposition of methylchlorosilanes as microfibrillar structures.

Hydrophobicity vs Water Permeability

Although silane and silicone derived coatings are in general the most hydrophobic, they maintain a high degree of permeability to water vapor. This allows coatings to breathe and reduce deterioration at the coating interface associated with entrapped water. Since ions are not transported through non-polar silane and silicone coatings, they offer protection to composite structures ranging from pigmented coatings to rebar reinforced concrete.



Automotive side windows are treated with fluoroalkylsilanes to provide self-cleaning properties. Water beads remove soil as they are blown over the glass substrate during acceleration.

Hydrophilic Silane Surface Treatments

The vast majority of surfaces are hydrophilic and water is omnipresent in the environment, yet the precise nature of interaction of water with specific surfaces is largely unknown. Water adsorption may be uniform or in isolated patches. It may be driven by a number of different physical and chemical processes. The adsorption of water by a surface may be assisted or retarded by other adsorbents present in the environment. The purpose of applying a hydrophilic surface treatment is to control the nature and extent of interaction of water with a surface.

The controlled interaction of water with substrates can offer various degrees of hydrophilicity ranging from physisorption to chemisorption and centers for ion-interaction. The utility of hydrophilic surfaces varies widely. Anti-fog coatings exploit high surface energies to flatten water droplets rather than allowing them to form light-scattering droplets. In biological systems hydrophilic surfaces can reduce nonspecific bonding of proteins. Hydrophilic coatings with hydrogen bonding sites allow formation of tightly adherent layers of water with high lubricity in biological systems and the ability to resist oil adsorption in anti-graffiti coatings. They can also be used to disperse particles in aqueous coatings and oil-in-water emulsions. Hydrophilic coatings with ionic sites form antistatic coatings, dye receptive surfaces and can generate conductive or electrophoretic pathways. Thick films can behave as polymeric electrolytes in battery and ion conduction applications.

In general, surfaces become more hydrophilic in the series: non-polar < polar, no hydrogen-bonding < polar, hydrogen-bonding < hydroxylic, < ionic. The number of sites and the structure and density of the interphase area also have significant influence on hydrophilicity.

Much of the discussion of hydrophobicity centers around high contact angles and their measurement. As a corollary, low or 0° contact angles of water are associated with hydrophilicity, but practically the collection of consistent data is more difficult. Discriminating between surfaces with a 0° contact angle is impossible. The use of heat of immersion is a method that generates more consistent data for solid surfaces, provided they do not react with, dissolve or absorb the tested liquid. Another important consideration is whether water adsorbed is “free” or “bound.” Free water is water that is readily desorbed under conditions of less than 100% relative humidity. If water remains bound to a substrate under conditions of less than 100% relative humidity, the surface is considered hygroscopic. Another description of hygroscopic water is a boundary layer of water adsorbed on a surface less than 200nm thick that cannot be removed without heating. A measure of the relative hygroscopic nature of surfaces is given by the water activity, the ratio of the fugacity, or escaping tendency, of water from a surface compared to the fugacity of pure water.

The hydrophilicity of a surface as measured or determined by contact angle is subject to interference by loosely bound oils and other contaminants. Heats of immersion and water activity measurements are less subject to this interference. Measurements of silane-modified surfaces demonstrate true modification of the intrinsic surface properties of substrates. If the immobilized hydrophilic layer is in fact a thin hydrogel film, then swelling ratios at equilibrium water absorption can provide useful comparative data.

Anti-fog coatings applied to one side of a visor can be prepared from combinations of polyalkylene oxide functional silanes and film-forming hydrophilic silanes.




<u>Heats of Immersion in Water, mJ/m²</u>	
titanium dioxide	225-250
talc	220-260
aminopropyltriethoxysilane*	230-270
silicon dioxide	210-225
glass	200-205
vinyltris(methoxyethoxy)silane*	110-190
mercaptopropyltrimethoxysilane*	80-170
graphite	32-35
polytetrafluoroethylene	24-25

*Data for silane treated surfaces in this table is primarily from B. Marciniec et al, Colloid & Polymer Science, 261, 1435, 1983 recalculated for surface area.

Hydrophilic Silane Surface Treatments (continued)

Controlling hydrophilic interaction with silane surface treatments is accomplished by the selection of a silane with the appropriate hydrophilic substitution. The classes of substitution are:

- Polar, Non-Hydrogen Bonding
- Polar, Hydrogen-Bonding
- Hydroxylic
- Ionic-Charged



Aortic stents are coated to promote hydrophilicity, coupling to polymers and drug delivery systems.

The selection of the class of hydrophilic substitution is dependent on the application. If it is sufficient for water to spread evenly over a surface to form a thin film that washes away and dries off quickly without leaving 'drying spots', then a polar aprotic silane is preferred. If a coating is desired that reduces non-specific binding of proteins or other biofoulants, then a polar hydrogen-bonding material such as a polyether functional silane is preferred. A very different application for a polar non-hydroxylic materials is thin film proton conduction electrolytes. Lubricious coatings are usually hydroxylic since they require a restrained adsorbed phase of water. Antistatic coatings are usually charged or charge-inducible as are ion-conductive coatings used in the construction of thin-film batteries. A combination of hydrophilicity and hydrophobicity may be a requirement in coatings which are used as primers or in selective adsorption applications such as chromatography. Formulation limitations may require that hydrophilicity is latent and becomes unmasked after application.

Factors affecting the intrinsic hydrolytic stability of silane treated surfaces are magnified when the water is drawn directly into the interface. Even pure silicon dioxide is ultimately soluble in water (at a level of 2-6ppm), but the kinetics, low concentration for saturation and phase separation, make this a negligible consideration in most applications. The equilibrium constant for the rupture of a Si-O-Si bond by water to two Si-OH bonds is estimated at 10^{-3} . Since at minimum 3 Si-O-Si bonds must be simultaneously broken under equilibrium conditions to dissociate an organosilane from a surface, in hydrophobic environments the long-term stability is a minor consideration. Depending on the conditions of exposure to water of a hydrophilic coating, the long-term stability can be an important consideration. Selection of a dipodal, polyodal or other network forming silane as the basis for inducing hydrophilicity or as a component in the hydrophilic surface treatment is often obligatory.

Range of Water Interaction with Surfaces

interaction	description	surface example	measurement - parameter
low	superhydrophobic	fluorocarbon	contact angle
	oleophobic		
	lipophobic		
	oleophilic		
	lipophilic		
moderate	hydrophobic	hydrocarbon	water-sliding angle critical surface tension
	polar hydrophilic	polymer oxide surface	heat of immersion
	hygroscopic	polyhydroxylic	water activity
strong	hydrogel film		equilibrium water absorption swell

Reacting with the Substrate

Leaving Groups

The reaction of an organofunctional silane with a surface bearing hydroxyl group results in a substitution reaction at silicon and the formation of the silylated surface where the silicon is covalently attached to the surface via an oxygen linkage. This connection may be formed directly or in the presence of water through a reactive silanol intermediate. In general the reactivity of hydroxylated surfaces with organofunctional silanes decreases in the order: $\text{Si-NR}_2 > \text{Si-Cl} > \text{Si-NH-Si} > \text{Si-O}_2\text{CCH}_3 > \text{Si-OCH}_3 > \text{Si-OCH}_2\text{CH}_3$. An analysis of the relevant bond energies indicates that the formation of the Si-O-surface bond is the driving force for the reaction under dry and aprotic conditions. Secondary factors contributing to the reactivity of organofunctional silanes with a surface are the volatility of the byproducts, the ability of the byproduct to hydrogen bond with the hydroxyls on the surface, the ability of the byproduct to catalyze further reactions, e.g. HCl or acetic acid, and the steric bulk of the groups on the silicon atom.

Although they are not the most reactive organosilanes, the methoxy and ethoxysilanes are the most widely used organofunctional silanes for surface modification. The reasons for this include the fact that they are easily handled and the alcohol byproducts are non-corrosive and volatile. The methoxysilanes are capable of reacting with substrates under dry, aprotic conditions, while the less reactive ethoxysilanes require catalysis for suitable reactivity. The low toxicity of ethanol as a byproduct of the reaction favors the ethoxysilanes in many commercial applications. The vast majority of organofunctional silane surface treatments are performed under conditions in which water is a part of the reaction medium, either directly added or contributed by adsorbed water on the substrate or atmospheric moisture.

Bond Dissociation Energies


Bond	Dissociation Energy (kcal/mole)
$\text{Me}_3\text{Si-NMe}_2$	98
$\text{Me}_3\text{Si-N}(\text{SiMe}_3)_2$	109
$\text{Me}_3\text{Si-Cl}$	117
$\text{Me}_3\text{Si-OMe}$	123
$\text{Me}_3\text{Si-OEt}$	122
$\text{Me}_3\text{Si-OSiMe}_3$	136

Common Leaving Groups


Type	Advantage	Disadvantage
dimethylamine	reactive, volatile byproduct	toxic
hydrogen chloride	reactive, volatile byproduct	corrosive
silazane (NH_3)	volatile	limited availability
methoxy	moderate reactivity, neutral byproduct	moderate toxicity
ethoxy	low toxicity	lower reactivity

Linker Length

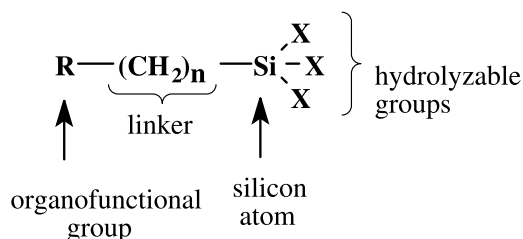An important factor in controlling the effectiveness and properties of a coupled system is the linker between the organic functionality and the silicon atom. The linker length imposes a number of physical property and reactivity limitations. The desirability of maintaining the reactive centers close to the substrate are most important in sensor applications, in heterogeneous catalysis, fluorescent materials and composite systems in which the interfacing components are closely matched in modulus and coefficient of thermal expansion. On the other hand, inorganic surfaces can impose enormous steric constraints on the accessibility of organic functional groups in close proximity. If the linker length is long the functional group has greater mobility and can extend further from the inorganic substrate. This has important consequences if the functional group is expected to react with a single component in a multi-component organic or aqueous phases found in homogeneous and phase transfer catalysis, biological diagnostics or liquid chromatography. Extended linker length is also important in oriented applications such as self-assembled monolayers (SAMs). The typical linker length is three carbon atoms, a consequence of the fact that the propyl group is synthetically accessible and has good thermal stability.







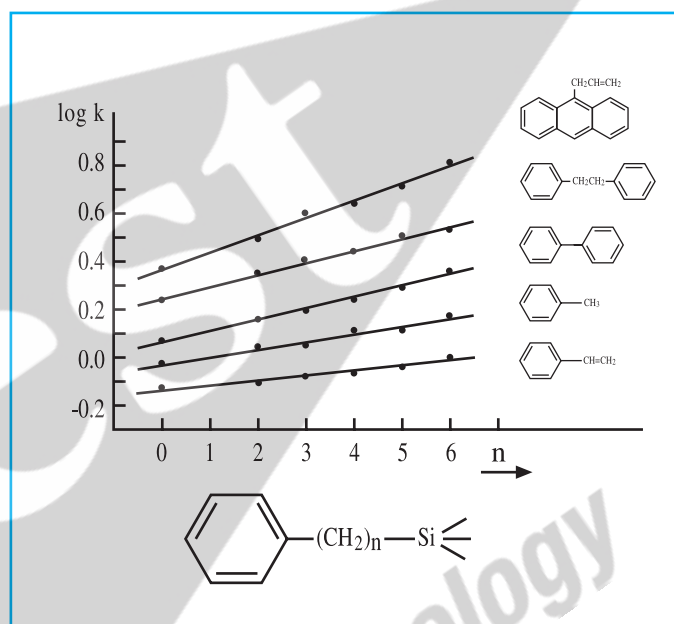Effect of linker length on the separation of aromatic hydrocarbons







T. Den et al, in "Silanes, Surfaces, Interfaces" D. Leyden ed., 1986 p403.

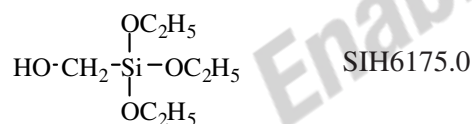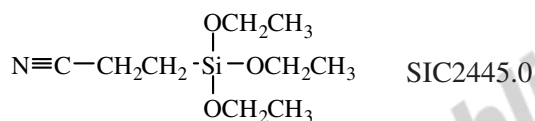Silanes with short linker length



Silanes with extended linker length

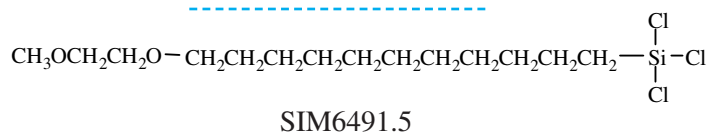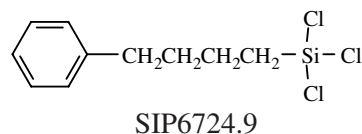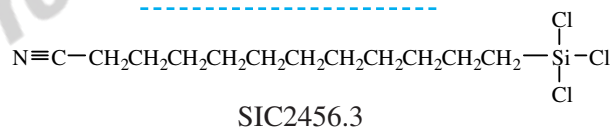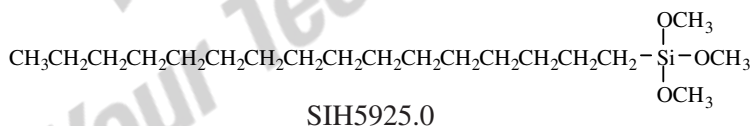

Partition, Orientation and Self-Assembly in Bonded Phases

Chromatography

Octadecyl, cyanopropyl and branched tricocyl silanes provide bonded phases for liquid chromatography. Reverse-phase thin-layer chromatography can be accomplished by treating plates with dodecyltrichlorosilane.

Liquid Crystal Displays

The interphase can also impose orientation of the bulk phase. In liquid crystal displays, clarity and permanence of image are enhanced if the display can be oriented parallel or perpendicular to the substrate. The use of surfaces treated with octadecyl(3-(trimethoxysilyl)propyl) ammonium chloride (perpendicular) or methylaminopropyl-trimethoxysilane (parallel) has eliminated micromachining operations. The oriented crystalline domains often observed in reinforced nylons have also been attributed to orientation effects of the silane in the interphase.

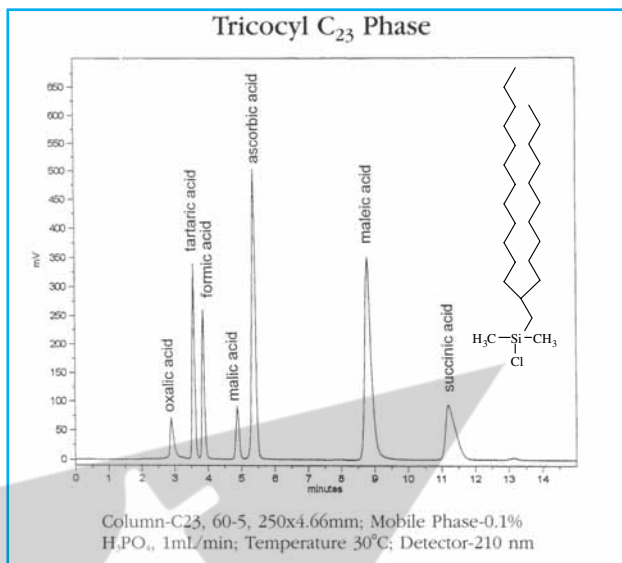
Self-Assembled Monolayers (SAMs)

A Self-Assembled Monolayer (SAM) is a one molecule thick layer of material that bonds to a surface in an ordered way as a result of physical or chemical forces during a deposition process. Silanes can form SAMs by solution or vapor phase deposition processes. Most commonly, chlorosilanes or alkoxy silanes are used and once deposition occurs a chemical (oxane) bond forms with the surface rendering a permanent modification of the substrate. Applications for SAMs include micro-contact printing, soft lithography, dip-pen nanolithography, anti-stiction coatings and orientation layers involved in nanofabrication of MEMs, fluidic microassemblies, semiconductor sensors and memory devices.


Common long chain alkyl silanes used in the formation of SAMs are simple hydrocarbon, fluoroalkyl and end-group substituted silanes. Silanes with one hydrolyzeable group maintain interphase structure after deposition by forming a single oxane bond with the substrate. Silanes with three hydrolyzeable groups form siloxane (silsesquioxane) polymers after deposition, bonding both with each other as well as the substrate. For non-oxide metal substrates, silyl hydrides may be used, reacting with the substrate by a dehydrogenative coupling.

The perpendicular orientation of silanes with C₁₀ or greater length can be utilized in micro-contact printing and other soft lithography methods. Here the silane may effect a simple differential adsorption, or if functionalized have a direct sensor effect.

Normal Phase HPLC of Carboxylic Acids with a C₂₃-Silane Bonded Phase




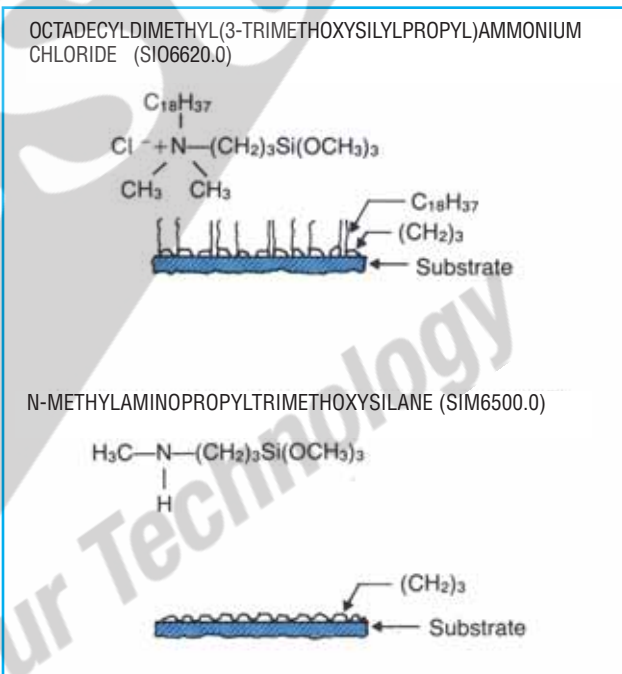Orientation effects of silanes for passive LCDs



F. Kahn., Appl. Phys. Lett. 22, 386, 1973

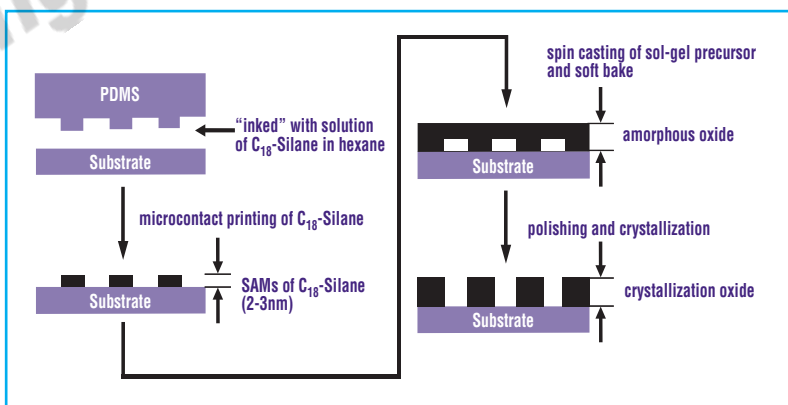Micro-Contact Printing Using SAMs



Modification of Metal Substrates

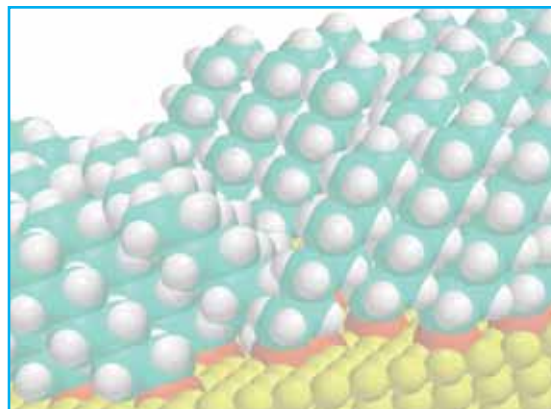
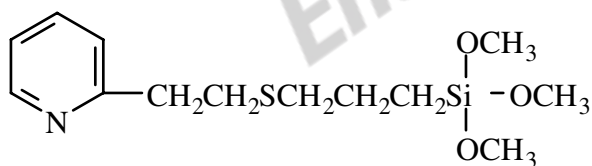
The optimum performance of silanes is associated with siliceous substrates. While the use of silanes has been extended to metal substrates, both the effectiveness and strategies for bonding to these less-reactive substrates vary. Four approaches of bonding to metals have been used with differing degrees of success. In all cases, selecting a dipodal or polymeric silane is preferable to a conventional trialkoxy silane.

Metals that form hydrolytically stable surface oxides, e.g. aluminum, tin, titanium. These oxidized surfaces tend to have sufficient hydroxyl functionality to allow coupling under the same conditions applied to the siliceous substrates discussed earlier.

Metals that form hydrolytically or mechanically unstable surface oxides, e.g. iron, copper, zinc.

These oxidized surfaces tend to dissolve in water leading to progressive corrosion of the substrate or form a passivating oxide layer without mechanical strength. The successful strategies for coupling to these substrates typically involves two or more silanes. One silane is a chelating agent such as a diamine, polyamine or polycarboxylic acid. A second silane is selected which has a reactivity with the organic component and reacts with the first silane by co-condensation. If a functional dipodal or polymeric silane is not selected, 10-20% of a non-functional dipodal silane typically improves bond strength.

Metals that do not readily form oxides, e.g. nickel, gold and other precious metals. Bonding to these substrates requires coordinative bonding, typically a phosphine, sulfur (mercapto), or amine functional silane. A second silane is selected which has a reactivity with the organic component. If a functional dipodal or polymeric silane is not selected, 10-20% of a non-functional dipodal silane typically improves bond strength.




Octylsilane adsorbed on titanium

figure courtesy of
M. Banaszak-Holl

Metals that form stable hydrides, e.g. titanium, zirconium, nickel. In a significant departure from traditional silane coupling agent chemistry, the ability of certain metals to form so-called amorphous alloys with hydrogen is exploited in an analogous chemistry in which hydride functional silanes adsorb and then coordinate with the surface of the metal. Most silanes of this class possess only simple hydrocarbon substitution such as octylsilane. However they do offer organic compatibility and serve to markedly change wet-out of the substrate. Both hydride functional silanes and treated metal substrates will liberate hydrogen in the presence of base or with certain precious metals such as platinum and associated precautions must be taken.

(see p72.)



Coupling Agents for Metals*			
Metal	Class	Screening Candidates	
Copper	Amine	SSP-060	SIT8398.0
Gold	Sulfur	SIT7908.0	SIP6926.2
	Phosphorus	SID4558.0	SIB1091.0
Iron	Amine	SIB1834.0	WSA-7011
	Sulfur	SIB1824.6	SIM6476.0
Tin	Amine	SIB1835.5	
Titanium	Epoxy	SIG5840.0	SIE6668.0
	Hydride	SIU9048.0	
Zinc	Amine	SSP-060	SIT8398.0
	Carboxylate	SIT8402.0	SIT8192.6

*These coupling agents are almost always used in conjunction with a second silane with organic reactivity or a dipodal silane.


Difficult Substrates

Silane coupling agents are generally recommended for applications in which an inorganic surface has hydroxyl groups and the hydroxyl groups can be converted to stable oxane bonds by reaction with the silane. Substrates such as calcium carbonate, copper and ferrous alloys, and high phosphate and sodium glasses are not recommended substrates for silane coupling agents. In cases where a more appropriate technology is not available a number of strategies have been devised which exploit the organic functionality, film-forming and crosslinking properties of silane coupling agents as the primary mechanism for substrate bonding in place of bonding through the silicon atom. These approaches frequently involve two or more coupling agents.

Calcium carbonate fillers and marble substrates do not form stable bonds with silane coupling agents. Applications of mixed silane systems containing a dipodal silane or tetraethoxysilane in combination with an organofunctional silane frequently increases adhesion. The adhesive mechanism is thought to be due to the low molecular weight and low surface energy of the silanes which allows them initially to spread to thin films and penetrate porous structures followed by the crosslinking which results in the formation of a silica-rich encapsulating network. The silica-rich encapsulating network is then susceptible to coupling chemistry comparable to siliceous substrates. Marble and calciferous substrates can also benefit from the inclusion of anhydride-functional silanes which, under reaction conditions, form dicarboxylates that can form salts with calcium ions.

Metals and many metal oxides can strongly adsorb silanes if a chelating functionality such as diamine or dicarboxylate is present. A second organofunctional silane with reactivity appropriate to the organic component must be present. Precious metals such as gold and rhodium form weak coordination bonds with phosphine and mercaptan functional silanes.

High phosphate and sodium content glasses are frequently the most frustrating substrates. The primary inorganic constituent is silica and would be expected to react readily with silane coupling agents. However alkali metals and phosphates not only do not form hydrolytically stable bonds with silicon, but, even worse, catalyze the rupture and redistribution of silicon-oxygen bonds. The first step in coupling with these substrates is the removal of ions from the surface by extraction with deionized water. Hydrophobic dipodal or multipodal silanes are usually used in combination with organofunctional silanes. In some cases polymeric silanes with multiple sites for interaction with the substrate are used. Some of these, such as the polyethylenimine functional silanes can couple to high sodium glasses in an aqueous environment.



Substrates with low concentrations of non-hydrogen bonded hydroxyl groups, high concentrations of calcium, alkali metals or phosphates pose challenges for silane coupling agents.

Removing Surface Impurities

Eliminating non-bonding metal ions such as sodium, potassium and calcium from the surface of substrates can be critical for stable bonds. Substrate selection can be essential. Colloidal silicas derived from tetraethoxysilane or ammonia sols perform far better than those derived from sodium sols. Bulk glass tends to concentrate impurities on the surface during fabrication. Although sodium concentrations derived from bulk analysis may seem acceptable, the surface concentration is frequently orders of magnitude higher. Surface impurities may be reduced by immersion in 5% hydrochloric acid for 4 hours, followed by a deionized water rinse, and then immersion in deionized water overnight followed by drying.

Oxides with high isoelectric points can adsorb carbon dioxide, forming carbonates. These can usually be removed by a high temperature vacuum bake.

Increasing Hydroxyl Concentration

Hydroxyl functionalization of bulk silica and glass may be increased by immersion in a 1:1 mixture of 50% aqueous sulfuric acid : 30% hydrogen peroxide for 30 minutes followed by rinses in D.I. water and methanol and then air drying. Alternately, if sodium ion contamination is not critical, boiling with 5% aqueous sodium peroxodisulfate followed by acetone rinse is recommended¹.

1. K. Shirai et al, J. Biomed. Mater. Res. 53, 204, 2000.

Catalyzing Reactions in Water-Free Environments

Hydroxyl groups without hydrogen bonding react slowly with methoxy silanes at room temperature. Ethoxy silanes are essentially non-reactive. The methods for enhancing reactivity include transesterification catalysts and agents which increase the acidity of hydroxyl groups on the substrate by hydrogen bonding. Transesterification catalysts include tin compounds such as dibutyldiacetytin and titanates such as titanium isopropoxide. Incorporation of transesterification catalysts at 2-3 weight % of the silane effectively promotes reaction and deposition in many instances. Alternatively, amines can be premixed with solvents at 0.01-0.5 weight % based on substrate prior or concurrent to silane addition. Volatile primary amines such as butylamine can be used, but are not as effective as tertiary amines such as benzyldimethylamine or diamines such as ethylenediamine. The more effective amines, however, are more difficult to remove after reaction¹.

1. S. Kanan et al, Langmuir, 18, 6623, 2002.

Hydroxylation by Water Plasma & Steam Oxidation

Various metals and metal oxides including silicon and silicon dioxide can achieve high surface concentrations of hydroxyl groups after exposure to H₂O/O₂ in high energy environments including steam at 1050° and water plasma¹.

1. N. Alcanter et al, in "Fundamental & Applied Aspects of Chemically Modified Surfaces" ed. J. Blitz et al, 1999, Roy. Soc. Chem., p212.

Applying Silanes

Deposition from aqueous alcohol solutions is the most facile method for preparing silylated surfaces. A 95% ethanol-5% water solution is adjusted to pH 4.5-5.5 with acetic acid. Silane is added with stirring to yield a 2% final concentration. Five minutes should be allowed for hydrolysis and silanol formation. Large objects, e.g. glass plates, are dipped into the solution, agitated gently, and removed after 1-2 minutes. They are rinsed free of excess materials by dipping briefly in ethanol. Particles, e.g. fillers and supports, are silylated by stirring them in solution for 2-3 minutes and then decanting the solution. The particles are usually rinsed twice briefly with ethanol. Cure of the silane layer is for 5-10 mins at 110°C or 24 hours at room temperature (<60% relative humidity).

Fig. 1 Reactor for slurry treatment of powders. Separate filtration and drying steps are required.



Deposition from aqueous solution is employed for most commercial fiberglass systems. The alkoxy silane is dissolved at 0.5-2.0% concentration in water. For less soluble silanes, 0.1% of a non-ionic surfactant is added prior to the silane and an emulsion rather than a solution is prepared. The solution is adjusted to pH 5.5 with acetic acid. The solution is either sprayed onto the substrate or employed as a dip bath. Cure is at 110-120°C for 20-30 minutes.

Stability of aqueous silane solutions varies from 2-12 hours for the simple alkyl silanes. Poor solubility parameters limit the use of long chain alkyl and aromatic silanes by this method. Distilled water is not necessary, but water containing fluoride ions must be avoided.

Bulk deposition onto powders, e.g. filler treatment, is usually accomplished by a spray-on method. It assumes that the total amount of silane necessary is known and that sufficient adsorbed moisture is present on the filler to cause hydrolysis of the silane. The silane is prepared as a 25% solution in alcohol. The powder is placed in a high intensity solid mixer, e.g. twin cone mixer with intensifier. The methods are most effective. If the filler is dried in trays, care must be taken to avoid wicking or skinning of the top layer of treated material by adjusting heat and air flow.

Fig. 2 Vacuum tumble dryers can be used for slurry treatment of powders.



Integral blend methods are used in composite formulations. In this method the silane is used as a simple additive. Composites can be prepared by the addition of alkoxy silanes to dry-blends of polymer and filler prior to compounding. Generally 0.2 to 1.0 weight percent of silane (of the total mix) is dispersed by spraying the silane in an alcohol carrier onto a pre-blend. The addition of the silane to non-dispersed filler is not desirable in this technique since it can lead to agglomeration. The mix is dry-blended briefly and then melt compounded. Vacuum devolatilization of byproducts of silane reaction during melt compounding is necessary to achieve optimum properties. Properties are sometimes enhanced by adding 0.5-1.0% of tetrabutyl titanate or benzyldimethylamine to the silane prior to dispersal.

Anhydrous liquid phase deposition of chlorosilanes, methoxysilanes, aminosilanes and cyclic azasilanes is preferred for small particles and nano-featured substrates. Toluene, tetrahydrofuran or hydrocarbon solutions are prepared containing 5% silane. The mixture is refluxed for 12-24 hours with the substrate to be treated. It is washed with the solvent. The solvent is then removed by air or explosion-proof oven drying. No further cure is necessary. This reaction involves a direct nucleophilic displacement of the silane chlorines by the surface silanol. If monolayer deposition is desired, substrates should be predried at 150°C for 4 hours. Bulk deposition results if adsorbed water is present on the substrate. This method is cumbersome for large scale preparations and rigorous controls must be established to ensure reproducible results. More reproducible coverage is obtained with monochlorosilanes.

Chlorosilanes can also be deposited from alcohol solution. Anhydrous alcohols, particularly ethanol or isopropanol are preferred. The chlorosilane is added to the alcohol to yield a 2-5% solution. The chlorosilane reacts with the alcohol producing an alkoxy silane and HCl. Progress of the reaction is observed by halt of HCl evolution. Mild warming of the solution (30-40°C) promotes completion of the reaction. Part of the HCl reacts with the alcohol to produce small quantities of alkyl halide and water. The water causes formation of silanols from alkoxy silanes. The silanols condense on the substrate. Treated substrates are cured for 5-10 mins. at 110°C or allowed to stand 24 hours at room temperature.



Fig. 3 Twin-cone blenders with intensive mixing bars are used for bulk deposition of silanes onto powders.

Applying Silanes

Vapor Phase Deposition

Silanes can be applied to substrates under dry aprotic conditions by chemical vapor deposition methods. These methods favor monolayer deposition. Although under proper conditions almost all silanes can be applied to substrates in the vapor phase, those with vapor pressures >5 torr at 100°C have achieved the greatest number of commercial applications. In closed chamber designs, substrates are supported above or adjacent to a silane reservoir and the reservoir is heated to sufficient temperature to achieve 5mm vapor pressure. Alternatively, vacuum can be applied until silane evaporation is observed. In still another variation the silane can be prepared as a solution in toluene, and the toluene brought to reflux allowing sufficient silane to enter the vapor phase through partial pressure contribution. In general, substrate temperature should be maintained above 50° and below 120° to promote reaction. Cyclic azasilanes deposit the quickest—usually less than 5 minutes. Amine functional silanes usually deposit rapidly (within 30 minutes) without a catalyst. The reaction of other silanes requires extended reaction times, usually 4-24 hours. The reaction can be promoted by addition of catalytic amounts of amines.

Spin-On

Spin-On applications can be made under hydrolytic conditions which favor maximum functionalization and polylayer deposition or dry conditions which favor monolayer deposition. For hydrolytic deposition 2-5% solutions are prepared (see deposition from aqueous alcohol). Spin speed is low, typically 500 rpm. Following spin-deposition a hold period of 3-15 minutes is required before rinse solvent. Dry deposition employs solvent solutions such as methoxypropanol or ethyleneglycol monoacetate (EGMA). Aprotic systems utilize toluene or THF. Silane solutions are applied at low speed under a nitrogen purge. If strict monolayer deposition is preferred, the substrate should be heated to 50°. In some protocols, limited polylayer formation is induced by spinning under an atmospheric ambient with 55% relative humidity.

Spray application

Formulations for spray applications vary widely depending on end-use. They involve alcohol solutions and continuously hydrolyzed aqueous solutions employed in architectural and masonry applications. The continuous hydrolysis is effected by feeding mixtures of silane containing an acid catalyst such as acetic acid into a water stream by means of a venturi (aspirator). Stable aqueous solutions (see water-borne silanes), mixtures of silanes with limited stability (4-8 hours) and emulsions are utilized in textile and fiberglass applications. Complex mixtures with polyvinyl acetates or polyesters enter into the latter applications as sizing formulations.

Figure 4.
Apparatus for vapor phase silylation.

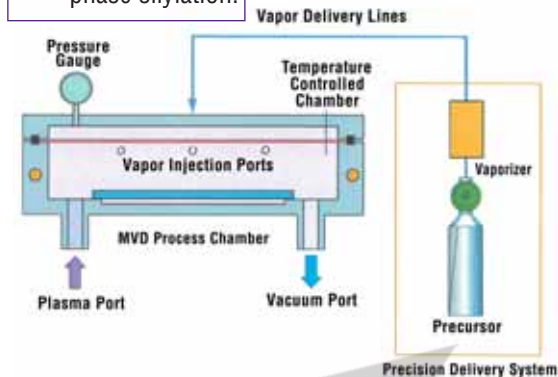



Figure 5.
Spin-coater for deposition on wafers.



Figure 6.
Spray application of silanes on large structures.



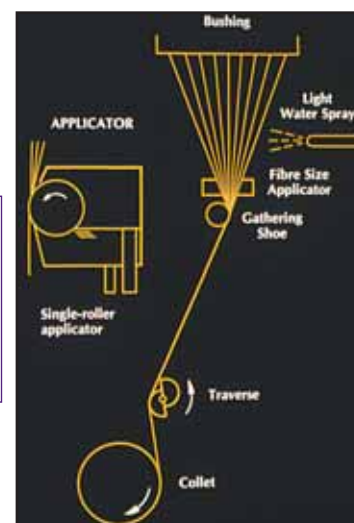Figure 7.
Spray & contact roller application of silanes on fiberglass.



Hydrophobic Silane Selection Guide

Hydrophobic silanes employed in surface modification form the following major categories:

Methyl-Silanes.	20
Linear Alkyl-Silanes	22
Branched Alkyl-Silanes.	24
Aromatic-Silanes.	26
Fluorinated Alkyl-Silanes	28
Dialkyl-Silanes	28

Methyl-Silanes very hydrophobic, hydrolyzates stable to 425°C, acceptable performance to 600°C reported, volatile

3 Hydrolyzeable Groups

Hydrolyzeable Groups	Product Code	Product Name
chloro	SIM6520.0	methyltrichlorosilane
methoxy	SIM6560.0	methyltrimethoxysilane
ethoxy	SIM6555.0	methyltriethoxysilane
propoxy	SIM6579.0	methyltri-n-propoxysilane
methoxyalkoxy	SIM6585.0	methyltris(methoxyethoxy)silane
acetoxy	SIM6519.0	methyltriacetoxysilane
dimethylamine	SIT8712.0	tris(dimethylamino)methylsilane
other amine	SIT8710.0	tris(cyclohexylamino)methylsilane
silazane (NH)		
oxime	SIM6590.0	methyltris(methylethylketoximino)silane

Methyl-SiloxanylSilanes

3 Hydrolyzeable Groups

Hydrolyzeable Groups	Product Code	Product Name
2 silicon atom compounds		
chloro	SIT8572.6	trimethylsiloxytrichlorosilane
ethoxy		
acetoxy		
3 silicon atom compounds		
chloro		
methoxy		
ethoxy		
chloro		
oligomeric polysiloxanes		
chloro	SID4236.0	dimethyltetramethoxydisiloxane
methoxy		
ethoxy		
amine/silazane		
silanol		
selected specialties		

Fumed silica treated with hexamethyldisilazane floats on water.



2 Hydrolyzeable Groups

1 Hydrolyzeable Group

Product Code	Product Name
SID4120.0	dimethyldichlorosilane
SID4123.0	dimethyldimethoxysilane
SID4121.0	dimethyldiethoxysilane
SID4076.0	dimethyldiacetoxysilane
SIB1072.0	bis(dimethylamino)dimethylsilane
SIB1068.0	bis(diethylamino)dimethylsilane
SIH6102.0	hexamethylcyclotrisilazane


Product Code	Product Name
SIT8510.0	trimethylchlorosilane
SIT8566.0	trimethylmethoxysilane
SIT8515.0	trimethylethoxysilane
SIT8568.0	trimethyl-n-propoxysilane
SIM6492.8	methoxypropoxytrimethylsilane
SIA0110.0	acetoxymethyltrimethylsilane
SID3605.0	dimethylaminotrimethylsilane
SID3398.0	diethylaminotrimethylsilane
SIH6110.0	hexamethyldisilazane

2 Hydrolyzeable Groups

1 Hydrolyzeable Group

Product Code	Product Name
SID3372.0	dichlorotetramethyldisiloxane
SIT7534.0	tetramethyldiethoxydisiloxane
SID3360.0	dichlorohexamethyltrisiloxane
SID3394.0	1,5-diethoxyhexamethyltrisiloxane
SIB1837.0	bis(trimethylsiloxy)dichlorosilane
DMS-K05	chlorine terminated polydimethylsiloxane
DMS-XM11	methoxy terminated polydimethylsiloxane
DMS-XE11	ethoxy terminated polydimethylsiloxane
DMS-N05	dimethylamine terminated polydimethylsiloxane
DMS-S12	silanol terminated polydimethylsiloxane

Product Code	Product Name
SIP6717.0	pentamethylacetoxydisiloxane
SIB1843.0	bis(trimethylsiloxy)methylmethoxysilane
SID4125.0	dimethylethoxysilane
SIT8719.5	[tris(trimethylsiloxy)silylethyl]dimethylchlorosilane

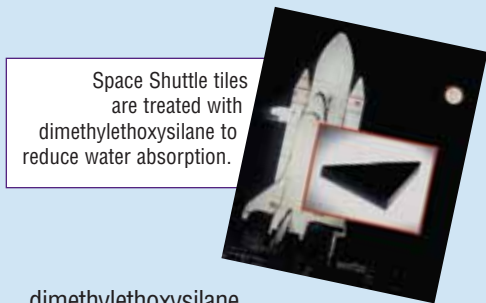

Hydrophobic Silane Selection Guide

Linear Alkyl-Silanes

3 Hydrolyzeable Groups

	Hydrolyzeable Groups	Product Code	Product Name
C₂	hydrophobic, treatment for microporous mineral powders used as fillers for plastics		
	chloro	SIE4901.0	ethyltrichlorosilane
	methoxy	SIE4901.4	ethyltrimethoxysilane
	ethoxy	SIE4901.2	ethyltriethoxysilane
C₃	hydrophobic, treatment for microporous mineral powders used as fillers for plastics		
	acetoxo	SIE4899.0	ethyltriacetoxysilane
	chloro	SIP6915.0	propyltrichlorosilane
	methoxy	SIP6918.0	propyltrimethoxysilane
C₄	hydrophobic, treatment for microporous mineral powders used as fillers for plastics		
	ethoxy	SIP6917.0	propyltriethoxysilane
	amine/silazane		
	moderate hydrophobicity, penetrates microporous structures, minimal organic compatibility		
C₅	chloro	SIB1982.0	n-butyltrichlorosilane
	methoxy	SIB1988.0	n-butyltrimethoxysilane
C₅	amine/silazane		
	moderate hydrophobicity with minimal organic compatibility		
C₅	chloro	SIP6720.0	pentyltrichlorosilane
	ethoxy	SIP6720.2	pentyltriethoxysilane
C₆	moderate hydrophobicity with moderate organic compatibility		
	chloro	SIH6167.0	hexyltrichlorosilane
	methoxy	SIH6168.5	hexyltrimethoxysilane
	ethoxy	SIH6167.5	hexyltriethoxysilane
C₇	moderate hydrophobicity with moderate organic compatibility		
	chloro	SIH5846.0	heptyltrichlorosilane
C₈	hydrophobic with moderate organic compatibility - generally most economical		
	chloro	SIO6713.0	octyltrichlorosilane
	methoxy	SIO6715.5	octyltrimethoxysilane
	ethoxy	SIO6715.0	octyltriethoxysilane
	amine silazane (NH)		
C₁₀	hydrophobic, concentrates on surface of microporous structures		
	chloro	SID2663.0	decyltrichlorosilane
C₁₁	hydrophobic, concentrates on surface of microporous structures, forms SAMs		
	ethoxy	SID2665.0	decyltriethoxysilane
C₁₁	hydrophobic, concentrates on surface of microporous structures, forms SAMs		
	chloro	SIU9050.0	undecyltrichlorosilane
C₁₂	hydrophobic, concentrates on surface of microporous structures, forms SAMs		
	chloro	SID4630.0	dodecyltrichlorosilane
C₁₂	hydrophobic, concentrates on surface of microporous structures, forms SAMs		
	ethoxy	SID4632.0	dodecyltriethoxysilane
C₁₄	hydrophobic, concentrates on surface of microporous structures, forms SAMs		
	chloro	SIT7093.0	tetradecyltrichlorosilane
C₁₆	forms hydrophobic and oleophilic coatings, liquid at room temperature, forms SAMs		
	chloro	SIH5920.0	hexadecyltrichlorosilane
	methoxy	SIH5925.0	hexadecyltrimethoxysilane
	ethoxy	SIH5922.0	hexadecyltriethoxysilane
C₁₈	forms hydrophobic and oleophilic coatings allowing full miscibility with parafinic materials, forms SAMs		
	chloro	SIO6640.0	octadecyltrichlorosilane
	methoxy	SIO6645.0	octadecyltrimethoxysilane
	ethoxy	SIO6642.0	octadecyltriethoxysilane
	amine proprietary	SIS6952.0/PPI-GC18	Siliclad®/Glassclad® 18
C₂₀	forms hydrophobic and oleophilic coatings, solid at room temperature		
	chloro	SIE4661.0	eicosyltrichlorosilane
C₂₀₋₂₄	forms hydrophobic and oleophilic coatings, solid at room temperature		
	chloro	SID4621.0	docosyltrichlorosilane blend
C_{26-C₃₄}	forms hydrophobic and oleophilic coatings, solid at room temperature		
	chloro	SIT8048.0	triacontyltrichlorosilane blend

2 Hydrolyzeable Groups

1 Hydrolyzeable Group

Product Code

Product Name

Product Code

Product Name

SIE4896.0

ethylmethyldichlorosilane

SIE4892.0

ethyldimethylchlorosilane

SIP6912.0
SIP6914.0

propylmethyldichlorosilane
propylmethyldimethoxysilane

SIP6910.0
SIP6911.0

SID4591.0

propyldimethylchlorosilane
propyldimethylmethoxysilane

dipropyltetramethyldisilazane

SIB1934.0

n-butyldimethylchlorosilane

SIB1937.0

n-butyldimethyl(dimethylamino)silane

Long chain alkylsilanes are processing additives for crosslinked polyethylene (XLPE) used in wire and cable.

SIH6165.6

hexylmethyldichlorosilane

SIH5845.0

heptylmethyldichlorosilane

SIO6712.0

octylmethyldichlorosilane

SIO6711.0
SIO6711.1

octyldimethylchlorosilane
octyldimethylmethoxysilane

SIO6712.2

octylmethyldiethoxysilane

SIO6711.3
SID4404.0

octyldimethyl(dimethylamino)silane
dioctyltetramethyldisilazane



SID2662.0

decylmethyldichlorosilane

SID2660.0

decyldimethylchlorosilane


Surface conductivity of glass substrates is reduced by application of hydrophobic coatings. Surface arc-tracking is eliminated on fluorescent light bulbs.

SID4628.0
SID4629.0

dodecylmethyldichlorosilane
dodecylmethyldiethoxysilane

SID4627.0

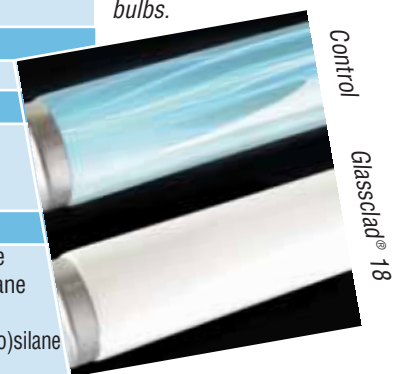dodecyldimethylchlorosilane



SIO6625.0
SIO6629.0
SIO6627.0

octadecylmethyldichlorosilane
octadecylmethyldimethoxysilane
octadecylmethyldiethoxysilane

SIO6615.0
SIO6618.0

SIO6617.0

octadecyldimethylchlorosilane
octadecyldimethylmethoxysilane

octadecyldimethyl(dimethylamino)silane

SID4620.0

docosylmethyldichlorosilane blend

SIT8045.0


triacontyldimethylchlorosilane blend

Hydrophobic Silane Selection Guide

Branched and Cyclic Alkyl-Silanes

3 Hydrolyzeable Groups

	Hydrolyzeable Groups	Product Code	Product Name
C₃	chloro		
C₄	chloro methoxy ethoxy chloro	SI16453.0 SI16453.7 SI16453.5 SIB1985.0	isobutyltrichlorosilane isobutyltrimethoxysilane isobutyltriethoxysilane t-butyltrichlorosilane
C₅	chloro methoxy	SIC2555.0 SIC2557.0	cyclopentyltrichlorosilane cyclopentyltrimethoxysilane
C₆	chloro chloro chloro methoxy	SID4069.0 SIT7906.6 SIC2480.0 SIC2482.0	(3,3-dimethylbutyl)trichlorosilane thexyltrichlorosilane cyclohexyltrichlorosilane cyclohexyltrimethoxysilane
C₇	norbornene chloro chloro	SIB0997.0 SIC2470.0	bicycloheptyltrichlorosilane (cyclohexylmethyl)trichlorosilane
C₈	chloro methoxy chloro	SI16457.0 SI16458.0 SIC2490.0	isooctyltrichlorosilane isooctyltrimethoxysilane cyclooctyltrichlorosilane
C₁₀			
C₁₂			
		SIA0325.0	adamantylethyltrichlorosilane
C₁₆		SIT8162.4	7-(trichlorosilylmethyl)pentadecane
C₁₈	silahydrocarbon chloro	SID4401.5	(di-n-octylmethylsilyl)ethyltrichlorosilane
C₂₄	chloro		
C₂₈	chloro	SIT8162.0	13-(trichlorosilylmethyl)heptacosane



2 Hydrolyzeable Groups

1 Hydrolyzeable Group

Product Code

Product Name

Product Code

Product Name

SII6463.0

isopropylmethyldichlorosilane

SII6462.0

isopropyldimethylchlorosilane

SII6452.8

isobutylmethyldimethoxysilane

SII6452.5

isobutyldimethylchlorosilane

SIB1972.2

t-butylmethyldichlorosilane

SIB1935.0

t-butyldimethylchlorosilane

Isobutyltriethoxysilane solutions in ethanol are applied by spray to protect architecture.



SIC2468.0
SIC2469.0

cyclohexylmethyldichlorosilane
cyclohexylmethyldimethoxysilane

SID4065.0
SIT7906.0
SIC2465.0

(3,3-dimethylbutyl)dimethylchlorosilane
hexyldimethylchlorosilane
cyclohexyldimethylchlorosilane

SIB0994.0

bicycloheptyldimethylchlorosilane

SII6456.6

isooctyldimethylchlorosilane

SID4074.0

(dimethylchlorosilyl)methylpinane

SID4401.0

(di-n-octylmethylsilyl)ethyldimethylchlorosilane

SIC2266.5

11-(chlorodimethylsilylmethyl)tricosane

SIC2266.0

13-(chlorodimethylsilylmethyl)heptacosane

Gelest
Enabling Your Technology

Hydrophobic Silane Selection Guide

Phenyl- and Phenylalkyl-Silanes

3 Hydrolyzeable Groups

Spacer Atoms	Hydrolyzeable Groups	Product Code	Product Name
spacer atoms = 0			
	chloro	SIP6810.0	phenyltrichlorosilane
	methoxy	SIP6822.0	phenyltrimethoxysilane
	ethoxy	SIP6821.0	phenyltriethoxysilane
	acetoxo	SIP6790.0	phenyltriacetoxysilane
	oxime/amine	SIP6826.5	phenyltris(methylethylketoximino)silane
spacer atoms = 1			
	chloro	SIB0970.0	benzyltrichlorosilane
	ethoxy	SIB0971.0	benzyltriethoxysilane
	chloro	SIP6813.0	1-phenyl-1-trichlorosilylbutane
spacer atoms = 2			
	chloro	SIP6722.0	phenethyltrichlorosilane
	methoxy	SIP6722.6	phenethyltrimethoxysilane
	amine/silazane		
spacer atoms = 3			
	chloro		
spacer atoms = 4			
	chloro	SIP6724.9	4-phenylbutyltrichlorosilane
	chloro	SIP6723.3	phenoxypropyltrichlorosilane
spacer atoms > 4			
	chloro	SIP6736.4	phenoxyundecyltrichlorosilane
	chloro	SIP6723.4	phenylhexyltrichlorosilane

Substituted Phenyl- and Phenylalkyl-Silanes

spacer atoms = 0			
	chloro	SIT8040.0	p-tolyltrichlorosilane
	methoxy	SIT8042.0	p-tolyltrimethoxysilane
spacer atoms = 2			
	methyl/chloro		
	ethyl/methoxy	SIE4897.5	ethylphenethyltrimethoxysilane
	t-butyl/chloro	SIB1973.0	p-(t-butyl)phenethyltrichlorosilane
spacer atoms = 3			
	chloro	SIM6492.5	3-(p-methoxyphenyl)propyltrichlorosilane

Naphthyl-Silanes

	methoxy	SIN6597.0	1-naphthyltrimethoxysilane
	chloro	SIN6596.0	(1-naphthylmethyl)trichlorosilane

Specialty Aromatic- Silanes

spacer atoms = 0			
	chloro		
spacer atoms = 4			
	chloro		

<i>2 Hydrolyzeable Groups</i>		<i>1 Hydrolyzeable Group</i>	
Product Code	Product Name	Product Code	Product Name
SIP6738.0	phenylmethylchlorosilane	SIP6728.0	phenyldimethylchlorosilane
SIP6740.0	phenylmethyldimethoxysilane		
SIP6739.0	phenylmethyldiethoxysilane	SIP6728.4	phenyldimethylethoxysilane
SIP6736.8	phenylmethylbis(dimethylamino)silane		
		SIB0962.0	benzyltrimethylchlorosilane
SIP6738.5	1-phenyl-1-methylchlorosilylbutane		
SIP6721.5	phenethylmethylchlorosilane	SP6721.0	phenethyltrimethylchlorosilane
		SIP6721.2	phenethyltrimethyl(dimethylamino)silane
SIP6744.0	(3-phenylpropyl)methylchlorosilane	SIP6743.0	(3-phenylpropyl)trimethylchlorosilane
SIP6724.8	4-phenylbutylmethylchlorosilane	SIP6724.7	4-phenylbutyltrimethylchlorosilane
SIP6723.25	phenoxypropylmethylchlorosilane	SIP6723.2	phenoxypropyltrimethylchlorosilane
SIT8035.0	p-tolylmethylchlorosilane	SIT8030.0	p-tolyltrimethylchlorosilane
SIM6511.0	(p-methylphenethyl)methylchlorosilane		
		SIB1972.5	p-(t-butyl)phenethyltrimethylchlorosilane
SIM6492.4	3-(p-methoxyphenyl)propylmethylchlorosilane		
		SIP6723.0	m-phenoxyphenyltrimethylchlorosilane
		SIN6598.0	p-nonylphenoxypropyltrimethylchlorosilane

Hydrophobic Silane Selection Guide

Fluorinated Alkyl-Silanes

3 Hydrolyzeable Groups

	Hydrolyzeable Groups	Product Code	Product Name
C ₃	chloro	SIT8371.0	(3,3,3-trifluoropropyl)trichlorosilane
	methoxy amine/silazane	SIT8372.0	(3,3,3-trifluoropropyl)trimethoxysilane
C ₆	chloro	SIN6597.6	nonafluorohexyltrichlorosilane
	methoxy	SIN6597.7	nonafluorohexyltrimethoxysilane
	ethoxy	SIN6597.65	nonafluorohexyltriethoxysilane
	amino	SIN6597.4	nonafluorohexyltris(dimethylamino)silane
C ₈	chloro	SIT8174.0	(tridecafluoro-1,1,2,2-tetrahydrooctyl)trichlorosilane
	methoxy	SIT8176.0	(tridecafluoro-1,1,2,2-tetrahydrooctyl)trimethoxysilane
	ethoxy	SIT8175.0	(tridecafluoro-1,1,2,2-tetrahydrooctyl)triethoxysilane
C ₁₀	chloro	SIH5841.0	(heptadecafluoro-1,1,2,2-tetrahydrodecyl)trichlorosilane
	methoxy	SIH5841.5	(heptadecafluoro-1,1,2,2-tetrahydrodecyl)trimethoxysilane
	ethoxy	SIH5841.2	(heptadecafluoro-1,1,2,2-tetrahydrodecyl)triethoxysilane

DiAlkyl Silanes

2 Hydrolyzeable Groups

Highest Carbon #	Next Carbon #	Hydrolyzeable Groups	Product Code	Product Name
C ₂	C ₂	chloro	SID3402.0	diethyldichlorosilane
		ethoxy	SID3404.0	diethyldiethoxysilane
C ₃	C ₃	chloro	SID3537.0	diisopropyldichlorosilane
		methoxy	SID3538.0	diisopropyldimethoxysilane
C ₄	C ₄	chloro	SID3203.0	di-n-butyl-dichlorosilane
		methoxy	SID3214.0	di-n-butyl-dimethoxysilane
		methoxy	SID3530.0	diisobutyl-dimethoxysilane
		ethoxy	SID3528.0	diisobutyl-diethoxysilane
C ₄	C ₃	methoxy	SI6452.6	isobutylisopropyldimethoxysilane
C ₅	C ₅	chloro	SID3390.0	dicyclopentyl-dichlorosilane
		methoxy	SID3391.0	dicyclopentyl-dimethoxysilane
C ₆	C ₆	chloro	SID3510.0	di-n-hexyl-dichlorosilane
		chloro	SID3382.0	dicyclohexyl-dichlorosilane
C ₈	C ₈	chloro	SID4400.0	di-n-octyl-dichlorosilane

2 Hydrolyzeable Groups

Product Code Product Name

SIT8369.0 (3,3,3-trifluoropropyl)methyldichlorosilane
 SIT8370.0 (3,3,3-trifluoropropyl)methyldimethoxysilane

SIN6597.5 nonafluorohexylmethyldichlorosilane

SIT8172.0 (tridecafluoro-1,1,2,2-tetrahydrooctyl)methyldichlorosilane

SH5840.6 (heptadecafluoro-1,1,2,2-tetrahydrodecyl)methyldichlorosilane

1 Hydrolyzeable Group

Product Code Product Name

SIT8364.0 (3,3,3-trifluoropropyl)dimethylchlorosilane

SIB1828.4 bis(trifluoropropyl)tetramethyldisilazane

SIN6597.3 nonafluorohexyldimethylchlorosilane

SIT8170.0 (tridecafluoro-1,1,2,2-tetrahydrooctyl)dimethylchlorosilane











SIH5840.4 (heptadecafluoro-1,1,2,2-tetrahydrodecyl)dimethylchlorosilane



Pigments treated with hydrophobic silanes resist agglomeration in highly polar vehicle and film-forming compositions such as those used in nail polish.

Hydrophobic Silane Properties

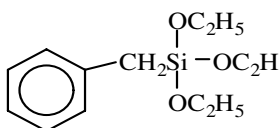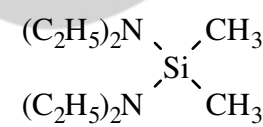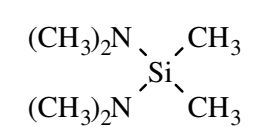Conventional Surface Bonding









	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SIA0110.0 ACETOXYTRIMETHYLSILANE <i>O</i> -TRIMETHYLSILYLACETATE C ₅ H ₁₂ O ₂ Si vapor pressure, 30°: 35mm HYDROLYTIC SENSITIVITY: 4 no reaction under neutral conditions [2754-27-0] TSCA HMIS: 3-4-1-X	132.23	103-4° (-32°)mp flashpoint: 4°C (39°F)	0.891	1.3890
	SIA0325.0 ADAMANTYLETHYLTRICHLOROSILANE C ₁₂ H ₁₉ Cl ₃ Si contains up to 5% α -isomer forms silica bonded phases for reverse phase chromatography ¹ . 1. Yang et al, Anal. Chem., 59, 2750, 1988 HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [37843-11-1] TSCA HMIS: 3-1-1-X	297.73	135°/3 (36-7°)mp flashpoint: 155°C (310°F)	1.2204	1.5135
	SIB0962.0 BENZYL DIMETHYLCHLOROSILANE C ₉ H ₁₃ ClSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [1833-31-4] TSCA HMIS: 3-2-1-X	184.74	75-6°/15 flashpoint: 73°C (163°F)	0.949	1.5040
	SIB0970.0 BENZYLTRICHLOROSILANE C ₇ H ₇ Cl ₃ Si dipole moment: 1.78 HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [770-10-5] TSCA HMIS: 3-2-1-X	225.58	140-2°/10 TOXICITY- oral rat, LD50: 2830mg/kg flashpoint: 87°C (189°F)	1.288	1.527
	SIB0971.0 BENZYL TRIETHOXY SILANE C ₁₃ H ₂₂ O ₃ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [2549-99-7] TSCA HMIS: 2-1-0-X	254.40	148°/26 flashpoint: 127°C (260°F)	0.986	1.4628 ²⁵
	SIB0994.0 2-(BICYCLOHEPTYL)DIMETHYLCHLOROSILANE C ₉ H ₁₇ ClSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [117046-42-1] HMIS: 3-2-1-X	188.77	52-5°/1 flashpoint: 87° (189°F)	0.99	
	SIB0997.0 2-(BICYCLOHEPTYL)TRICHLOROSILANE C ₇ H ₁₁ Cl ₃ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18245-29-9] TSCA HMIS: 3-2-1-X	229.61	63-4°/4.5 flashpoint: 83°C (181°F)	1.2678	1.4919
	SIB1068.0 BIS(DIETHYLAMINO)DIMETHYLSILANE C ₁₀ H ₂₆ N ₂ Si silylates diamines to cyclic diaminosilanes ¹ . 1. E. Schwartz et al, J. Org. Chem., 50, 5469, 1985. HYDROLYTIC SENSITIVITY: 8 Si-NR reacts rapidly with moisture, water, protic solvents [4669-59-4] TSCA HMIS: 3-3-1-X	202.42	192-5° flashpoint: 35°C (95°F)	0.826	1.435
	SIB1072.0 BIS(DIMETHYLAMINO)DIMETHYLSILANE C ₆ H ₁₈ N ₂ Si couples silanol-terminated siloxanes HYDROLYTIC SENSITIVITY: 8 Si-NR reacts rapidly with moisture, water, protic solvents [3768-58-9] TSCA HMIS: 3-4-1-X	146.31	128-9° (-98°)mp flashpoint: -3°C (27°F)	0.810	1.4169 ²²
	SIB1828.4 BIS(TRIFLUOROPROPYL)TETRAMETHYL-DISILAZANE, 95% C ₁₀ H ₂₁ F ₆ NSi ₂ fluorinated blocking agent HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [39482-87-6] TSCA HMIS: 2-2-1-X	325.45	76-8°/10 flashpoint: 78°C (173°F)	1.110	1.3860

HYDROPHOBIC












COMMERCIAL












COMMERCIAL

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
$\begin{array}{c} \text{CH}_3 \quad \text{Cl} \quad \text{CH}_3 \\ \quad \quad \\ \text{CH}_3-\text{Si}-\text{O}-\text{Si}-\text{O}-\text{Si}-\text{CH}_3 \\ \quad \quad \\ \text{CH}_3 \quad \text{Cl} \quad \text{CH}_3 \end{array}$	SIB1837.0 BIS(TRIMETHYLSILOXY)DICHLOROSILANE 3,3-DICHLOROHEXAMETHYLTRISILOXANE C ₆ H ₁₈ Cl ₂ O ₂ Si ₃ [2750-44-9] HMIS: 3-2-1-X	277.37	173° (-53°)mp vapor pressure, 57°: 12mm 25g/\$96.00	1.0017	1.3983
$\begin{array}{c} \text{CH}_3 \\ \\ \text{H}_3\text{C}-\text{Si}-\text{CH}_3 \\ \\ \text{H}_3\text{C}-\text{Si}-\text{O}-\text{CH}_3 \\ \\ \text{O} \\ \\ \text{H}_3\text{C}-\text{Si}-\text{CH}_3 \\ \\ \text{CH}_3 \end{array}$	SIB1843.0 BIS(TRIMETHYLSILOXY)METHYMETHOXY SILANE METHOXYHEPTAMETHYLTRISILOXANE C ₈ H ₂₄ O ₃ Si ₃ [7671-19-4] HMIS: 3-2-1-X	252.53	82°/47 25g/\$68.00	0.862	1.38832 ²⁵
$\begin{array}{c} \text{OSi}(\text{CH}_3)_3 \\ \\ \text{CH}_3\text{C}=\text{NSi}(\text{CH}_3)_3 \end{array}$	SIB1846.0 N,O-BIS(TRIMETHYLSILYL)ACETAMIDE C ₈ H ₂₁ NOSi ₂ BSA versatile blocking agent. flashpoint: 42°C (108°F) TOXICITY - oral rat, LD50: 1580mg/kg HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [10416-59-8] TSCA HMIS: 3-3-1-X	203.43	71-3°/35 (-24°)mp flashpoint: 42°C (108°F) TOXICITY - oral rat, LD50: 1580mg/kg 25g/\$16.00 100g/\$52.00 2kg/\$560.00	0.832	1.418
$\begin{array}{c} \text{OSi}(\text{CH}_3)_3 \\ \\ \text{CF}_3\text{C}=\text{NSi}(\text{CH}_3)_3 \end{array}$	SIB1876.0 BIS(TRIMETHYLSILYL)TRIFLUOROACETAMIDE BSTFA C ₈ H ₁₈ F ₃ NOSi ₂ silylation reagent for preparing derivatives of amino acids ¹ . 1. D. Stalling et al, Biochem. Biophys., Res. Comm., 37, 616, 1968. HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [25561-30-2] TSCA HMIS: 3-3-1-X	257.40	45-50°/15 (-10°)mp flashpoint: 24°C (75°F) 25g/\$49.00 100g/\$152.00 2kg/\$1360.00	0.969	1.3840
$\begin{array}{c} \text{CH}_3 \\ \\ \text{CH}_3\text{CH}_2\text{CH}_2\text{CH}_2\text{Si}-\text{Cl} \\ \\ \text{CH}_3 \end{array}$	SIB1934.0 n-BUTYLDIMETHYLCHLOROSILANE C ₆ H ₁₅ ClSi forms bonded phases for HPLC HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [1000-50-6] TSCA HMIS: 3 -3-1-X	150.72	138° flashpoint: 39°C (103°F) 25g/\$43.00 100g/\$140.00	0.8751	1.4205
$\begin{array}{c} \text{CH}_3 \quad \text{Me} \\ \quad \\ \text{H}_3\text{C}-\text{C}-\text{Si}-\text{Cl} \\ \quad \\ \text{CH}_3 \quad \text{Me} \end{array}$	SIB1935.0 t-BUTYLDIMETHYLCHLOROSILANE C ₆ H ₁₅ ClSi vapor pressure, 100°: 476mm flashpoint: 22°C (73°F) silylation reagent - derivatives resistant to Grignards, alkyl lithium compounds etc. blocking agent widely used in prostaglandin synthesis HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18162-48-6] TSCA HMIS: 3-4-1-X	150.72	124-6° (87-90°)mp flashpoint: 22°C (73°F) 25g/\$36.00 100g/\$117.00 2kg/\$720.00	0.83	
$\begin{array}{c} \text{CH}_3 \\ \\ \text{CH}_3\text{CH}_2\text{CH}_2\text{CH}_2\text{Si}-\text{N}(\text{CH}_3)_2 \\ \\ \text{CH}_3 \end{array}$	SIB1937.0 n-BUTYLDIMETHYL(DIMETHYLAMINO)SILANE C ₈ H ₂₁ NSi highly reactive reagent for bonded phases without acidic byproduct HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [181231-67-4] TSCA-L HMIS: 3-3-1-X	159.35	47-9°/12 flashpoint: 26°C (79°F) 10g/\$38.00 50g/\$152.00	0.772	1.4220
$\begin{array}{c} \text{CH}_3 \quad \text{OCH}_3 \quad \text{CH}_3 \\ \quad \quad \\ \text{H}_3\text{C}-\text{C}-\text{Si}-\text{CH} \\ \quad \quad \\ \text{CH}_3 \quad \text{OCH}_3 \quad \text{CH}_3 \end{array}$	SIB1971.0 t-BUTYLISOPROPYLDIMETHOXYSILANE C ₉ H ₂₂ O ₂ Si HMIS: 3-2-1-X	190.36	75°/20 1.0g/\$126.00	0.871	1.4189
$\begin{array}{c} \text{CH}_3\text{CH}_2\text{CH}_2\text{CH}_2-\text{Si}-\text{Cl} \\ \\ \text{H}_3\text{C} \end{array}$	SIB1972.0 n-BUTYLMETHYLDICHLOROSILANE C ₅ H ₁₂ Cl ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [18147-23-4] TSCA HMIS: 3-3-1-X	171.14	148° flashpoint: 30°C (86°F) 10g/\$35.00	1.0424	1.4312
$\begin{array}{c} \text{CH}_3 \quad \text{CH}_3 \\ \quad \\ \text{H}_3\text{C}-\text{C}-\text{Si}-\text{Cl} \\ \quad \\ \text{CH}_3 \quad \text{Cl} \end{array}$	SIB1972.2 t-BUTYLMETHYLDICHLOROSILANE C ₅ H ₁₂ Cl ₂ Si flashpoint: 26°C (79°F) HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [18147-18-7] HMIS: 3-3-1-X	171.14	130-2° (88-90°)mp flashpoint: 26°C (79°F) 5.0g/\$89.00		







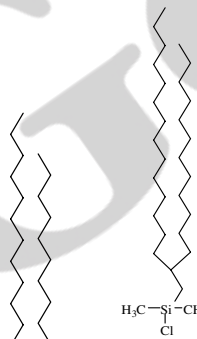



	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SIB1972.5 p-(t-BUTYL)PHENETHYLDIMETHYLCHLORO-SILANE contains ~5% meta isomer C ₁₄ H ₂₃ ClSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [93502-75-1] HMIS: 3-2-1-X	254.87	122-3°/2	0.95	
			25g/\$78.00		
	SIB1973.0 p-(t-BUTYL)PHENETHYLTRICHLOROSILANE C ₁₂ H ₁₇ Cl ₃ Si mixed isomers for HPLC bonded phase HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents HMIS: 3-2-1-X	295.71	124-9°/2.5 flashpoint: 108°C (226°F)	1.16	
			25g/\$78.00		
CH ₃ CH ₂ CH ₂ CH ₂ SiCl ₃	SIB1982.0 n-BUTYLTRICHLOROSILANE C ₄ H ₉ Cl ₃ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [7521-80-4] TSCA HMIS: 3-3-1-X	191.56	142-3° flashpoint: 45°C (114°F) vapor pressure, 31°: 10mm	1.1608	1.4364
			25g/\$37.00		100g/\$121.00
	SIB1985.0 t-BUTYLTRICHLOROSILANE C ₄ H ₉ Cl ₃ Si forms silanetriol HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [18171-74-9] TSCA HMIS: 3-3-1-X	191.56	142-3° (97-100°)mp flashpoint: 40°C (105°F)	1.1608	1.436
			10g/\$41.00		50g/\$164.00
CH ₃ CH ₂ CH ₂ CH ₂ Si(OCH ₃) ₃	SIB1988.0 n-BUTYLTRIMETHOXYSILANE C ₇ H ₁₈ O ₃ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [1067-57-8] TSCA HMIS: 3-2-1-X	178.30	164-5° flashpoint: 49°C (120°F)	0.9312	1.3979
			25g/\$42.00		100g/\$136.00
	SIB1989.0 t-BUTYLTRIMETHOXYSILANE C ₇ H ₁₈ O ₃ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [18395-29-4] HMIS: 3-2-1-X	178.30	140-1°	0.903	1.3941
			10g/\$143.00		
	SIC2266.0 13-(CHLORODIMETHYLSILYLMETHYL)-HEPTACOSANE, 95% C ₃₀ H ₆₃ ClSi forms hydrophobic bonded phases HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [194243-00-0] TSCA-L HMIS: 3-1-1-X	487.37	200-210°/0.01	0.848 ²⁵	1.4542 ³⁰
			10g/\$117.00		
	SIC2266.5 11-(CHLORODIMETHYLSILYLMETHYL)-TRICOSANE C ₂₆ H ₅₅ ClSi forms self-assembled oleophilic monolayers employed as bonded phase in HPLC HMIS: 3-1-1-X	431.27	170°/0.075		1.4575 ²²
			10g/\$101.00		
	SIC2465.0 CYCLOHEXYLDIMETHYLCHLOROSILANE C ₈ H ₁₇ ClSi silane blocking agent with good resistance to Grignard reagents. HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [71864-47-6] HMIS: 3-2-1-X	176.76	52-3°/2 flashpoint: 63°C (145°F)	0.956	1.4626
			25g/\$36.00		100g/\$117.00
	COMMERCIAL SIC2468.0 CYCLOHEXYLMETHYLDICHLOROSILANE C ₇ H ₁₄ Cl ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [5578-42-7] TSCA HMIS: 3-2-1-X	197.18	83°/15 flashpoint: 66°C (151°F)	1.095	1.4724
			25g/\$25.00		2 kg/\$402.00



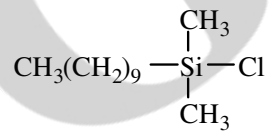
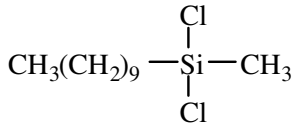
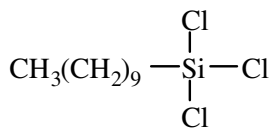
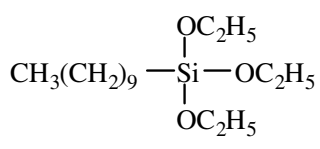
PLEASE INQUIRE ABOUT BULK QUANTITIES

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SIC2469.0 CYCLOHEXYLMETHYLDIMETHOXYSILANE C ₉ H ₂₀ O ₂ Si vapor pressure, 20°: 12mm donor for polyolefin polymerization HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [17865-32-6] TSCA HMIS: 2-3-1-X	188.34	196°	0.9472	1.4354
		25g/\$11.00	100g/\$37.00	2kg/\$496.00	
	SIC2470.0 (CYCLOHEXYLMETHYL)TRICHLOROSILANE C ₇ H ₁₃ Cl ₃ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18388-16-4] TSCA HMIS: 3-2-1-X	231.62	94-8°/11		
			10g/\$93.00		
	SIC2480.0 CYCLOHEXYLTRICHLOROSILANE C ₆ H ₁₁ Cl ₃ Si intermediate for melt-processable silsesquioxane-siloxanes ¹ . employed in solid-phase extraction columns ² . 1. J. Lichtenhan et al, <i>Macromolecules</i> , 26 , 2141, 1993. 2. B. Tippins, <i>Nature</i> , 334 , 273, 1988. HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [98-12-4] TSCA HMIS: 3-2-1-X	217.60	90-1°/10 flashpoint: 91°C (195°F)	1.222	1.4774
		25g/\$34.00		100g/\$110.00	
	SIC2482.0 CYCLOHEXYLTRIMETHOXYSILANE C ₉ H ₂₀ O ₃ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [17865-54-2] HMIS: 2-3-1-X	204.34	207-9°		
		10g/\$31.00		50g/\$124.00	
	SIC2490.0 CYCLOOCTYLTRICHLOROSILANE, 95% C ₈ H ₁₅ Cl ₃ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents HMIS: 3-2-1-X	245.65	85-9°/1.25	1.19	
		10g/\$37.00		50g/\$148.00	
	SIC2555.0 CYCLOPENTYLTRICHLOROSILANE C ₅ H ₉ Cl ₃ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [14579-03-4] HMIS: 3-2-1-X	203.57	178-9° flashpoint: 77°C (171°F)	1.2255	1.4713
		25g/\$45.00		100g/\$146.00	
	SIC2557.0 CYCLOPENTYLTRIMETHOXYSILANE C ₈ H ₁₈ O ₃ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [143487-47-2] HMIS: 3-3-1-X	190.31	75°/10 flashpoint: 54°C (130°F)	0.990 ²⁵	1.4240 ²⁵
		10g/\$34.00		50g/\$136.00	
	SID2660.0 n-DECYLDIMETHYLCHLOROSILANE C ₁₂ H ₂₇ ClSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [38051-57-9] TSCA HMIS: 3-1-1-X	234.88	98°/2 flashpoint: 137°C (279°F)	0.866	1.441
		25g/\$36.00		100g/\$117.00	
	SID2662.0 n-DECYLMETHYLDICHLOROSILANE C ₁₁ H ₂₄ Cl ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18051-88-2] TSCA HMIS: 3-1-1-X	255.31	111-4°/3 flashpoint: 120°C (248°F)	0.960	1.4490
		25g/\$30.00			
	SID2663.0 n-DECYLTRICHLOROSILANE C ₁₀ H ₂₁ Cl ₃ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [13829-21-5] TSCA HMIS: 3-1-1-X	275.72	133-7°/5 flashpoint: >110°C (>230°F)	1.0540	1.4528
		25g/\$20.00		100g/\$65.00	
	SID2665.0 n-DECYLTRIETHOXYSILANE C ₁₆ H ₃₆ O ₃ Si see also SIB1829.0 for dipodal version HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [2943-73-9] HMIS: 2-1-0-X	304.54	150°/8	0.8790	1.4220
		25g/\$54.00		100g/\$175.00	

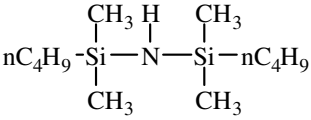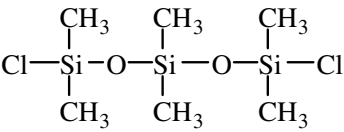
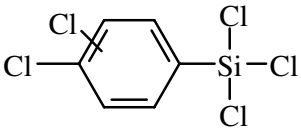
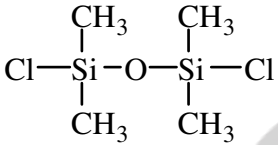





	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SID3203.0 DI-n-BUTYLDICHLOROSILANE, 95% C ₈ H ₁₈ Cl ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [3449-28-3] TSCA HMIS: 3-2-1-X	213.22	212° flashpoint: 64°C (147°F)	0.991	1.4448
	SID3214.0 DI-n-BUTYLDIMETHOXYSILANE C ₁₀ H ₂₄ O ₂ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [18132-63-3] TSCA-L HMIS: 3-2-1-X	204.39	125°/50 flashpoint: 103°C (217°F)	0.861	
	SID3349.0 DI-n-BUTYLTETRAMETHYLDISILAZANE C ₁₂ H ₃₁ NSi ₂ HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [82356-80-7] HMIS: 2-1-1-X	245.55	81°/2 flashpoint: 86°C (187°F)	0.80	1.4353
	SID3360.0 1,5-DICHLOROHEXAMETHYLTRISILOXANE, 95% C ₆ H ₁₈ Cl ₂ O ₂ Si ₃ ΔHvap: 11.4 kcal/mole HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [3582-71-6] TSCA HMIS: 3-2-1-X	277.37	184° (-53°)mp flashpoint: 76°C (169°F) vapor pressure: 50°: 1mm	1.018	1.4071
	SID3367.6 DICHLOROPHENYLTRICHLOROSILANE, 95% C ₆ H ₃ Cl ₅ Si-isomeric mixture vapor pressure, 102°: 7mm HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [27137-85-5] TSCA HMIS: 3-1-1-X	280.44	260-1° flashpoint: 150°C (302°F)	1.553	1.564
	SID3372.0 1,3-DICHLOROTETRAMETHYLDISILOXANE C ₄ H ₁₂ Cl ₂ O ₂ Si ₂ vapor pressure, 25°: 8mm blocking agent HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [2401-73-2] TSCA HMIS: 3-4-1-X	203.22	138° (-37°)mp flashpoint: 15°C (59°F)	1.039	1.4054
	SID3382.0 DICYCLOHEXYLDICHLOROSILANE C ₁₂ H ₂₂ Cl ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18035-74-0] HMIS: 3-1-1-X	265.30	123°/0.4 flashpoint: 149°C (300°F)	1.103	
	SID3390.0 DICYCLOPENTYLDICHLOROSILANE C ₁₀ H ₁₈ Cl ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [139147-73-2] HMIS: 3-2-1-X	237.24	105-7°/10 flashpoint: 84°C (183°F)	1.110	
	SID3391.0 DICYCLOPENTYLDIMETHOXYSILANE C ₁₂ H ₂₄ O ₂ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [126990-35-0] TSCA HMIS: 3-1-1-X	228.40	120°/6 flashpoint: 102°C (216°F)	1.00	1.4663
	SID3394.0 1,5-DIETHOXYHEXAMETHYLTRISILOXANE C ₁₀ H ₂₈ O ₄ Si ₃ [17928-13-1] HMIS: 2-2-1-X	296.59	51-2°/0.8 flashpoint: 10°C (50°F)	0.912	1.3889
	SID3398.0 (DIETHYLAMINO)TRIMETHYLSILANE TMSDEA C ₇ H ₁₉ NSi ΔHform: -87.7kcal/mole silylation reagent: F&F: 3, 317; 4, 544; 6, 634; 18, 382 HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [996-50-9] TSCA HMIS: 3-4-1-X	145.32	126-7° (-10°)mp flashpoint: 10°C (50°F)	0.7627	1.4109

PLEASE INQUIRE ABOUT BULK QUANTITIES











name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
SID3402.0 DIETHYLDICHLOROSILANE <chem>C4H10Cl2Si</chem>  ΔHvap: 10.0 kcal/mole dipole moment: 2.4 surface tension: 30.3 dynes/cm vapor pressure, 21°: 10mm HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [1719-53-5] TSCA HMIS: 3-3-1-X	157.11	130° (-96.5)mp	1.0504	1.4309
SID3404.0 DIETHYLDIETHOXYOSILANE <chem>C8H20O2Si</chem>  vapor pressure, 73°: 38mm HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [5021-93-2] TSCA HMIS: 2-3-1-X	176.33	157° flashpoint: 43°C (109°F)	0.8622	1.4022
SID3510.0 DI-n-HEXYLDICHLOROSILANE <chem>C12H26Cl2Si</chem>  HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18204-93-8] TSCA HMIS: 3-2-1-X	269.33	111-3°/6 flashpoint: 88°C (190°F)	0.962	1.4518
SID3526.0 DIISOBUTYLCHLOROSILANE <chem>C8H19ClSi</chem>  HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18279-73-7] HMIS: 3-3-1-X	178.78	166-7° flashpoint: 42°C (108°F)	0.995	1.4340
SID3528.0 DIISOBUTYLDIETHOXYOSILANE <chem>C12H28O2Si</chem>  [18297-14-8] HMIS: 2-2-1-X	232.44	221° flashpoint: 102°C (216°F)	0.8450	1.4179
SID3530.0 DIISOBUTYLDIMETHOXYOSILANE <chem>C10H24O2Si</chem>  intermediate for diisobutylsilanediol, a liquid crystal. employed in polyolefin polymerization HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [17980-32-4] TSCA HMIS: 2-1-1-X	204.39	120°/6 flashpoint: 102°C (216°F)	0.87	1.4167
SID3537.0 DIISOPROPYLDICHLOROSILANE <chem>C6H14Cl2Si</chem>  forms bis(blocked) or tethered alcohols ^{1,2} . 1. J. Hutchinson et al, Tet. Lett., 32, 573, 1991. 2. C. Bradford et al, Tet. Lett., 36, 4189, 1995. HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [7751-38-4] HMIS: 3-3-1-X	185.17	64-5°/25 flashpoint: 43°C (109°F)	1.026	1.4450
SID3538.0 DIISOPROPYLDIMETHOXYOSILANE <chem>C8H20O2Si</chem>  cocatalyst for α-olefin polymerization ¹ . 1. S. Lee et al, US Pat. 5,223,466, 1993 HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [18230-61-0] TSCA HMIS: 3-3-1-X	176.33	85-7°/50 flashpoint: 43°C (109°F)	0.875	1.4140
SID3544.0 3,5-DIMETHOXYPHENYLTRIETHOXYOSILANE <chem>C14H24O5Si</chem>  HMIS: 2-1-1-X	300.43	136-8°/0.6	1.050	
SID3605.0 (N,N-DIMETHYLAMINO)TRIMETHYLSILANE TMSDMA PENTAMETHYLSILANAMINE <chem>C5H15NSi</chem>  stronger silylation reagent than HMDS; silylates amino acids ¹ . selectively silylates equatorial hydroxyl groups in prostaglandin synthesis ² . 1. K. Rühlman, Chem. Ber., 94, 1876, 1961. 2. E. Yankee et al, J. Am. Chem. Soc., 94, 3651, 1972. HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [2083-91-2] TSCA HMIS: 3-4-1-X	117.27	85-6° flashpoint: -19°C (-3°F) ΔHvap: 7.6 kcal/mole	0.741	1.3970



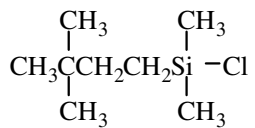

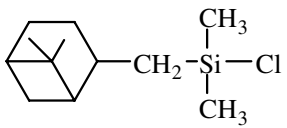
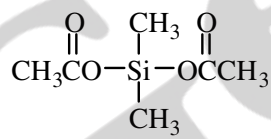

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SID4040.0 DIMETHYLBIS(s-BUTYLAMINO)SILANE 95% C ₁₀ H ₂₆ N ₂ Si	202.42	82°/15 (-50°)mp	0.810	1.4271
	chain-extender for silicones HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [93777-98-1] TSCA HMIS: 3-3-1-X	25g/\$41.00	100g/\$133.00		
	SID4065.0 (3,3-DIMETHYLBUTYL)DIMETHYLCHLORO-SILANE <i>NEOHEXYLDIMETHYLCHLOROSILANE</i> C ₈ H ₁₉ ClSi	178.78	167° flashpoint: 38°C (100°F)	0.849	1.4240
	blocking agent HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [96220-76-7] HMIS: 3-3-1-X	25g/\$34.00	100g/\$110.00		
	SID4069.0 (3,3-DIMETHYLBUTYL)TRICHLOROSILANE <i>NEOHEXYLTRICHLOROSILANE</i> C ₆ H ₁₃ Cl ₃ Si	219.61	183-4°	1.1355	1.4479
	[105732-02-3] HMIS: 3-2-1-X	25g/\$48.00			
	SID4074.0 (DIMETHYLCHLOROSILYL)METHYLPINANE C ₁₂ H ₂₃ ClSi	230.85	93-4°/2 flashpoint: 92°C (198°F) 1*S,2*S,5*S [α] _D : -5.15; >95% optical purity	0.957	1.4780
	acetylenic derivative forms chiral polymer membrane that resolves amino acids ¹ . 1. T. Aoki et al, Makromol. Chem. Rapid Commun, 73, 565, 1992 HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [2182-66-3] TSCA HMIS: 3-2-1-X	10g/\$37.00			
COMMERCIAL	SID4074.4 1,1-DIMETHYLCYCLOSILAZANES, 22-25% in hexane primarily trimer and tetramer		flashpoint: 20°C (-25°F)	0.69	
	HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture TSCA HMIS: 2-4-1-X	100g/\$20.00	2kg/\$190.00		
	SID4076.0 DIMETHYLDIACETOXSILANE C ₆ H ₁₂ O ₄ Si	176.24	164-6° flashpoint: 37°C (98°F)	1.054	1.4030
	reagent for the preparation of cis-diols and corticosteroids ¹ . 1. R. Kelley, J. Chromatog., 43, 229, 1969; F&F 3, 113 HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [2182-66-3] TSCA HMIS: 2-3-1-X	100g/\$30.00	500g/\$120.00		
COMMERCIAL	SID4120.0 DIMETHYLDICHLOROSILANE C ₂ H ₆ Cl ₂ Si	129.06	70-1° (-76°)mp	1.0637	1.4055
	viscosity: 0.47 cSt ΔHvap: 8.0 kcal/mole vapor pressure, 17°: 100mm coefficient of thermal expansion: 1.3 x 10 ⁻³ critical temperature: 247.2° autoignition temperature: 410° fundamental monomer for silicones; hydrophobic surface treatment HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [75-78-5] TSCA HMIS: 3-4-2-X	500g/\$25.00	2kg/\$58.00	18kg/\$477.00*+container *zDR-S-019 or zCYL-S-019 required	
	SID4120.1 DIMETHYLDICHLOROSILANE, 99+% C ₂ H ₆ Cl ₂ Si	129.06	70-1° (-76°)mp	1.0637	1.4055
	redistilled HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [75-78-5] TSCA HMIS: 3-4-2-X	25g/\$11.00	500g/\$68.00	18kg/\$1224.00*+container *zDR-S-019 or zCYL-S-019 required	

name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
<p>SID4121.0 DIMETHYLDIETHOXY-SILANE C₆H₁₆O₂Si viscosity; 0.53cSt vapor pressure, 25°: 15mm ΔHvap: 9.8 kcal/mole ΔHform: 200 kcal/mole coefficient of thermal expansion: 1.3 x 10⁻³ hydrophobic surface treatment and release agent HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [78-62-6] TSCA HMIS: 2-4-1-X</p>	148.28	114-5° (-97°)mp	0.8395	1.3805
<p>SID4123.0 DIMETHYLDIMETHOXY-SILANE C₄H₁₂O₂Si ΔHcomb: 832 kcal/mole ΔHform: 171 kcal/mole vapor pressure, 36°: 100mm coefficient of thermal expansion: 1.3 x 10⁻³ HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [1112-39-6] TSCA HMIS: 3-4-1-X</p>	120.22	82° (-80°)mp	0.8646	1.3708
<p>SID4123.1 DIMETHYLDIMETHOXY-SILANE, 99+% DMDMOS C₄H₁₂O₂Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [1112-39-6] TSCA HMIS: 3-4-1-X</p>	120.22	82° (-80°)mp	0.8646	1.3708
<p>SID4125.0 DIMETHYLETHOXY-SILANE C₄H₁₂O₂Si vapor pressure, 25°: 281mm undergoes hydrosilylation reactions waterproofing agent for space shuttle thermal tiles¹. 1. W. Hill et al, Poly. Mat. Sci. Eng., 62, 668, 1990 HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [14857-34-2] TSCA HMIS: 2-4-1-X</p>	104.22	54-5°	0.757	1.3683
<p>SID4210.0 DIMETHYLMETHOXYCHLOROSILANE, 90% C₃H₉ClOSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [1825-68-9] TSCA HMIS: 3-4-1-X</p>	124.64	77° flashpoint: -9°C (16°F)	0.953 ²⁵	1.3865
<p>SID4236.0 1,3-DIMETHYLTETRAMETHOXY-DISILOXANE, 95% C₆H₁₈O₅Si₂ HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [18186-97-5] HMIS: 3-3-1-X</p>	226.38	165° flashpoint: 30°C (86°F)	1.010	1.3834
<p>SID4400.0 DI-n-OCTYLDICHLOROSILANE C₁₆H₃₄Cl₂Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18416-07-4] HMIS: 3-2-1-X</p>	325.44	145°/0.2	0.940	
<p>SID4401.0 (DI-n-OCTYLMETHYLSILYL)ETHYLDIMETHYL-CHLOROSILANE C₂₁H₄₇ClSi₂ forms bonded phases for reverse phase chromatography HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [472513-03-7] HMIS: 3-2-1-X</p>	391.23	165-6°/0.1	0.859	

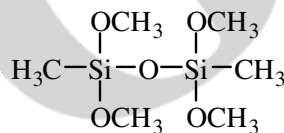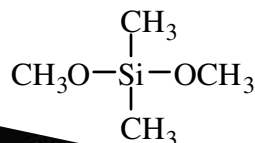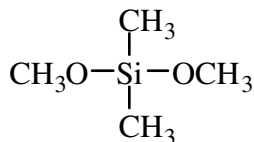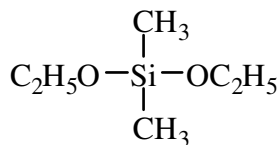


	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SID4401.5 (DI-n-OCTYLMETHYLSILYL)ETHYLTRICHLOROSILANE C ₁₉ H ₄₁ Cl ₃ Si ₂ forms bonded phases for reverse phase HPLC HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents HMIS: 3-2-1-X	432.06	166-8°/0.1	0.966	
	SID4404.0 1, 3-DI-n-OCTYLTETRAMETHYLDISILAZANE C ₂₀ H ₄₇ NSi ₂ HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [69519-51-3] HMIS: 2-1-0-X	357.77	160-5°/1 flashpoint: >110°C (>230°F)	0.826	1.4500
	COMMERCIAL SID4510.0 DIPHENYLDICHLOROSILANE, 95% C ₁₂ H ₁₀ Cl ₂ Si vapor pressure, 125°: 2mm ΔHvap: 15.0 kcal/mole coefficient of thermal expansion: 0.7 x 10 ⁻³ specific heat: 0.30 silicone monomer; forms diol on contact with water HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [80-10-4] TSCA HMIS: 3-1-1-X	253.20	304-5° (-22°)mp TOXICITY- ipr mus, LD50: 383mg/kg flashpoint: 157°C (314°F) dipole moment: 2.6 debye viscosity, 25°: 4.1 cSt	1.2216	1.5819
	SID4510.1 DIPHENYLDICHLOROSILANE, 99% C ₁₂ H ₁₀ Cl ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [80-10-4] TSCA HMIS: 3-1-1-X	253.20	304-5° (-22°)mp TOXICITY- ipr mus, LD50: 383mg/kg flashpoint: 157°C (314°F)	1.2216	1.5819
	SID4525.0 DIPHENYLDIETHOXYLSILANE C ₁₆ H ₂₀ O ₂ Si vapor pressure, 125°: 2mm HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [2553-19-7] TSCA HMIS: 2-1-0-X	272.42	167°/15 flashpoint: 175°C (347°F)	1.0329	1.5269
	COMMERCIAL SID4535.0 DIPHENYLDIMETHOXYLSILANE C ₁₄ H ₁₆ O ₂ Si viscosity, 25°: 8.4 cSt HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [6843-66-9] TSCA HMIS: 3-1-1-X	244.36	161°/15 flashpoint: 121°C (250°F)	1.0771	1.5447
	SID4552.0 DIPHENYLMETHYLCHLOROSILANE C ₁₃ H ₁₃ ClSi vapor pressure, 125°: 3mm ΔHvap: 149 kcal/mole surface tension: 40.0 dynes/cm α silylates esters, lactones; precursors to α silyl enolates ¹ . 1. G. Larson et al, J. Am. Chem. Soc., 103, 2418, 1981. HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [144-79-6] TSCA HMIS 3-1-1-X	232.78	295° (-22°C)mp flashpoint: 141°C (286°F) viscosity, 25°: 5.3 cSt thermal conductivity: 0.112 W/m°C	1.128	1.5742
	SID4552.5 DIPHENYLMETHYL(DIMETHYLAMINO)SILANE C ₁₅ H ₁₉ NSi HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [68733-63-1] TSCA-L HMIS: 3-3-1-X	241.41	98-9°/0.25	1.011	

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SID4553.0 DIPHENYLMETHYLETHOXSILANE C ₁₅ H ₁₈ OSi ΔHvap: 14.8 kcal/mole vapor pressure: 125°: 3mm HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [1825-59-8] TSCA HMIS: 2-0-0-X	242.39	100-2°/0.3 (-27°)mp flashpoint: 165°C (329°F) viscosity, 25°: 6.5 cSt	1.018	1.5440 ²⁵
	SID4586.0 1,3-DIPHENYL-1,1,3,3,-TETRAMETHYL-DISILAZANE C ₁₆ H ₂₃ NSi ₂ HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [3449-26-1] TSCA-L HMIS: 3-1-1-X	285.54	96-9°/0.1 flashpoint: 162°C (324°F)	0.985	1.5384
	SID4591.0 1,3-DI-n-PROPYLTETRAMETHYLDISILAZANE C ₁₀ H ₂₇ NSi ₂ [14579-90-9] HMIS: 3-2-1-X	217.51	84°/9 flashpoint: 65°C (150°F) 25g/\$140.00	0.800	1.4290
	SID4598.0 DI(p-TOLYL)DICHLOROSILANE, 95% C ₁₄ H ₁₄ Cl ₂ Si forms polymers w/liquid crystal behavior ¹ . 1. M. Lee et al, Polymer, 34, 4882, 1993. HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18414-38-5] HMIS: 3-2-1-X	281.26	225-6°/50 contains 4-4'dimethylbiphenyl	1.10	1.568
	SID4599.0 DI(p-TOLYL)DIMETHOXSILANE C ₁₆ H ₂₀ O ₂ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [92779-72-1] HMIS: 3-2-1-X	272.42	140°/0.5 25g/\$155.00	1.023	1.5355 ²⁵
	SID4620.0 DOCOSYLMETHYLDICHLOROSILANE, blend C ₂₃ H ₄₈ Cl ₂ Si contains C ₂₀ to C ₂₄ homologs HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [67892-56-2] TSCA HMIS: 3-1-1-X	423.62	218-20°/0.5 (21-9°)mp flashpoint: 172°C (342°F) 50g/\$130.00	0.93	
	SID4621.0 DOCOSYLTRICHLOROSILANE, blend C ₂₂ H ₄₅ Cl ₃ Si contains C ₂₀ to C ₂₄ homologs HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [7325-84-0] TSCA HMIS: 3-1-1-X	444.04	210°/0.2 (20-8°)mp flashpoint: 200°C (392°F) 25g/\$85.00	0.94	
	SID4627.0 DODECYLDIMETHYLCHLOROSILANE C ₁₄ H ₃₁ ClSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [66604-31-7] HMIS: 3-2-1-X	262.94	291-3° 25g/\$58.00	0.865	1.445
	SID4628.0 DODECYLMETHYLDICHLOROSILANE C ₁₃ H ₂₈ Cl ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18407-07-3] TSCA HMIS: 3-1-1-X	283.36	124-7°/3 flashpoint: 143°C (289°F) 25g/\$48.00	0.955	1.4581
	SID4629.0 DODECYLMETHYLDIETHOXSILANE C ₁₇ H ₃₈ O ₂ Si HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [60317-40-0] TSCA HMIS: 2-1-0-X	302.57	140°/0.5 flashpoint: 152°C (305°F) 25g/\$55.00	0.845 ²⁵	




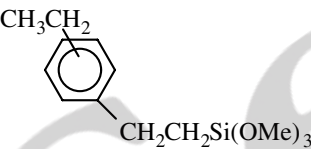


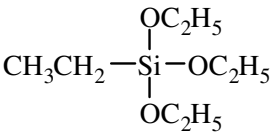
	name	MW	bp/mm (mp)	D ₄ ²⁰	n _b ²⁰
CH ₃ (CH ₂) ₁₀ CH ₂ SiCl ₃	SID4630.0 DODECYLTRICHLOROSILANE C ₁₂ H ₂₅ Cl ₃ Si	303.77	120°/3 (-30°)mp flashpoint: 165°C (329°F)	1.0242	1.4581
	HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [4484-72-4] TSCA HMIS: 3-1-1-X	25g/\$16.00		250g/\$112.00	
CH ₃ (CH ₂) ₁₀ CH ₂ Si(OC ₂ H ₅) ₃	SID4632.0 DODECYLTRIETHOXYSILANE C ₁₈ H ₄₀ O ₃ Si	332.60	152-3°/3 flashpoint: >110°C (>230°F)	0.8842 ²⁵	1.4330 ²⁵
	HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [18536-91-9] TSCA HMIS: 2-1-0-X	25g/\$27.00		100g/\$88.00	
CH ₃ (CH ₂) ₁₈ CH ₂ SiCl ₃	SIE4661.0 EICOSYLTRICHLOROSILANE, 95% C ₂₀ H ₄₁ Cl ₃ Si	415.9	200°/0.5 flashpoint: 230°C (446°F)		
	HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18733-57-8] TSCA HMIS: 3-0-1-X	25g/\$160.00			
	SIE4892.0 ETHYLDIMETHYLCHLOROSILANE C ₄ H ₁₁ ClSi	122.67	91° flashpoint: -4°C (24°F)	0.8756	1.4050
	HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [6917-76-6] HMIS: 3-4-1-X	10g/\$24.00		50g/\$96.00	
	SIE4896.0 ETHYLMETHYLDICHLOROSILANE C ₃ H ₈ Cl ₂ Si	143.09	100° flashpoint: 2°C (36°F)	1.0630	1.4197
	dipole moment: 2.32 debye HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [4525-44-4] TSCA HMIS: 3-4-1-X	25g/\$31.00		100g/\$100.00	
	SIE4897.0 (ETHYLMETHYLKETOXIMINO)TRIMETHYL- SILANE <i>O</i> -(TRIMETHYLSILYL)OXIME-2-BUTANONE C ₇ H ₁₇ NOSi	159.30	65°/75	0.826 ²⁵	1.4125 ²⁵
	HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [37843-14-4] HMIS: 2-3-1-X	10g/\$41.00			
	SIE4897.5 m,p-ETHYLPHENETHYLTRIMETHOXY- SILANE, 95% C ₁₃ H ₂₂ O ₃ Si	254.40	93-6°/4	0.996	1.4776 ²⁵
	component in optical hard coating resins HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [259818-29-6] HMIS: 3-2-1-X	25g/\$102.00			
	SIE4899.0 ETHYLTRIACETOXYSILANE C ₈ H ₁₄ O ₆ Si	243.28	107-8°/8 (7-9°)mp flashpoint: 106°C (223°F)	1.143	1.4123
	liquid cross-linker for silicone RTVs HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [17689-77-9] TSCA HMIS: 3-1-1-X	25g/\$10.00		2.0kg/\$148.00	
	SIE4901.0 ETHYLTRICHLOROSILANE C ₂ H ₅ Cl ₃ Si	163.51	100-1° (-106°)mp vapor pressure, 20°: 26mm, 30.4°: 66mm ΔHvap: 9.0 kcal/mole coefficient of expansion: 1.5x10 ⁻³ viscosity: 0.48 cSt	1.237	1.426
	HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [115-21-9] TSCA HMIS: 3-3-1-X	25g/\$10.00	500g/\$29.00	4kg/\$176.00	
	SIE4901.2 ETHYLTRIETHOXYSILANE C ₈ H ₂₀ O ₃ Si	192.33	158-9° (-78°)mp viscosity: 0.70 cSt vapor pressure, 50°: 10mm coefficient of thermal expansion: 1.5 x 10 ⁻³ ΔHvap: 7.8 kcal/mole	0.8963	1.3955
	HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [78-07-9] TSCA HMIS: 3-2-1-X	100g/\$37.00	TOXICITY- oral rat, LD50: 13,720 mg/kg flashpoint: 40°C (104°F) autoignition temperature: 235°C (455°F) specific heat: 0.43/g° γc of treated surface: 26.3 dynes/cm critical temperature: 314°	500g/\$148.00	




COMMERCIAL

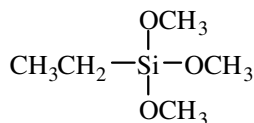PLEASE INQUIRE ABOUT BULK QUANTITIES



name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
SIE4901.4 ETHYLTRIMETHOXYSILANE C ₅ H ₁₄ O ₃ Si viscosity: 0.5 cSt HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [5314-55-6] TSCA HMIS: 3-3-1-X	150.25	124-5° flashpoint: 27°C (80°F) ΔHcomb: 3425 kcal/mole	0.9488	1.3838
PP1-GC18 GLASSCLAD® 18 OCTADECYL FUNCTIONAL SILANE 20% in <i>t</i> -BUTYL ALCOHOL and DIACETONE ALCOHOL γc of treated glass surface: 31 dynes/cm coefficient of friction of treated glass surface: 0.2-0.3 surface resistivity of treated surface: 1.2 x 10 ¹³ ohms reduces blood protein adsorption ¹ . 1. B. Arkles et al in "Silanes Surfaces & Interfaces" D. Leyden ed, Gordon & Breach, 1986, p91 TSCA HMIS: 2-3-1-X		flashpoint: 10°C(50°F) amber liquid	0.88	
SIH5840.4 (HEPTADEC AFLUORO-1,1,2,2-TETRA- HYDRODECYL)DIMETHYLCHLOROSILANE PERFLUORODECYL-1H,1H,2H,2H-DIMETHYLCHLOROSILANE C ₁₂ H ₁₀ ClF ₁₇ Si derivatizing agent for fluorous phase synthesis. HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [74612-30-9] HMIS: 3-2-1-X	540.72	197-8°	1.51	1.3410
SIH5840.6 (HEPTADEC AFLUORO-1,1,2,2-TETRA- HYDRODECYL)METHYLDICHLOROSILANE C ₁₁ H ₇ Cl ₂ F ₁₇ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [3102-79-2] HMIS: 3-2-1-X	561.14	205-7° (26-7°)mp	1.63	
SIH5841.0 (HEPTADEC AFLUORO-1,1,2,2-TETRA- HYDRODECYL)TRICHLOROSILANE PERFLUORODECYL-1H,1H,2H,2H-TRICHLOROSILANE C ₁₀ H ₄ Cl ₃ F ₁₇ Si γc of treated surfaces: 12 dynes/cm ¹ . 1. J. Brzoska et al, Langmuir, 10, 4367, 1994 HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [78560-44-8] TSCA HMIS: 3-2-1-X	581.56	216-8° TOXICITY- oral rat, LD50: >5000 mg/kg	1.703	1.3490
SIH5841.2 (HEPTADEC AFLUORO-1,1,2,2-TETRA- HYDRODECYL)TRIETHOXYSILANE C ₁₆ H ₁₉ F ₁₇ O ₃ Si hydrolysis in combination with polydimethoxysiloxane gives hard hydrophobic coatings ¹ . 1. T. Oota et al, Jpn. Kokai JP 06,293,782, 1993; CA 122: 136317d, 1995 HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [101947-16-4] HMIS: 3-2-1-X	610.38	103-6°/3	1.407 ²⁵	1.3419
SIH5841.5 (HEPTADEC AFLUORO-1,1,2,2-TETRA- HYDRODECYL)TRIMETHOXYSILANE C ₁₃ H ₁₃ F ₁₇ O ₃ Si HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [83048-65-1] HMIS: 3-2-1-X	568.30	247°	1.54	1.331 ²⁵
SIH5842.0 (3-HEPTAFLUOROISOPROPOXY)PROPYL- TRICHLOROSILANE C ₆ H ₆ Cl ₃ F ₇ OSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [15538-93-9] HMIS: 3-3-1-X	361.55	85-7°/35	1.497	1.3710
SIH5845.0 <i>n</i> -HEPTYLMETHYLDICHLOROSILANE C ₈ H ₁₈ Cl ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [18395-93-2] TSCA HMIS: 3-2-1-X	213.22	207-8° flashpoint: 66°C (150°F)	0.978	1.4396 ²⁵

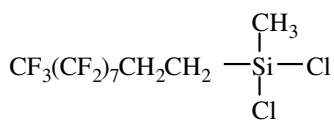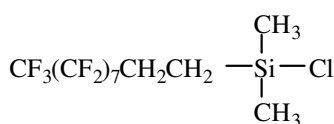

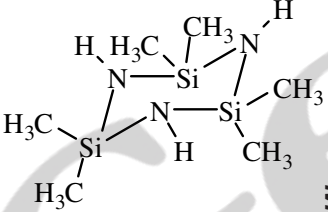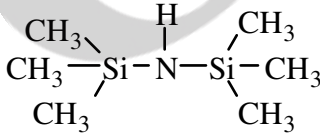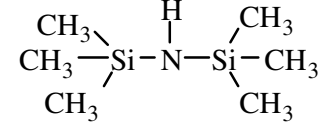	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
$\text{CH}_3(\text{CH}_2)_6\text{SiCl}_3$	SIH5846.0 n-HEPTYLTRICHLOROSILANE $\text{C}_7\text{H}_{15}\text{Cl}_3\text{Si}$ HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [871-41-0] HMIS: 3-2-1-X	233.64	211-2° flashpoint: 64°C (146°F) 25g/\$74.00	1.087	1.4439 ²⁵
$\text{H}_2\text{C}=\text{CHCF}_2(\text{CF}_2)_6\text{CF}_2\text{CH}_2\text{CH}_2\text{SiCl}_3$	SIH5918.0 HEXADECAFLUORODODEC-11-ENE-1-YL-TRICHLOROSILANE $\text{C}_{12}\text{H}_7\text{Cl}_3\text{F}_{16}\text{Si}$ forms self-assembled monolayers/ reagent for immobilization of DNA HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture HMIS: 3-1-1-X	589.61	94-6°/0.6 5.0g/\$190.00	1.626	1.3713
$\text{CH}_3(\text{CH}_2)_{14}\text{CH}_2\text{SiCl}_3$	SIH5920.0 HEXADECYLTRICHLOROSILANE, 95% $\text{C}_{16}\text{H}_{33}\text{Cl}_3\text{Si}$ γc of treated surfaces: 21 dynes/cm HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [5894-60-0] TSCA HMIS: 3-1-1-X	359.88	202°/10 flashpoint: 154°C (309°F) 25g/\$13.00	0.98	1.4592
$\text{CH}_3(\text{CH}_2)_{14}\text{CH}_2\text{Si}(\text{OC}_2\text{H}_5)_3$	SIH5922.0 HEXADECYLTRIETHOXYSILANE, 95% $\text{C}_{22}\text{H}_{48}\text{O}_3\text{Si}$ HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [16415-13-7] HMIS: 2-1-1-X	388.71	160-1°/1 (-9°)mp 25g/\$23.00	0.888	1.4370
$\text{CH}_3(\text{CH}_2)_{14}\text{CH}_2\text{Si}(\text{OCH}_3)_3$	SIH5925.0 HEXADECYLTRIMETHOXYSILANE, 95% $\text{C}_{19}\text{H}_{42}\text{O}_3\text{Si}$ viscosity: 7 cSt HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [16415-12-6] TSCA HMIS: 2-2-1-X	346.63	155°/0.2 (-1°)mp 25g/\$18.00 2kg/\$290.00 16kg/\$1536.00	0.89	
	SIH6102.0 1,1,3,3,5,5-HEXAMETHYLCYCLOTRISILAZANE $\text{C}_6\text{H}_{21}\text{N}_3\text{Si}_3$ ΔHform: 132 kcal/mole viscosity, 20°: 1.7 cSt modifies positive resists for O ₂ plasma resistance ¹ . polymerizes to polydimethylsilazane oligomer in presence of Ru/H ₂ ² . silylation reagent for diols ³ . 1. E. Babich et al, Microelectron. Eng., 11, 503, 1990. 2. Y. Blum et al, US Pat., 4,216,383, 1986; US Pat. 4,788,309, 1988. 3. L. Birkofer et al, J. Orgmet. Chem., 187, 21, 1980. see also SID4074.4 HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [1009-93-4] TSCA HMIS: 2-2-1-X	219.51	186-8° (-10°)mp flashpoint: 61°C (142°F) dipole moment: 0.92 dielectric constant, 1000Hz: 2.57 25g/\$29.00 100g/\$94.00 2kg/\$636.00	0.922	1.4448
	SIH6110.0 HEXAMETHYLDISILAZANE $\text{C}_6\text{H}_{19}\text{NSi}_2$ HMDS, HMDZ viscosity: 0.90 cSt vapor pressure, 50°: 50mm pKa: 7.55 surface tension: 18.2 dynes/cm Ea, reaction w/SiO ₂ surface: 17.6 kcal/mole versatile silylation reagent; creates hydrophobic surfaces HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [999-97-3] TSCA HMIS: 2-4-1-X	161.39	126-7° TOXICITY- oral rat, LD50: 850mg/kg TOXICITY- ipr mus, LDLo: 650mg/kg flashpoint: 14°C (57°F) ΔHvap: 8.3 kcal mole dielectric constant, 1000 Hz: 2.27 specific wetting surface: 485 m ² /g 25g/\$10.00 1.5kg/\$60.00 14kg/\$305.00	0.7742	1.4080
	SIH6110.1 HEXAMETHYLDISILAZANE, 99% $\text{C}_6\text{H}_{19}\text{NSi}_2$ HMDS, HMDZ <5ppm chloride photoresist adhesion promoter HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [999-97-3] TSCA HMIS: 2-4-1-X	161.39	126-7° TOXICITY- ipr mus, LDLo: 650mg/kg 25g/\$13.00 1.5kg/\$85.00	0.7742	1.4080
$\text{CH}_3(\text{CH}_2)_4\text{CH}_2\text{SiCl}_2$	SIH6165.6 HEXYLMETHYLDICHLOROSILANE $\text{C}_7\text{H}_{16}\text{Cl}_2\text{Si}$ HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [14799-94-1] TSCA HMIS: 3-2-1-X	199.19	204-6° flashpoint: 85°C (185°F) 25g/\$31.00	0.993	1.4390

COMMERCIAL

PLEASE INQUIRE ABOUT BULK QUANTITIES

HYDROPHOBIC











COMMERCIAL












COMMERCIAL

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SIH6167.0 HEXYLTRICHLOROSILANE C ₆ H ₁₃ Cl ₃ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [928-65-4] TSCA HMIS: 3-2-1-X	219.61	191-2° flashpoint: 85°C (185°F)	1.107	1.3473
	SIH6167.5 HEXYLTRIETHOXSILANE C ₁₂ H ₂₈ O ₃ Si HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [18166-37-5] HMIS: 2-1-1-X	248.44	115°/18 flashpoint: 95°C (203°F)	0.860	1.408 ²⁵
	SIH6168.5 HEXYLTRIMETHOXSILANE C ₉ H ₂₂ O ₃ Si HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [3069-19-0] TSCA HMIS: 3-2-1-X	206.35	202-3° flashpoint: 62°C (144°F)	0.911 ²⁵	1.4070
	SII6452.5 ISOBUTYLDIMETHYLCHLOROSILANE C ₆ H ₁₅ ClSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [60090-96-2] HMIS: 3-4-1-X	150.72	131-3° flashpoint: 18°C (64°F)		1.4187 ²⁵
	SII6452.8 ISOBUTYLMETHYLDIMETHOXSILANE C ₇ H ₁₈ O ₂ Si HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [18293-82-8] HMIS: 2-3-1-X	162.30	63°/40 flashpoint: 38°C (101°F)	0.851	1.3962
	SII6453.0 ISOBUTYLTRICHLOROSILANE C ₄ H ₉ Cl ₃ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18169-57-8] TSCA HMIS: 3-3-1-X	191.56	140° flashpoint: 37°C (100°F)	1.162	1.4335
	SII6453.5 ISOBUTYLTRIETHOXSILANE C ₁₀ H ₂₄ O ₃ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [17980-47-1] TSCA HMIS: 2-2-1-X	220.38	190-1° flashpoint: 63°C (145°F)	0.9104	1.3908
	SII6453.7 ISOBUTYLTRIMETHOXSILANE <i>TRIMETHOXSILYL-2-METHYLPROPANE</i> C ₇ H ₁₈ O ₃ Si viscosity: 0.8 cSt branched structure provides hydrophobic surface treatments for architectural coatings HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [18395-30-7] TSCA HMIS: 3-2-1-X	178.30	154° flashpoint: 42°C (107°F)	0.933	1.3960
	SII6456.6 ISOCTYLDIMETHYLCHLOROSILANE C ₁₀ H ₂₃ ClSi [79957-95-2] HMIS: 3-3-1	206.83	83-5°/10 25g/\$72.00	0.852	
	SII6457.0 ISOCTYLTRICHLOROSILANE <i>1-TRICHLOROSILYL-2,4,4-TRIMETHYLPENTANE</i> C ₈ H ₁₇ Cl ₃ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18379-25-4] TSCA HMIS: 3-2-1-X	247.67	117°/50 flashpoint: 85°C (185°F)	1.0684	1.4510
	SII6458.0 ISOCTYLTRIMETHOXSILANE C ₁₁ H ₂₆ O ₃ Si viscosity: 2 cSt. HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [34396-03-7] TSCA HMIS: 3-2-1-X	234.41	90°/10 flashpoint: 52°C (126°F) autoignition temp.: 310°	0.887	1.4176

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SII6462.0 ISOPROPYLDIMETHYLCHLOROSILANE C ₅ H ₁₃ ClSi see also SID4065.0 HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [3634-56-8] HMIS: 3-4-1-X	136.69	114° flashpoint: 15°C (59°F)	0.873	1.4138
	SIM6492.4 3-(p-METHOXYPHENYL)PROPYLMETHYL-DICHLOROSILANE C ₁₁ H ₁₆ Cl ₂ OSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents HMIS: 3-1-1-X store <5°	263.24	115-6°/0.3 flashpoint: >110°C (>230°F)	1.13	
	SIM6492.5 3-(p-METHOXYPHENYL)PROPYLTRICHLORO-SILANE C ₁₀ H ₁₃ Cl ₃ OSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [163155-57-5] HMIS: 3-1-1-X	283.66	128-9°/1 flashpoint: >110°C (>230°F)	1.226	
	SIM6492.8 (1-METHOXY-2-PROPOXY)TRIMETHYLSILANE C ₇ H ₁₈ O ₂ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [55816-62-1] HMIS: 3-2-1-X	162.30	132° (-40°)mp flashpoint: 20°C (68°F) viscosity: 2 cSt	0.83	1.3965
	SIM6511.0 (p-METHYLPHENETHYL)METHYLDICHLORO-SILANE, 95% (p-TOLYLETHYL)METHYLDICHLOROSILANE C ₁₀ H ₁₄ Cl ₂ Si α: β ~ 40:60 HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture [63126-87-4] TSCA-L HMIS: 3-1-1-X	233.21	103-5°/2 flashpoint: 95°C (203°F)	1.1	1.5100 ²⁵
	SIM6512.5 (2-METHYL-2-PHENYLETHYL)METHYL-DICHLOROSILANE METHYL(α-METHYLPHENETHYL)DICHLOROSILANE C ₁₀ H ₁₄ Cl ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture [13617-28-2] TSCA HMIS: 3-1-1-X	233.21	104-5°/9	1.1165	1.5152
	SIM6519.0 METHYLTRIACETOXYSILANE, 95% C ₇ H ₁₂ O ₆ Si vapor pressure, 94°: 9mm most common crosslinker for condensation cure silicone RTV's HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [4253-34-3] TSCA HMIS: 3-2-1-X	220.25	87-8°/3 (40°)mp flashpoint: 85°C (185°F)	1.175	1.4083
	COMMERCIAL SIM6520.0 METHYLTRICHLOROSILANE CH ₃ Cl ₃ Si vapor pressure, 13.5°: 100mm ΔHvap: 7.4 kcal/mole viscosity: 0.46 cSt critical pressure: 39 atm specific heat: 0.22 cal/g/° coefficient of thermal expansion: 1.3 x 10 ⁻³ HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture [75-79-6] TSCA HMIS: 3-4-2-X	149.48	66.4° (-78°)mp TOXICITY- ihl rat,LDLo: 450ppm/4H flashpoint: -15°C (5°F) autoignition temperature: 395° critical temperature: 243°C ionization potential: 11.36 eV surface tension: 20.3 dynes/cm	1.275	1.4110
	SIM6520.1 METHYLTRICHLOROSILANE, 99% CH ₃ Cl ₃ Si in combination w/H ₂ forms SiC by CVD ¹ . 1. A. Josiek et al, Chem. Vap. Dep., 2, 17, 1996 HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture [75-79-6] TSCA HMIS: 3-4-2-X	149.48	66.4° (-78°)mp	1.275	1.4110

PLEASE INQUIRE ABOUT BULK QUANTITIES

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SIM6555.0 METHYLTRIETHOXSILANE C ₇ H ₁₈ O ₃ Si vapor pressure, 25°: 6mm dipole moment: 1.72 debye viscosity: 0.6 cSt HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [2031-67-6] TSCA HMIS: 1-3-1-X	178.30	142°	0.8948	1.3832
	SIM6560.0 METHYLTRIMETHOXSILANE C ₄ H ₁₂ O ₃ Si viscosity: 0.50 cSt dipole moment: 1.60 debye intermediate for coating resins HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [1185-55-3] TSCA HMIS: 3-4-1-X	136.22	102-3° (-78°)mp	0.955	1.3696
	SIM6560.1 METHYLTRIMETHOXSILANE, 99+% C ₄ H ₁₂ O ₃ Si viscosity: 0.50 cSt dipole moment: 1.60 debye intermediate for coating resins [1185-55-3] TSCA HMIS: 3-4-1-X	136.22	102-3° (-78°)mp	0.955	1.3696
	SIM6579.0 METHYLTRI-n-PROPOXSILANE C ₁₀ H ₂₄ O ₃ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [5581-66-8] TSCA HMIS: 2-2-1-X	220.38	83-4°/13	0.878	1.4085
	SIM6585.0 METHYLTRIS(METHOXYETHOXY)SILANE C ₁₀ H ₂₄ O ₆ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [17980-64-2] TSCA HMIS: 3-1-0-X	268.38	145°/15	1.045	1.4178
	SIM6590.0 METHYLTRIS(METHYLETHYLKETOXIME)- SILANE, 95% METHYLTRIS(2-BUTANONEOXIME)SILANE C ₁₃ H ₂₇ N ₃ O ₃ Si neutral crosslinker for condensation cure silicones HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [22984-54-9] TSCA HMIS: 2-2-1-X	301.46	110-1°/2 (-22°)mp	0.982	1.4548 ²⁵
	SIN6596.0 (1-NAPHTHYLMETHYL)TRICHLOROSILANE C ₁₁ H ₉ Cl ₃ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [17998-59-3] HMIS: 3-2-1-X	275.64	150-1°/7	1.3112	1.5974
	SIN6597.0 1-NAPHTHYLTRIMETHOXSILANE C ₁₃ H ₁₆ O ₃ Si employed in high refractive index surface modification HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [18052-76-1] HMIS: 3-2-1-X	248.35	150°/2 (33-5°)mp		1.5562
	SIN6597.3 NONAFLUOROHEXYLDIMETHYLCHLORO- SILANE C ₈ H ₁₀ ClF ₉ Si HMIS: 3-3-1-X	340.69	162-4°	1.3422	
	SIN6597.6 NONAFLUOROHEXYLTRICHLOROSILANE C ₆ H ₄ Cl ₃ F ₉ Si [78560-47-1] TSCA HMIS: 3-2-1-X	381.53	70-2°/15	1.542	

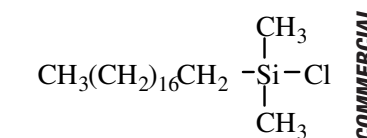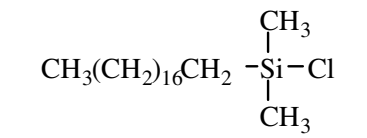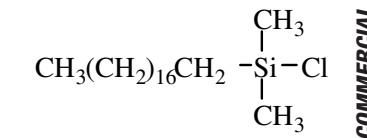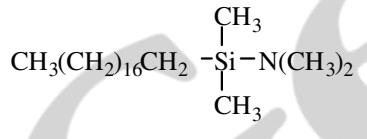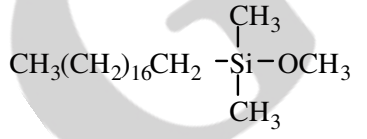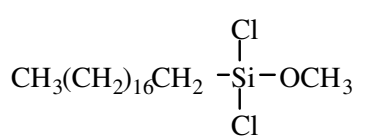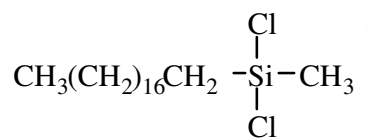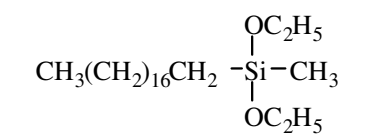
	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SIN6597.65 NONAFLUOROHEXYLTRIETHOXYLSILANE C ₁₂ H ₁₉ F ₉ O ₃ Si [102390-98-7] TSCA HMIS: 2-2-1-X	410.35	25g/\$74.00		
	SIN6597.7 NONAFLUOROHEXYLTRIMETHOXYLSILANE C ₉ H ₁₃ F ₉ O ₃ Si γc of treated surface: 23 dynes/cm [85877-79-8] TSCA HMIS: 3-2-1-X	368.27	68-9°/15	1.335	1.3376
	SIN6598.0 p-NONYLPHENOXYPROPYLDIMETHYL- CHLOROSILANE, 90% C ₂₀ H ₃₅ ClOSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents HMIS: 3-1-1-X	355.04	181°/0.75	0.963	1.4925
	COMMERCIAL SIO6615.0 n-OCTADECYLDIMETHYLCHLOROSILANE DIMETHYL-n-OCTADECYLCHLOROSILANE C ₂₀ H ₄₃ ClSi contains 5-10% C ₁₈ isomers employed in bonded HPLC reverse phases ¹ . 1. S. Wise et al in "Silanes Surfaces & Interfaces" D. Leyden ed., Gordon & Breach, 1986, p349. HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18643-08-8] TSCA HMIS: 3-1-1-X	347.10	159°/0.1 (28-30°)mp flashpoint: 201°C (394°F)	0.856 ²⁹	1.4998 ²⁹
	SIO6615.1 n-OCTADECYLDIMETHYLCHLOROSILANE, 97% DIMETHYL-n-OCTADECYLCHLOROSILANE C ₂₀ H ₄₃ ClSi contains 3-6% C ₁₈ isomers HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18643-08-8] TSCA HMIS: 3-1-1-X	347.10	159°/0.1 (28-30°)mp flashpoint: 201°C (394°F)	0.956 ²⁹	1.4998 ²⁹
	COMMERCIAL SIO6615.2 n-OCTADECYLDIMETHYLCHLOROSILANE, 70% in toluene C ₂₀ H ₄₃ ClSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18643-08-8] TSCA HMIS: 3-3-1-X	347.10	159°/0.1 flashpoint: 5°C (41°F)	0.854	
	SIO6617.0 n-OCTADECYLDIMETHYL(DIMETHYLAMINO)- SILANE contains 5-10% C ₁₈ isomers C ₂₂ H ₄₉ NSi HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [76328-77-3] TSCA HMIS: 3-3-1-X	355.72	160°/0.1		50g/\$168.00
	SIO6618.0 n-OCTADECYLDIMETHYLMETHOXYLSILANE C ₂₁ H ₄₆ O ₂ Si contains 5-10% C ₁₈ isomers employed in SAM resist ¹ . 1. T. Oh et al, Mol. Cryst. Liq. Cryst. Sci. A, 337, 7, 1999. HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [71808-65-6] TSCA HMIS: 2-1-0-X	342.68	184-6°/0.2	0.83 ²⁵	1.444
	SIO6624.0 n-OCTADECYLMETHOXYDICHLORO- SILANE, 95% C ₁₉ H ₄₀ Cl ₂ O ₂ Si maintains reactivity of octadecyltrichlorosilane, but with reduced HCl byproduct HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents HMIS: 3-1-1-X	383.51	144-7°/1.5	0.94 ²⁵	1.452
	SIO6625.0 n-OCTADECYLMETHYLDICHLOROSILANE C ₁₉ H ₄₀ Cl ₂ Si contains 5-10% C ₁₈ isomers flashpoint: 185°C (365°F) HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [5157-75-5] TSCA HMIS: 3-1-1-X	367.52	185°/2.5 (24-6°)mp flashpoint: 185°C (365°F)	0.930	
	SIO6627.0 n-OCTADECYLMETHYLDIETHOXYLSILANE C ₂₃ H ₅₀ O ₂ Si contains 5-10% C ₁₈ isomers HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [67859-75-0] TSCA HMIS: 2-1-0-X	386.73	197°/2 flashpoint: >110°C (>230°F)	0.852	1.4407

PLEASE INQUIRE ABOUT BULK QUANTITIES

HYDROPHOBIC

COMMERCIAL

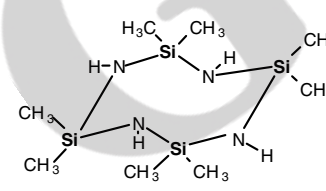COMMERCIAL

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
$\text{CH}_3(\text{CH}_2)_{16}\text{CH}_2-\text{Si}(\text{OCH}_3)_2-\text{CH}_3$	<p>SIO6629.0 n-OCTADECYLMETHYLDIMETHOXYSILANE C₂₁H₄₆O₂Si contains 5-10% C₁₈ isomers</p> <p>flashpoint: >110°C (>230°F) autoignition temp: 225°</p> <p>HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [70851-50-2] TSCA HMIS: 3-1-0-X</p>	358.68	190°/3 (17-18°)mp	0.85	1.4427
$\text{CH}_3(\text{CH}_2)_{16}\text{CH}_2-\text{Si}(\text{Cl})_2$	<p>SIO6640.0 n-OCTADECYLTRICHLOROSILANE, 95% C₁₈H₃₇Cl₃Si contains 5-10% C₁₈ isomers</p> <p>provides lipidophilic surface coatings employed in patterning and printing of electroactive molecular films^{1,2}. see also SIO6624.0 1. Z. Huan et al, Synth. Met., 85, 1375, 1997. 2. N. Jeon et al, Langmuir, 13, 3382, 1997.</p> <p>HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [112-04-9] TSCA HMIS: 3-1-1-X</p>	387.93	160-2°/3 (22°)mp flashpoint: 189°C (372°F)	0.950 ²²	1.4602
$\text{CH}_3(\text{CH}_2)_{16}\text{CH}_2-\text{Si}(\text{Cl})_2$	<p>SIO6640.1 n-OCTADECYLTRICHLOROSILANE C₁₈H₃₇Cl₃Si contains <3% C₁₈ isomers highest concentration of terminal silane substitution</p> <p>HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [112-04-9] TSCA HMIS: 3-1-1-X</p>	387.93	160-2°/3 (22°)mp	0.950 ²²	1.4602
$\text{CH}_3(\text{CH}_2)_{16}\text{CH}_2-\text{Si}(\text{OC}_2\text{H}_5)_3$	<p>SIO6642.0 n-OCTADECYLTRIETHOXYSILANE, 95% C₂₄H₅₂O₃Si contains 5-10% C₁₈ isomers forms hydrophobic, oleophilic coatings</p> <p>HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [7399-00-0] HMIS: 2-1-0-X</p>	416.76	165-9°/0.2 (10-12°)mp flashpoint: >150°C (>302°F)	0.87	1.4386
$\text{CH}_3(\text{CH}_2)_{16}\text{CH}_2-\text{Si}(\text{OCH}_3)_3$	<p>SIO6645.0 n-OCTADECYLTRIMETHOXYSILANE, 95% C₂₁H₄₆O₃Si contains 5-10% C₁₈ isomers see also SIH5925.0 forms clear, ordered, films w/ tetramethoxysilane¹. 1. A. Shimjima et al, J. Am. Chem. Soc., 120, 4258, 1998.</p> <p>HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [3069-42-9] TSCA HMIS: 2-1-1-X</p>	374.68	170°/1 (13-17°)mp TOXICITY- oral rat, LD50: >5000mg/kg flashpoint: 140°C (284°F)	0.885	1.439
	<p>SIO6698.0 OCTAMETHYLCYCLOTETRASILAZANE C₈H₂₈N₄Si₄ ΔHform: 188 kcal/mole forms α-Si₃N₄ by ammonia thermal synthesis¹. 1. S. Schaible et al, Applied Organomet. Chem., 7, 53, 1993</p> <p>HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [1020-84-4] TSCA HMIS: 2-2-1-X</p>	292.68	225° (97°)mp flashpoint: 66°C (150°F)	0.950 ²²	1.458 ²⁵
$\text{CH}_3(\text{CH}_2)_6\text{CH}_2-\text{Si}(\text{CH}_3)_2\text{Cl}$	<p>SIO6710.5 n-OCTYLDIISOPROPYLCHLOROSILANE C₁₄H₃₁ClSi</p> <p>reagent for preparation of HPLC stationary phases w/high stability and efficiency¹. 1. J. Kirkland et al, J. Chrom. Sci., 32, 473, 1994.</p> <p>HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [117559-37-2] HMIS: 3-1-1-X</p>	262.94	95-9°/0.5 flashpoint: >110°C (>230°F)	0.875	1.4550
$\text{CH}_3(\text{CH}_2)_6\text{CH}_2-\text{Si}(\text{CH}_3)_2\text{N}(\text{CH}_3)_2$	<p>SIO6710.7 n-OCTYLDIISOPROPYL(DIMETHYLAMINO)- SILANE C₁₆H₃₇NSi</p> <p>HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [151613-25-1] TSCA HMIS: 3-2-1-X</p>	271.57	105°/0.7	0.833	1.4560











	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
$\begin{array}{c} \text{CH}_3 \\ \\ \text{CH}_3(\text{CH}_2)_6\text{CH}_2 - \text{Si} - \text{Cl} \\ \\ \text{CH}_3 \end{array}$	SIO6711.0 n-OCTYLDIMETHYLCHLOROSILANE C ₁₀ H ₂₃ ClSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18162-84-0] TSCA HMIS: 3-1-1-X	206.83	222-5° flashpoint: 97°C (207°F)	0.794	1.4328 ²⁵
$\begin{array}{c} \text{CH}_3 \\ \\ \text{CH}_3(\text{CH}_2)_6\text{CH}_2 - \text{Si} - \text{OCH}_3 \\ \\ \text{CH}_3 \end{array}$	SIO6711.1 OCTYLDIMETHYLMETHOXYSILANE C ₁₁ H ₂₆ O ₂ Si [93804-29-6] HMIS: 3-2-1-X	202.42	221-223° flashpoint: 82°C (181°F) 25g/\$84.00	0.813	1.4230
$\begin{array}{c} \text{CH}_3 \\ \\ \text{CH}_3(\text{CH}_2)_6\text{CH}_2 - \text{Si} - \text{N}(\text{CH}_3)_2 \\ \\ \text{CH}_3 \end{array}$	SIO6711.3 n-OCTYLDIMETHYL(DIMETHYLAMINO)SILANE C ₁₂ H ₂₉ NSi HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [2530-86-1] HMIS: 3-2-1-X	215.45	94-6°/10 flashpoint: 69°C (156°F) 25g/\$52.00	0.80 ²⁵	
$\begin{array}{c} \text{CH}_3(\text{CH}_2)_6\text{CH}_2 \\ \\ \text{H}_3\text{C} - \text{Si} \\ \quad \\ \text{Cl} \quad \text{Cl} \end{array}$	SIO6712.0 n-OCTYLMETHYLDICHLOROSILANE C ₉ H ₂₀ Cl ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [14799-93-0] TSCA HMIS: 3-2-1-X	227.25	94°/6 flashpoint: 98°C (209°F) 25g/\$20.00	0.9761	1.4440
$\begin{array}{c} \text{CH}_3(\text{CH}_2)_6\text{CH}_2 \\ \\ \text{H}_3\text{C} - \text{Si} \\ \quad \\ \text{OC}_2\text{H}_5 \quad \text{OC}_2\text{H}_5 \end{array}$	SIO6712.2 n-OCTYLMETHYLDIETHOXYSILANE C ₁₃ H ₃₀ O ₂ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [2652-38-2] HMIS: 2-2-0-X	246.47	80-2°/2 flashpoint: >110°C (>230°F) 25g/\$21.00	0.8478	1.4190
$\begin{array}{c} \text{CH}_3(\text{CH}_2)_6\text{CH}_2 \\ \\ \text{H}_3\text{C} - \text{Si} \\ \quad \\ \text{OCH}_3 \quad \text{OCH}_3 \end{array}$	SIO6712.4 n-OCTYLMETHYLDIMETHOXYSILANE C ₁₁ H ₂₆ O ₂ Si [85712-15-8] HMIS: 3-2-1-X	218.42	87-9°/5 flashpoint: 94°C (201°F) 25g/\$30.00	0.858	1.4190
$\begin{array}{c} \text{Cl} \\ \\ \text{CH}_3(\text{CH}_2)_6\text{CH}_2 - \text{Si} - \text{Cl} \\ \\ \text{Cl} \end{array}$	SIO6713.0 n-OCTYLTRICHLOROSILANE C ₈ H ₁₇ Cl ₃ Si vapor pressure, 140°: 2mm HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [5283-66-9] TSCA HMIS: 3-1-1-X	247.67	224-6° (<-50°)mp flashpoint: 96°C (204°F) 25g/\$11.00	1.0744	1.4490
$\begin{array}{c} \text{OC}_2\text{H}_5 \\ \\ \text{CH}_3(\text{CH}_2)_6\text{CH}_2 - \text{Si} - \text{OC}_2\text{H}_5 \\ \\ \text{OC}_2\text{H}_5 \end{array}$	SIO6715.0 n-OCTYLTRIETHOXYSILANE C ₁₄ H ₃₂ O ₃ Si viscosity: 1.9 cSt vapor pressure, 75°: 1mm may be formulated to stable water emulsions ¹ . 1. R. Depasquale et al, US Pat. 4,648,904, 1987. HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [2943-75-1] TSCA HMIS: 2-1-0-X	276.48	98-9°/2 (<-40°)mp flashpoint: 100°C (212°F) 50g/\$10.00 2.0kg/\$140.00 15kg/\$585.00	0.8750	1.4160
$\begin{array}{c} \text{OCH}_3 \\ \\ \text{CH}_3(\text{CH}_2)_6\text{CH}_2 - \text{Si} - \text{OCH}_3 \\ \\ \text{OCH}_3 \end{array}$	SIO6715.5 n-OCTYLTRIMETHOXYSILANE C ₁₁ H ₂₆ O ₃ Si vapor pressure, 75°: 0.1mm see also- SI6458.0 ISOCTYLTRIMETHOXYSILANE HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [3069-40-7] TSCA HMIS: 3-2-1-X	234.41	191-2° flashpoint: 68°C (154°F) 25g/\$10.00	0.907	1.417
$\begin{array}{c} \text{O} \\ \\ \text{CH}_3\text{C} - \text{O} - \text{Si} - \text{O} - \text{Si} - \text{CH}_3 \\ \quad \\ \text{CH}_3 \quad \text{CH}_3 \end{array}$	SIP6717.0 1,1,1,3,3-PENTAMETHYL-3-ACETOXY-DISILOXANE C ₇ H ₁₈ O ₃ Si ₂ HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [70693-47-9] TSCA HMIS: 2-2-1-X	206.39	149-50° flashpoint: 40°C (104°F) 10g/\$36.00	0.90	1.3887 ²⁵
$\begin{array}{c} \text{Cl} \\ \\ \text{C}_5\text{H}_{11}\text{Si} - \text{Cl} \\ \\ \text{Cl} \end{array}$	SIP6720.0 PENTYLTRICHLOROSILANE AMYLTRICHLOROSILANE mixed isomers C ₅ H ₁₁ Cl ₃ Si specific heat: 0.35 cal/g/° HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [107-72-2] TSCA HMIS: 3-3-1-X	209.59	171-2° flashpoint: 61°C (142°F) viscosity: 1.1 cSt. 25g/\$45.00	1.142	1.4456











PLEASE INQUIRE ABOUT BULK QUANTITIES

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SIP6720.2 PENTYLTRIEHOXYSILANE <i>AMYLTRIEHOXYSILANE</i> mixed isomers C ₁₁ H ₂₆ O ₃ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [2761-24-2] TSCA HMIS: 2-2-1-X	234.41	95-6°/1.3 flashpoint: 68°C (154°F) viscosity: 2.1 cSt	0.895	1.4059
	SIP6720.5 PERFLUORODODECYL-1H,1H,2H,2H-TRIEHOXY-SILANE -PERFLUOROTETRADECYL-1H,1H,2H,2H-TRIEHOXYSILANE MIXTURE, 80% (contains ~ 5% SIH5841.2, balance higher homologs) for the preparation of low surface energy substrates HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture HMIS: 2-1-1-X	710-810	157-198°/1.5 (70-85°)mp		
	SIP6720.7 PERFLUOROOCTYLPHENYLTRICHLOROSILANE C ₁₄ H ₄ Cl ₃ F ₁₇ Si thermally stable to >300° contact angle treated glass surface, water: 115°. ¹ 1. Y. Kondo, J. Oleoscience, <i>53</i> , 143, 2004 [753025-21-7] HMIS: 3-1-1-X	629.60	67-9°/3		
	SIP6720.8 PHENETHYLDIISOPROPYLCHLOROSILANE, C ₈ H ₂₂ ClSi contains α,β-isomers [151613-24-4] TSCA HMIS: 3-2-1-X	254.87	105-9°/0.3	0.97	
	SIP6721.0 PHENETHYLDIMETHYLCHLOROSILANE C ₁₀ H ₁₅ ClSi contains α,β-isomers see also SIP6724.7 HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [17146-08-6] TSCA HMIS: 3-2-1-X	198.77	56°/0.2 flashpoint: 70°C (158°F)	0.999	1.5185
	SIP6721.2 PHENETHYLDIMETHYL(DIMETHYLAMINO)-SILANE contains α,β-isomers C ₁₂ H ₂₁ NSi HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [181231-68-5] TSCA-L HMIS: 3-2-1-X	207.39	109°/2	0.890	
	SIP6721.5 PHENETHYLMETHYLDICHLOROSILANE <i>METHYL(PHENETHYL)DICHLOROSILANE</i> C ₉ H ₁₂ Cl ₂ Si contains α,β-isomers HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [17146-08-6] TSCA HMIS: 3-2-1-X	219.19	99°/6 flashpoint: 80°C (176°F)	1.127	1.5120
	SIP6722.0 PHENETHYLTRICHLOROSILANE C ₈ H ₉ Cl ₃ Si contains α,β-isomers HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [940-41-0] TSCA HMIS: 3-1-1-X	239.60	93-6°/3 TOXICITY- oral rat, LD50: 2830mg/kg flashpoint: 91°C (196°F)	1.240	1.5185
	SIP6722.6 PHENETHYLTRIMETHOXYSILANE C ₁₁ H ₁₈ O ₃ Si contains α,β-isomers HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [49539-88-0] TSCA HMIS: 3-1-1-X	226.35	95-6°/2 flashpoint: 109°C (228°F)	1.037	1.4753
	SIP6723.0 m-PHENOXYPHENYLDIMETHYLCHLORO-SILANE, 95% contains other isomers C ₁₄ H ₁₅ ClOSi end-capper for low-temperature lubricating fluids ¹ . 1. M. Gardos, ASLE Transactions, <i>18</i> , 31, 1972. HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents HMIS: 3-2-1-X	262.81	102-6°/1	1.11 ²⁵	1.5603 ²⁵
	SIP6723.2 3-PHENOXYPROPYLDIMETHYLCHLOROSILANE C ₁₁ H ₁₇ ClOSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [69733-73-9] HMIS: 3-2-1-X	228.78	90-2°/0.25 flashpoint: 109°C (228°F)		

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _b ²⁰
	SIP6723.25 3-PHENOXYPROPYLMETHYLDICHLOROSILANE C ₁₀ H ₁₄ OCl ₂ Si [28229-56-3] HMIS: 3-2-1-X	249.21	110°/1 25g/\$84.00		
	SIP6723.3 3-PHENOXYPROPYLTRICHLOROSILANE C ₉ H ₁₁ Cl ₃ Osi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [60333-76-8] HMIS: 3-2-1-X	269.63	40°/0.02 flashpoint: >110°C (>230°F) 25g/\$36.00	1.2574	1.5190
	SIP6723.4 11-PHENOXYUNDECYLTRICHLOROSILANE C ₁₇ H ₂₇ Cl ₃ Osi forms SAMs that orient pentacene [526204-46-6] HMIS: 3-1-1-X	381.85	5.0g/\$210.00		
	SIP6724.7 4-PHENYLBUTYLDIMETHYLCHLOROSILANE C ₁₂ H ₁₉ ClSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents HMIS: 3-2-1-X	226.83	85-7°/0.6 flashpoint: >110°C (>230°F) 25g/\$110.00	0.964	1.4979 ²⁵
	SIP6724.8 4-PHENYLBUTYLMETHYLDICHLOROSILANE C ₁₁ H ₁₆ Cl ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents HMIS: 3-2-1-X	247.24	105-9°/1.5 flashpoint: >110°C (>230°F) 25g/\$110.00	1.09 ²⁵	
	SIP6724.9 4-PHENYLBUTYLTRICHLOROSILANE C ₁₀ H ₁₃ Cl ₃ Si employed in bonded phases for HPLC HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [17886-88-3] TSCA HMIS: 3-2-1-X	267.06	82°/0.4 flashpoint: >110°C (>230°F) 25g/\$110.00	1.192	1.5121
	SIP6726.0 PHENYLDIMETHYLACETOXY-SILANE C ₁₀ H ₁₄ O ₂ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [17887-60-4] TSCA HMIS: 2-2-1-X	194.30	127-9°/44 flashpoint: 72°C (162°F) 25g/\$68.00	1.006	1.4907
	COMMERCIAL SIP6728.0 PHENYLDIMETHYLCHLOROSILANE C ₈ H ₁₁ ClSi vapor pressure, 25°: 1 mm viscosity: 1.4 cSt HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [768-33-2] TSCA HMIS: 3-2-1-X	170.71	192-3° flashpoint: 61°C (141°F) ΔHvap: 11.4 kcal/mole 25g/\$26.00 100g/\$84.00 2kg/\$700.00	1.032	1.5082
	SIP6728.4 PHENYLDIMETHYLETHOXY-SILANE C ₁₀ H ₁₆ Osi viscosity: 1.3 cSt dipole moment: 1.34 HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [1825-58-7] TSCA HMIS: 2-2-0-X	180.32	93°/25 TOXICITY- oral rat, LD50: 2460mg/kg flashpoint: 61°C (141°F) 10g/\$20.00 50g/\$80.00	0.926	1.4799
	SIP6730.0 PHENYLETHYLDICHLOROSILANE C ₈ H ₁₀ Cl ₂ Si ΔHvap: 11.9 kcal/mole HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [1125-27-5] TSCA HMIS: 3-2-1-X	205.16	225-6° flashpoint: 92°C (198°F) vapor pressure, 100°: 13mm 25g/\$110.00	1.184	1.5321
	SIP6736.4 6-PHENYLHEXYLTRICHLOROSILANE C ₁₂ H ₁₇ Cl ₃ Si [18035-33-1] HMIS: 3-1-1-X	295.71	95°/0.1 5.0g/\$96.00	1.5052 ²⁵	

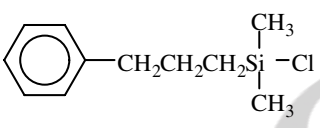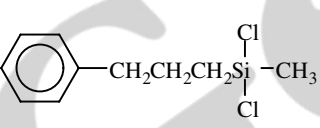PLEASE INQUIRE ABOUT BULK QUANTITIES











	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SIP6736.8 PHENYLMETHYLBIS(DIMETHYLAMINO)SILANE C ₁₁ H ₂₀ N ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [33567-83-8] HMIS: 3-2-1-X	208.38	108-9°/11 flashpoint: 78°C (172°F)		1.4982
	SIP6738.0 PHENYLMETHYLDICHLOROSILANE C ₇ H ₈ Cl ₂ Si vapor pressure, 82.5°: 13mm ΔHvap: 11.5 kcal/mole HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [149-74-6] TSCA HMIS: 3-2-1-X	191.13	205-6° (-53°)mp TOXICITY- ipr mus, LD50: 300mg/kg flashpoint: 82°C (180°F)	1.187	1.5180
	SIP6738.5 1-PHENYL-1-(METHYLDICHLOROSILYL)BUTANE C ₁₁ H ₁₆ Cl ₂ Si HMIS: 3-2-1-X	247.24	87-9°/1 flashpoint: >110°C(>230°F) 25g/\$120.00	1.10	1.5120
	SIP6739.0 PHENYLMETHYLDIETHOXSILANE C ₁₁ H ₁₈ O ₂ Si dipole moment: 1.32 HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [775-56-4] TSCA HMIS: 2-2-1-X	210.35	117-8°/31 flashpoint: 89°C (192°F)	0.963	1.4690
	SIP6740.0 PHENYLMETHYLDIMETHOXSILANE C ₉ H ₁₄ O ₂ Si viscosity, 20°: 1.65 cSt HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [3027-21-2] TSCA HMIS: 3-2-1-X	182.29	199-200° TOXICITY- oral rat, LD50: 892 mg/kg flashpoint: 76°C (168°F)	0.9934	1.4694
	SIP6743.0 (3-PHENYLPROPYL)DIMETHYLCHLOROSILANE C ₁₁ H ₁₇ ClSi see also SIP6724.7 HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [17146-09-7] TSCA HMIS: 3-1-1-X	212.78	75°/0.5 flashpoint: 103°C (216°F)	0.963	
	SIP6744.0 (3-PHENYLPROPYL)METHYLDICHLOROSILANE C ₁₀ H ₁₄ Cl ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [17776-66-8] HMIS: 3-2-1-X	233.21	96-8°/4 flashpoint: 102°C (216°F)	1.086 ²⁵	1.5090 ²⁵
	SIP6790.0 PHENYLTRIACETOXSILANE C ₁₂ H ₁₄ O ₆ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [18042-54-1] TSCA HMIS: 3-2-1-X	282.32	158°/30 flashpoint: 102°C (216°F)	1.194	1.4708
	SIP6810.0 PHENYLTRICHLOROSILANE C ₆ H ₅ Cl ₃ Si ΔHvap: 11.4 kcal/mole vapor pressure, 75°: 10mm surface tension: 27.9 dynes/cm specific heat: 0.24 cal/g° coefficient of thermal expansion: 1.2 x 10 ⁻³ HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [98-13-5] TSCA HMIS: 3-2-1-X	211.55	201° (-33°)mp TOXICITY- oral rat, LD50: 2340mg/kg flashpoint: 91°C (195°F) viscosity: 1.08 cSt dipole moment: 2.41 critical temperature: 438°	1.324	1.5247
	SIP6813.0 1-PHENYL-1-TRICHLOROSILYL BUTANE C ₁₀ H ₁₃ Cl ₃ Si HMIS: 3-2-1-X	267.65	78-80°/0.8 flashpoint: >110°C(>230°F) 10g/\$110.00	1.201	1.5180

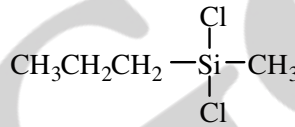	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SIP6821.0 PHENYLTRIETHOXSILANE C ₁₂ H ₂₀ O ₃ Si vapor pressure, 75°: 1mm coefficient of thermal expansion: 0.9 x 10 ⁻³ dipole moment: 1.85 debye viscosity, 25°: 1.7 cSt improves photoresist adhesion to silicon nitride effective treatment for organic-grafted clays ¹ . 1. K. Canrado et al, Chem. Mater. 13, 3766, 2001. HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture	240.37	112-3°/10	0.996	1.4718
	TOXICITY- oral rat, LD50: 2830mg/kg flashpoint: 96°C (205°F) surface tension 28 dynes/cm dielectric constant: 4.12				
	SIP6822.0 PHENYLTRIMETHOXSILANE C ₉ H ₁₄ O ₃ Si viscosity, 25°: 2.1 cSt vapor pressure, 108°: 20mm dipole moment: 1.77 intermediate for silicone resin coatings HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture	198.29	211° (-25°)mp	1.064	1.4734
	TOXICITY- ivn mus, LD50: 180mg/kg flashpoint: 86°C (187 °F) dielectric constant: 4.44				
	SIP6826.5 PHENYLTRIS(METHYLETHYLKETOXIMINO)- SILANE, 95% C ₁₈ H ₂₉ N ₃ O ₃ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture	363.53	60-5°/3 flashpoint: >61°C (>142°F)	0.995	
	SIP6910.0 n-PROPYLDIMETHYLCHLOROSILANE C ₅ H ₁₃ ClSi HYDROLYTIC SENSITIVITY: 8 Si-Cl reacts rapidly with water/moisture	136.70	113-4° flashpoint: 10°C (50°F)	0.8726	1.4138
	SIP6911.0 PROPYLDIMETHYLMETHOXSILANE C ₆ H ₁₆ OSi [18182-14-4] HMIS: 3-3-1-X	132.28	94-6°	0.787	1.3927 ²⁵
	SIP6912.0 n-PROPYLMETHYLDICHLOROSILANE C ₄ H ₁₀ Cl ₂ Si viscosity, 20°: 0.8 cSt. HYDROLYTIC SENSITIVITY: 8 Si-Cl reacts rapidly with water/moisture	157.11	125° flashpoint: 27°C (81°F)	1.027	1.425
	SIP6914.0 PROPYLMETHYLDIMETHOXSILANE C ₆ H ₁₆ O ₂ Si [18173-73-4] HMIS: 3-3-1-X	148.28	126°	0.8689	1.3931
	SIP6915.0 n-PROPYLTRICHLOROSILANE C ₃ H ₇ Cl ₃ Si vapor pressure, 16°: 10mm HYDROLYTIC SENSITIVITY: 8 Si-Cl reacts rapidly with water/moisture	177.53	123-4° flashpoint: 35°C (95°F) ΔHvap: 8.7 kcal/mole	1.185	1.4290
	SIP6917.0 n-PROPYLTRIETHOXSILANE C ₉ H ₂₂ O ₃ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture	206.36	179-80° flashpoint: 57°C (135°F)	0.8916	1.3956
	SIP6918.0 n-PROPYLTRIMETHOXSILANE C ₆ H ₁₆ O ₃ Si γc of treated surface: 28.5 dynes/cm utilized in architectural hydrophobic coatings HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture	164.27	142° flashpoint: 34°C (93°F)	0.932 ²⁵	1.3880

PLEASE INQUIRE ABOUT BULK QUANTITIES

HYDROPHOBIC
COMMERCIAL

name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
SIS6952.0 SILICLAD® OCTADECYL FUNCTIONAL SILANE flashpoint: 25°C (77°F) 20% in <i>t</i> -AMYL ALCOHOL and DIACETONE ALCOHOL amber liquid γc of treated glass surface: 31 dynes/cm coefficient of friction of treated glass surface: 0.2-0.3 surface resistivity of treated surface: 1.2 x 10 ¹³ ohms reduces blood protein adsorption ¹ . hydrophobic, anti-stiction coating for silicon substrates ² . 1. B. Arkles et al, in "Silanes Surfaces & Interfaces" D. Leyden ed, Gordon & Breach, 1986, p 91. 2. A. Almanza-Workman et al, J. Electro Chem. Soc. 149, H6, 2002 for application information see Performance Products Brochure HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture			0.88	
[39443-39-5] TSCA HMIS: 2-3-1-X	100g/\$20.00	1.5kg/\$172.00	15kg/\$480.00	
SIS6984.0 SODIUM METHYLSILICONATE, 30% in water CH ₅ NaO ₃ Si	116.12		1.24	
[16589-43-8] TSCA HMIS: 3-0-0-X	500g/\$17.00	2.0kg/\$50.00	20kg/\$420.00	
SIT7093.0 TETRADECYLTRICHLOROSILANE C ₁₄ H ₂₉ Cl ₃ Si	331.83	155-6°/3		1.4575
[18402-22-7] TSCA HMIS: 3-1-1-X	25g/\$80.00			
SIT7095.0 1,1,3,3-TETRAETHOXY-1,3-DIMETHYL-DISILOXANE, 95% C ₁₀ H ₂₆ O ₅ Si ₂ HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture	282.48	205° flashpoint: 58°C (136°F)	0.953	1.3912
[18001-60-0] HMIS: 3-3-1-X	25g/\$57.00			
SIT7534.0 1,1,3,3-TETRAMETHYL-1,3-DIETHOXYSILOXANE C ₈ H ₂₂ O ₃ Si ₂ viscosity: 1.0 cSt HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture	222.43	161° (-134°)mp flashpoint: 38°C (100°F)	0.879	1.3880
[18420-09-2] TSCA HMIS: 2-2-0-X	25g/\$28.00		100g/\$90.00	
SIT7753.0 1,1,3,3-TETRAPHENYLDIMETHYLDISILAZANE C ₂₆ H ₂₇ NSi ₂	409.68	218-220°/1.5 (91°)mp flashpoint: >110°C (>230°F)		
[7453-26-1] TSCA-L HMIS: 2-1-0-X	5.0g/\$25.00		25g/\$102.00	
SIT7906.0 THEXYLDIMETHYLCHLOROSILANE <i>t</i> -HEXYLDIMETHYLCHLOROSILANE C ₈ H ₁₉ ClSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents, protic solvents	178.78	55-6°/10 (14-15°)mp flashpoint: 51°C (125°F)	0.911	1.4490
[67373-56-2] HMIS: 3-2-1-X	5.0g/\$16.00		25g/\$64.00	
SIT7906.6 THEXYLTRICHLOROSILANE C ₆ H ₁₃ Cl ₃ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents, protic solvents	219.61	70-2°/15		
[18151-53-6] HMIS: 3-3-1-X	10g/\$101.00			
SIT8030.0 p-TOLYLDIMETHYLCHLOROSILANE C ₉ H ₁₃ ClSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents, protic solvents	184.74	215-7° flashpoint: 67°C (153°F)	1.007 ²⁵	1.5055
[35239-30-6] TSCA HMIS: 3-2-1-X	5.0g/\$37.00			
SIT8035.0 p-TOLYLMETHYLDICHLOROSILANE C ₈ H ₁₀ Cl ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents, protic solvents	205.16	161-5°/7 flashpoint: 80°C (176°F)	1.1609	1.5330
[25898-37-7] TSCA HMIS: 3-2-1-X	25g/\$114.00			

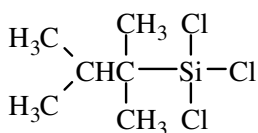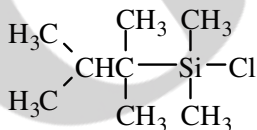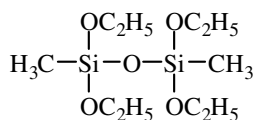

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SIT8040.0 p-TOLYLTRICHLOROSILANE C ₇ H ₇ Cl ₃ Si γc of treated surface: 34 dynes/cm HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents, protic solvents [701-35-9] TSCA HMIS: 3-2-1-X	225.58	218-20° flashpoint: 92°C (197°F)	1.28	1.5224 ²⁵
	SIT8042.0 p-TOLYLTRIMETHOXYSILANE C ₁₀ H ₁₆ O ₃ Si γc of treated surface: 34 dynes/cm charge control surface treatment for electrostatic copier particles ¹ . 1. H. Yamazaki, Jpn. Kokai, JP 06027719 A2, 1994. HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [17873-01-7] HMIS: 3-1-1-X	212.32	75-8°/8 flashpoint: 94°C (201°C)	1.033	1.4726 ²⁵
	SIT8045.0 TRIACONTYLDIMETHYLCHLOROSILANE, blend C ₃₂ H ₆₇ ClSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents, protic solvents [70851-52-4] TSCA HMIS: 3-1-0-X	515.42	(60-82°)mp 80% C ₃₀ and higher, 20% C ₂₂ -C ₂₈		100g/\$169.00
	SIT8048.0 TRIACONTYLTRICHLOROSILANE, blend C ₃₀ H ₆₁ Cl ₃ Si employed in bonded phases for HPLC of carotenes HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents, protic solvents [70851-48-8] TSCA HMIS: 3-1-1-X	556.26	(60-82°)mp 80% C ₃₀ and higher, 20% C ₂₂ -C ₂₈		100g/\$169.00
	SIT8162.0 13-(TRICHLOROSILYL METHYL)HEPTACOSANE, 95% 2-DODECYLHEXADECYLTRICHLOROSILANE C ₂₈ H ₅₇ Cl ₃ Si contains isomers HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [194242-99-4] TSCA-L HMIS: 3-1-1-X	528.21	215°/0.01 (20-35°)mp	0.946	10g/\$127.00
	SIT8162.4 7-(TRICHLOROSILYL METHYL)PENTADECANE C ₁₆ H ₃₃ Cl ₃ Si 2-HEXYLDECYLTRICHLOROSILANE HMIS: 3-1-1-X	359.88	146-9°/0.2	0.985	10g/\$174.00
	SIT8170.0 (TRIDECAFLUORO-1,1,2,2-TETRAHYDRO-OCTYL)DIMETHYLCHLOROSILANE C ₁₀ H ₁₀ ClF ₁₃ Si PERFLUORO-OCTYL-1H,1H,2H,2H-DIMETHYLCHLOROSILANE employed in column chromatography where low protein retention is required ¹ . employed in solid phase extraction of fluoruous phases ² . modification of layered silicate yields material w/ film forming properties ³ . 1. G. Xindu et al, J. Chromatog, 269, 96, 1983. 2. D. Curran, J. Org. Chem. 62,6714, 1997. 3. M. Ogawa et al, Chem. Mater., 10, 3787, 1998. HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [102488-47-1] HMIS: 3-3-1-X	440.70	189-91° flashpoint: 52°C (127°F)	1.473	1.3453
	SIT8172.0 (TRIDECAFLUORO-1,1,2,2-TETRAHYDRO-OCTYL)METHYLDICHLOROSILANE C ₉ H ₇ Cl ₂ F ₁₃ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [73609-36-6] HMIS: 3-3-1-X	461.12	189-90° flashpoint: 51°C (125°F) vapor pressure, 76°: 12mm	1.550 ²⁵	1.3500
	SIT8174.0 (TRIDECAFLUORO-1,1,2,2-TETRAHYDRO-OCTYL)TRICHLOROSILANE C ₈ H ₄ Cl ₃ F ₁₃ Si lowers the coefficient of friction of silicon substrates ¹ . 1. V. DePalma et al, Langmuir, 5, 868, 1989. HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [78560-45-9] TSCA-L HMIS: 3-3-1-X	481.55	84-5°/17 flashpoint: 54°C (129°F)	1.639	1.3521
	SIT8175.0 (TRIDECAFLUORO-1,1,2,2-TETRAHYDRO-OCTYL)TRIETHOXYSILANE C ₁₄ H ₁₉ F ₁₃ O ₃ Si viscosity: 3.5 cSt. HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [51851-37-7] TSCA HMIS: 2-2-1-X	510.36	86°/1.5 (<-38°)mp flashpoint: 84°C (183°F) ΔHvap: 66.1 kJ/mole	1.351	1.3436

COMMERCIAL










	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
$\begin{array}{c} \text{OCH}_3 \\ \\ \text{CF}_3\text{CF}_2\text{CF}_2\text{CF}_2\text{CF}_2\text{CF}_2\text{CF}_2\text{CH}_2\text{CH}_2\text{Si}-\text{OCH}_3 \\ \\ \text{OCH}_3 \end{array}$	SIT8176.0 (TRIDECAFLUORO-1,1,2,2-TETRAHYDRO-OCTYL)TRIMETHOXYSILANE C ₁₁ H ₁₃ F ₁₃ O ₃ Si HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [85857-16-5] HMIS: 3-1-1-X	468.29	60-2°/0.5	1.44	1.3322
$\begin{array}{c} \text{Cl} \\ \\ \text{CF}_3\text{CH}_2\text{CH}_2-\text{Si}-\text{CH}_3 \\ \\ \text{Cl} \end{array}$	SIT8369.0 (3,3,3-TRIFLUOROPROPYL)METHYL-DICHLOROSILANE C ₄ H ₇ Cl ₂ F ₃ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [675-62-7] TSCA HMIS: 3-4-1-X	211.08	121-2°	1.2611	1.3850
$\begin{array}{c} \text{Cl} \\ \\ \text{CF}_3\text{CH}_2\text{CH}_2-\text{Si}-\text{Cl} \\ \\ \text{Cl} \end{array}$	SIT8371.0 (3,3,3-TRIFLUOROPROPYL)TRICHLOROSILANE C ₃ H ₄ Cl ₃ F ₃ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [592-09-6] TSCA HMIS: 3-4-1-X	231.50	113-4° flashpoint: 15°C (59°F)	1.395	1.385
$\begin{array}{c} \text{OCH}_3 \\ \\ \text{CF}_3\text{CH}_2\text{CH}_2-\text{Si}-\text{OCH}_3 \\ \\ \text{OCH}_3 \end{array}$	SIT8372.0 (3,3,3-TRIFLUOROPROPYL)TRIMETHOXYSILANE C ₆ H ₁₃ F ₃ O ₃ Si HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [429-60-7] TSCA HMIS: 3-3-1-X	218.25	144° flashpoint: 38°C (100°F) γc of treated surface: 33.5 dynes/cm	1.137	1.3546
$\begin{array}{c} \text{CH}_3 \\ \\ \text{Cl}-\text{Si}-\text{CH}_3 \\ \\ \text{CH}_3 \end{array}$	SIT8510.0 TRIMETHYLCHLOROSILANE C ₃ H ₉ ClSi <i>TMCS</i> vapor pressure, 20°: 190mm; 50°: 591 mm ΔHvap: 6.6 kcal/mole most economical and broadly used silylation reagent [75-77-4] TSCA HMIS: 3-4-2-X	108.64	57.6° (-57.7°)mp flashpoint: -27°C (-17°F) autoignition temperature: 395°	0.8580	1.3885
$\begin{array}{c} \text{CH}_3 \\ \\ \text{C}_2\text{H}_5\text{O}-\text{Si}-\text{CH}_3 \\ \\ \text{CH}_3 \end{array}$	SIT8515.0 TRIMETHYLETHOXYSILANE ETHOXYTRIMETHYLSILANE C ₅ H ₁₄ O ₂ Si dipole moment: 1.2 ΔHcomb: 970.4 kcal/mole critical temperature: 233° HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [1825-62-3] TSCA HMIS: 2-4-1-X	118.25	75-6° (-83°)mp flashpoint: -27°C (-17°F) vapor pressure, 25°: 111mm ΔHvap: 33.5 kcal/mole	0.7573	1.3742
$\begin{array}{c} \text{CH}_3 \\ \\ \text{CH}_3\text{O}-\text{Si}-\text{CH}_3 \\ \\ \text{CH}_3 \end{array}$	SIT8566.0 TRIMETHYLMETHOXYSILANE C ₄ H ₁₂ O ₂ Si dipole moment: 1.18 debye HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [1825-61-2] TSCA HMIS: 3-4-1-X	104.22	57-8° flashpoint: -11°C (12°F)	0.7560	1.3678
$\begin{array}{c} \text{CH}_3 \quad \text{Cl} \\ \quad \\ \text{H}_3\text{C}-\text{Si}-\text{O}-\text{Si}-\text{Cl} \\ \quad \\ \text{CH}_3 \quad \text{Cl} \end{array}$	SIT8572.6 TRIMETHYLSILOXYTRICHLOROSILANE C ₃ H ₉ Cl ₃ O ₂ Si ₂ [2750-45-0] HMIS: 3-4-1-X	223.63	128° flashpoint: 16°C (61°F)	1.126	
$\begin{array}{c} \text{H}_3\text{C} \quad \text{CH}_3 \\ \quad \\ \text{N} \quad \text{N} \\ \quad \\ \text{CH}_3-\text{Si}-\text{N} \\ \quad \\ \text{H}_3\text{C} \quad \text{CH}_3 \end{array}$	SIT8712.0 TRIS(DIMETHYLAMINO)METHYLSILANE C ₇ H ₂₁ N ₃ Si HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [3768-57-8] TSCA HMIS: 3-3-1-X	175.35	55-6°/17 (-11°)mp flashpoint: 30°C (86°F)	0.850 ²²	1.432 ²²
$\begin{array}{c} \text{CH}_3 \\ \\ \text{H}_3\text{C}-\text{Si}-\text{CH}_3 \\ \\ \text{O} \\ \\ \text{Si} \\ \\ \text{O} \\ \\ \text{H}_3\text{C}-\text{Si}-\text{CH}_3 \\ \\ \text{Cl} \end{array}$	SIT8719.5 [TRIS(TRIMETHYLSILOXY)SILYLETHYL]DIMETHYL-CHLOROSILANE C ₁₃ H ₃₇ O ₃ ClSi ₅ forms hydrophobic monolayers HYDROLYTIC SENSITIVITY: 8 Si-Cl reacts rapidly with water/moisture, protic solvents HMIS: 3-2-1-X	417.32	85°/0.6	0.906	1.43175
$\text{CH}_3(\text{CH}_2)_9\text{CH}_2\text{SiCl}_3$	SIU9050.0 UNDECYLTRICHLOROSILANE C ₁₁ H ₂₃ Cl ₃ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18052-07-8] HMIS: 3-1-1-X	289.75	155-60°/15 flashpoint: 107°C (225°)	1.02	

HYDROPHOBIC

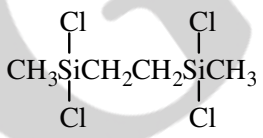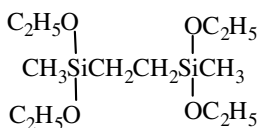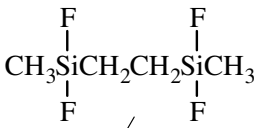COMMERCIAL


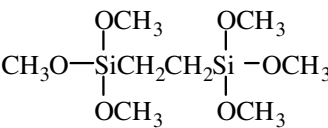
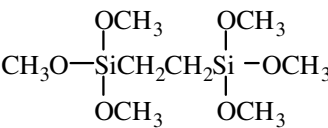

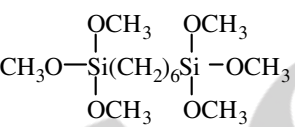


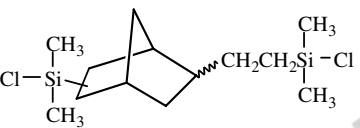

Hydrophobic Dipodal Silanes

Dipodal Surface Bonding

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SIB1030.0 BIS[2-(CHLORODIMETHYLSILYL)-ETHYL]BENZENE mixed isomers C ₁₄ H ₂₄ Cl ₂ Si ₂ intermediate for silahydrocarbon polymers HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [74129-20-7] TSCA HMIS: 3-1-1-X	319.42	116-7°/0.2 flashpoint: 187°C (369°F)	1.02	
			50g/\$204.00		
	SIB1042.0 1,2-BIS(CHLORODIMETHYLSILYL)ETHANE TETRAMETHYLDICHLORODISILETHYLENE C ₆ H ₁₆ Cl ₂ Si ₂ reagent for protection of primary amines, including amino acids ¹ . 1. S. Djuric et al, Tet. Lett., 22, 1787, 1981 HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [13528-93-3] TSCA HMIS: 3-2-1-X	215.27	198-9° (36-9°)mp flashpoint: 40°C (104°F)		
			25g/\$21.00	100g/\$68.00	
	SIB1046.0 1,6-BIS(CHLORODIMETHYLSILYL)HEXANE, 95% C ₁₀ H ₂₄ Cl ₂ Si ₂ HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [14799-66-7] HMIS: 3-1-1-X	271.38	113-6°/3 flashpoint: 150°C (302°F)	0.961	1.4538
			25g/\$52.00	100g/\$169.00	
	SIB1048.0 1,8-BIS(CHLORODIMETHYLSILYL)OCTANE, 95% C ₁₂ H ₂₈ Cl ₂ Si ₂ intermediate for sila-hydrocarbon polymers HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [5089-28-1] HMIS: 3-1-1-X	299.43	106-7°/0.4 flashpoint: 180°C (356°F)	0.946	1.4540
			25g/\$41.00	100g/\$134.00	
	SIB1048.2 1,3-BIS(CHLORODIMETHYLSILYL)PROPANE C ₇ H ₁₈ Cl ₂ Si ₂ forms cyclic derivatives of polyalkyleneoxides suitable for anionic copolymerization ¹ . 1. T. Zundel et al, Macromol, 31, 2724, 1998 HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [2295-06-9] HMIS: 3-2-1-X	229.30	94°/19	1.0244	1.4647
			5.0g/\$102.00		
	SIB1614.0 BIS(METHYLDICHLOROSILYL)ETHANE 1,4-DIMETHYL-1,1,4,4-TETRACHLORO-1,4-DISILABUTANE C ₄ H ₁₀ Cl ₄ Si ₂ dipodal coupling agent HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [3353-69-3] TSCA HMIS: 3-2-1-X	256.11	208-210° (31-3°)mp flashpoint: 94°C (201°F)	1.2628	1.4760
			25g/\$31.00	100g/\$100.00	
	SIB1615.0 BIS(METHYLDIETHOXY-SILYL)ETHANE C ₁₂ H ₃₀ O ₄ Si ₂ [18043-74-8] HMIS: 2-2-1-X	294.54	80°/1.5	0.92	1.4170
			25g/\$62.00		
	SIB1630.0 BIS(METHYLDIFLUOROSILYL)ETHANE C ₄ H ₁₀ F ₄ Si ₂ HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents HMIS: 3-3-1-X	190.29	114°	1.118	
			10g/\$69.00		
	SIB1808.0 1,2-BIS(TRICHLOROSILYL)DECANE C ₁₀ H ₂₀ Cl ₆ Si ₂ [62987-03-3] HMIS: 3-2-1-X	409.16	114°/1	1.2496	1.4754
			25g/\$85.00		

PLEASE INQUIRE ABOUT BULK QUANTITIES

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
$\begin{array}{c} \text{CF}_2\text{CF}_2\text{CF}_2\text{CF}_2\text{CF}_2\text{CF}_2\text{CF}_2\text{CF}_2\text{CF}_2 \\ \qquad \qquad \qquad \\ \text{CH}_2 \qquad \qquad \qquad \text{CH}_2 \\ \qquad \qquad \qquad \\ \text{SiCl}_3 \qquad \qquad \qquad \text{SiCl}_3 \end{array}$	SIB1811.5 1,8-BIS(TRICHLOROSILYLETHYL)HEXA-DECAFLUOROCTANE C ₁₂ H ₈ Cl ₆ F ₁₆ Si ₂ HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [445303-83-3] HMIS: 3-1-1-X	725.06	142-4°/0.6 (69-70°)mp		
$\begin{array}{c} \text{Cl} \qquad \qquad \text{Cl} \\ \qquad \qquad \\ \text{Cl}-\text{Si}(\text{CH}_2)_6-\text{Si}-\text{Cl} \\ \qquad \qquad \\ \text{Cl} \qquad \qquad \text{Cl} \end{array}$	SIB1812.0 BIS(TRICHLOROSILYL)HEXANE C ₆ H ₁₂ Cl ₆ Si ₂ forms mesoporous sol-gel structures HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [13083-94-8] TSCA HMIS: 3-2-1-X	353.05	148-50°/10 flashpoint: 75°C (167°F)	1.327	1.4759
$\begin{array}{c} \text{Cl} \qquad \qquad \text{Cl} \\ \qquad \qquad \\ \text{Cl}-\text{SiCH}_2\text{Si}-\text{Cl} \\ \qquad \qquad \\ \text{Cl} \qquad \qquad \text{Cl} \end{array}$	SIB1813.0 BIS(TRICHLOROSILYL)METHANE CH ₂ Cl ₆ Si ₂ nucleus for star polymers and dendrimers HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [4142-85-2] HMIS: 3-2-1-X	282.9	183°	1.5567	1.4740
$\begin{array}{c} \text{Cl} \qquad \qquad \text{Cl} \\ \qquad \qquad \\ \text{Cl}-\text{Si}(\text{CH}_2)_8-\text{Si}-\text{Cl} \\ \qquad \qquad \\ \text{Cl} \qquad \qquad \text{Cl} \end{array}$	SIB1814.0 BIS(TRICHLOROSILYL)OCTANE C ₈ H ₁₆ Cl ₆ Si ₂ forms mesoporous sol-gel structures HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [52217-53-5] HMIS: 3-1-1-X	381.10	140°/1 flashpoint: 115°C (240°F)	1.22	1.4757
$\begin{array}{c} \text{Cl} \qquad \qquad \text{Cl} \\ \qquad \qquad \\ \text{Cl}-\text{SiCH}_2\text{CH}_2\text{CH}_2\text{Si}-\text{Cl} \\ \qquad \qquad \\ \text{Cl} \qquad \qquad \text{Cl} \end{array}$	SIB1815.0 1,3-BIS(TRICHLOROSILYL)PROPANE C ₃ H ₆ Cl ₆ Si ₂ forms mesoporous sol-gel structures HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18171-50-1] HMIS: 3-2-1-X	310.97	115-7°/4 (29-30°)mp	1.4394	1.4732
$\text{Cl}_3\text{Si}-(\text{CH}_2)_{11}\text{O}(\text{CH}_2)_{11}-\text{SiCl}_3$	SIB1815.4 BIS(TRICHLOROSILYLUNDECYL)ETHER C ₂₂ H ₄₄ Cl ₆ O ₂ Si ₂ HMIS: 3-1-1-X	593.48			
$\begin{array}{c} \text{C}_2\text{H}_5\text{O} \qquad \text{OC}_2\text{H}_5 \\ \qquad \qquad \\ \text{C}_2\text{H}_5\text{O}-\text{Si}-\text{C}_6\text{H}_4-\text{Si}-\text{OC}_2\text{H}_5 \\ \qquad \qquad \\ \text{C}_2\text{H}_5\text{O} \qquad \text{OC}_2\text{H}_5 \end{array}$	SIB1816.6 1,4-BIS(TRIETHOXYMETHYLBENZENE) C ₁₈ H ₃₄ O ₆ Si ₂ forms thermally stable hybrid silica fibers ¹ . 1. Y. Yang et al, Chem. Mater., 18, 1324, 2006 HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [52217-60-4] HMIS: 2-2-1-X	402.64	130-2°/0.4	1.015	1.4549
$\begin{array}{c} \text{OC}_2\text{H}_5 \qquad \text{OC}_2\text{H}_5 \\ \qquad \qquad \\ \text{C}_2\text{H}_5\text{O}-\text{SiCH}_2\text{CH}_2\text{Si}-\text{OC}_2\text{H}_5 \\ \qquad \qquad \\ \text{OC}_2\text{H}_5 \qquad \text{OC}_2\text{H}_5 \end{array}$	SIB1817.0 BIS(TRIETHOXYMETHYLENE)ETHANE HEXAETHOXYDISILETHYLENE C ₁₄ H ₃₄ O ₆ Si ₂ ΔHvap: 101.5 kJ/mole additive to silane coupling agent formulations that enhances hydrolytic stability employed in corrosion-resistant coatings/primer for steel and aluminum ^{1,2} . sol-gels of α,ω-bis(trimethoxysilyl)alkanes reported ³ . forms mesoporous, derivatizable molecular sieves ⁴ . 1. W. Van Ooij et al, J. Adhes. Sci. Tech. 11, 29, 1997. 2. W. Van Ooij et al, Chemtech., 28, 26, 1998. 3. D. A. Loy et al, J. Am. Chem. Soc., 121, 5413, 1999. 4. B. Molde et al, Chem. Mat., 11, 3302, 1999. HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [16068-37-4] TSCA-S HMIS: 3-1-1-X	354.59	96°/0.3 flashpoint: 107°C (225°F) vapor pressure, 150°: 10mm TOXICITY - oral rat, LD50: 161mg/kg	0.957	1.4052
$\begin{array}{c} \text{OEt} \qquad \text{OEt} \\ \qquad \qquad \\ \text{EtO}-\text{SiCH}_2\text{Si}-\text{OEt} \\ \qquad \qquad \\ \text{OEt} \qquad \text{OEt} \end{array}$	SIB1821.0 BIS(TRIETHOXYMETHYLENE)METHANE 4,4,6,6-TETRAETHOXY-3,7-DIOXA-4,6-DISILANONANE C ₁₃ H ₃₂ O ₆ Si ₂ intermediate for sol-gel coatings, hybrid inorganic-organic polymers HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [18418-72-9] HMIS: 2-3-0-X	340.56	114-5°/3.5	0.9741	1.4098

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
$(C_2H_5O)_3Si(CH_2)_8Si(OC_2H_5)_3$ 	SIB1824.0 BIS(TRIETHOXYSILYL)OCTANE C ₂₀ H ₄₆ O ₆ Si ₂ employed in sol-gel synthesis of mesoporous structures sol-gels of α, ω-bis(trimethoxysilyl)alkanes reported ¹ . 1. D. A. Loy et al, J. Am. Chem. Soc., 121, 5413, 1999. HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [52217-60-4] TSCA-L HMIS: 2-1-1-X	438.76	172-5°/0.75	0.926	1.4240
	25g/\$30.00	100g/\$98.00			
	SIB1829.0 1,2-BIS(TRIMETHOXYSILYL)DECANE C ₁₆ H ₃₈ O ₆ Si ₂ pendant dipodal silane; employed in high pH HPLC HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture HMIS: 3-2-1-X	382.65	130-2°/0.4	0.984	1.4303
	25g/\$51.00	100g/\$165.00			
	SIB1830.0 BIS(TRIMETHOXYSILYL)ETHANE C ₈ H ₂₂ O ₆ Si ₂ flashpoint: 65° (149°F) vapor pressure, 20°: 0.08mm CAUTION: INHALATION HAZARD employed in fabrication of multilayer printed circuit boards 1. J. Palladino, U.S. Pat. 5,073,456, 1991. see also SIB1817.0 HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [18406-41-2] TSCA HMIS: 4-2-1-X	270.43	103-4°/5	1.068	1.4091
	25g/\$64.00	100g/\$208.00			
	SIB1831.0 BIS(TRIMETHOXYSILYLETHYL)BENZENE C ₁₆ H ₃₀ O ₆ Si ₂ mixed isomers flashpoint: 193°C (380°F) HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [58298-01-4] TSCA HMIS: 2-1-0-X	374.58	148-50°/1	1.08	1.4734
	10g/\$33.00	50g/\$132.00			
	SIB1832.0 1,6-BIS(TRIMETHOXYSILYL)HEXANE C ₁₂ H ₃₀ O ₆ Si ₂ sol-gels of α, ω-bis(trimethoxysilyl)alkanes reported ¹ . 1. D. A. Loy et al, J. Am. Chem. Soc., 121, 5413, 1999. HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [87135-01-1] HMIS: 3-2-1-X	326.54	161°/2	1.014	1.4213
	10g/\$38.00	50g/\$152.00			
	SIB1832.2 p-BIS(TRIMETHOXYSILYLMETHYL)BENZENE C ₁₄ H ₂₆ O ₆ Si ₂ HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [193358-40-6] HMIS: 3-1-1-X	346.53	124-5°/0.05	1.097	1.470 ²⁵
	10g/\$180.00				
	SIB1833.4 BIS-1,3-(TRIMETHOXYSILYL)PROPYL)-BENZENE C ₁₈ H ₃₄ O ₆ Si ₂ HMIS: 3-2-1-X	402.64			
	5.0g/\$145.00				
	SIC2265.5 (CHLORODIMETHYLSILYL)-6-[2-(CHLORODIMETHYLSILYL)ETHYL]BICYCLOHEPTANE mixture of 1 and 2 regio isomers, exo and endo C ₁₃ H ₂₆ Cl ₂ Si ₂ forms polymers HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture HMIS: 3-2-1-X	309.43		1.03	1.4863
	25g/\$48.00				
	COMMERCIAL SIT8185.8 1-(TRIETHOXYSILYL)-2-(DIETHOXYMETHYLSILYL)ETHANE C ₁₃ H ₃₂ O ₅ Si dipodal silane; forms abrasion-resistant sol-gel coatings HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [18418-54-7] TSCA HMIS: 3-2-1-X	324.56	100°/0.5	0.946	1.4112
	25g/\$40.00	100g/\$130.00	2kg/\$840.00		

PLEASE INQUIRE ABOUT BULK QUANTITIES

Polymeric Hydrophobic Silanes

Polymeric Surface Bonding

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	Polybutadiene SSP-055 TRIETHOXY-SILYL MODIFIED POLY-1,2-BUTADIENE, 50% in toluene viscosity: 100-200 cSt. coupling agent for EPDM resins	3500-4500		0.90	
	[72905-90-9] TSCA HMIS: 2-4-1-X store <5°	100g/\$60.00		2.0kg/\$780.00	
	SSP-056 TRIETHOXY-SILYL MODIFIED POLY-1,2-BUTADIENE, 50% in volatile silicone viscosity: 100-200 cSt. primer coating for silicone rubbers	3500-4500		0.93	
	[72905-90-9] TSCA HMIS: 2-3-1-X store <5°	100g/\$68.00			
	SSP-058 DIETHOXYMETHYLSILYL MODIFIED POLY-1,2-BUTADIENE, 50% in toluene viscosity: 75-150 cSt. water tree resistance additive for crosslinkable HDPE cable cladding	3500-4500		0.90	
	HMIS: 2-4-1-X store <5°	100g/\$86.00			
	SSP-255 (30-35% TRIETHOXY-SILYLETHYL)ETHYLENE- (35-40% 1,4-BUTADIENE) - (25-30% STYRENE) terpolymer, 50% in toluene viscosity: 20-30 cSt.	4500-5500			
	HMIS: 2-3-1-X	100g/\$86.00			

Reactive Polydimethylsiloxane Oligomers

Chlorine Terminated PolyDimethylsiloxanes

CAS: [67923-13-1] TSCA

Code	Viscosity	Molecular Weight	Specific Gravity	Price/100g	Price/1kg
DMS-K05	3 - 6	425-600	1.00	\$55.00	\$358.00
DMS-K13	20-50	2000-4000	0.99	\$120.00	
DMS-K26	500-800	15,000-20,000	0.99	\$94.00	

Dimethylamino Terminated PolyDimethylsiloxanes

CAS: [67762-92-9] TSCA

Code	Viscosity	Molecular Weight	Specific Gravity	Price/100g
DMS-N05	3 - 8	450-600	0.93	\$160.00

Ethoxy Terminated PolyDimethylsiloxanes

CAS: [70851-25-1] TSCA

Code	Viscosity	Molecular Weight	Specific Gravity	Price/100g	Price/1kg
DMS-XE11	5-10	800-900	0.94	\$32.00	\$210.00

Methoxy Terminated PolyDimethylsiloxanes

CAS: [68951-97-3] TSCA

Code	Viscosity	Molecular Weight	Specific Gravity	Price/100g	Price/1kg
DMS-XM11	5-12	900-1000	0.94	\$29.00	\$188.00

Silanol Terminated PolyDimethylsiloxanes

CAS: [70131-67-8] TSCA

Code	Viscosity	Molecular Weight	% (OH)	(OH) - Eq/kg	Specific Gravity	Refractive Index	Price/100g	Price/3kg	Price/16kg
DMS-S12	16-32	400-700	4.5-7.5	2.3-3.5	0.95	1.401	\$19.00	\$124.00	\$496.00
DMS-S14	35-45	700-1500	3.0-4.0	1.7-2.3	0.96	1.402	\$18.00	\$117.00	\$460.00
DMS-S15	45-85	2000-3500	0.9-1.2	0.53-0.70	0.96	1.402	\$18.00	\$117.00	\$460.00

Hydrophilic Silane Properties

Polar - Non-hydrogen Bonding

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
$\begin{array}{c} \text{NCCH}_2\text{CH}_2\text{CH}_2 \diagdown \\ \text{Si} \\ \text{NCCH}_2\text{CH}_2\text{CH}_2 \diagup \end{array} \begin{array}{l} \text{OCH}_3 \\ \text{OCH}_3 \end{array}$	SIB1057.5 BIS(3-CYANOPROPYL)DIMETHOXYSILANE C ₁₀ H ₁₈ N ₂ O ₂ Si highly polar monomer for silicones HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [92779-73-2] HMIS: 3-2-1-X	226.35	180-2°/1	0.985	
$\begin{array}{c} \text{CH}_3\text{O} \\ \\ \text{CH}_3\text{Si}(\text{CH}_2)_3\text{O}(\text{CH}_2\text{CHO})_n(\text{CH}_2)_3\text{Si} \\ \\ \text{CH}_3\text{O} \end{array} \begin{array}{l} \text{CH}_3 \\ \\ \text{OCH}_3 \\ \\ \text{OCH}_3 \end{array}$	SIB1660.0 BIS[(3-METHYLDIMETHOXYSILYL)PROPYL]- POLYPROPYLENE OXIDE viscosity: 6000-10,000 cSt. w/tin catalyst forms moisture-crosslinkable resins hydrophilic dipodal silane HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [75009-88-0] TSCA HMIS: 3-1-1-X	600-800	flashpoint: >110°C (>230°F)	1.00	1.452 ²⁵
$\begin{array}{c} \text{CH}_2 \\ \\ \text{O}(\text{CH}_2\text{CH}_2\text{O})_{6-8}\text{CH}_2\text{CCH}_2(\text{OCH}_2\text{CH}_2)_{6-8}\text{O} \\ \\ (\text{C}_2\text{H}_5\text{O})_2\text{Si} \end{array} \begin{array}{l} (\text{CH}_2)_3 \\ \\ \text{Si}(\text{OCH}_2\text{CH}_3)_3 \end{array}$	SIB1824.9 1,3-[BIS(3-TRIETHOXYSILYLPROPYL)POLY- ETHYLENOXY]-2-METHYLENEPROPANE C ₅₀ H ₁₀₄ O ₂₀ Si ₂ (average) vinyl functional hydrophilic dipodal coupling agent for protein immobilization HMIS: 2-2-1-X	1113.5			1.0g/\$292.00
$\begin{array}{c} \text{CH}_3 \\ \\ \text{N}\equiv\text{C}-\text{CHCH}_2\text{CH}_2 \\ \\ \text{H}_3\text{C}-\text{Si}-\text{Cl} \end{array}$	SIC2436.0 (3-CYANOBTYL)DIMETHYLCHLOROSILANE C ₇ H ₁₄ ClNSi HMIS: 3-2-1-X	175.73	80-4°/1	0.993	100g/\$130.00
$\begin{array}{c} \text{CH}_3 \\ \\ \text{N}\equiv\text{C}-\text{CHCH}_2\text{CH}_2 \\ \\ \text{H}_3\text{C}-\text{Si}-\text{Cl} \end{array}$	SIC2437.0 (3-CYANOBTYL)METHYLDICHLOROSILANE 4-(DICHLOROMETHYLSILYL)-2-METHYLBUTYRONITRILE C ₆ H ₁₁ Cl ₂ NSi [71550-62-4] TSCA HMIS: 3-2-1-X	196.17	63°/0.3	1.104	100g/\$130.00
$\begin{array}{c} \text{CH}_3 \\ \\ \text{N}\equiv\text{C}-\text{CHCH}_2\text{CH}_2 \\ \\ \text{H}_3\text{C}-\text{Si}-\text{OCH}_3 \\ \\ \text{OCH}_3 \end{array}$	SIC2437.5 (3-CYANOBTYL)METHYLDIMETHOXY- SILANE C ₈ H ₁₇ NO ₂ Si [793681-94-4] TSCA HMIS: 3-2-1-X	187.32	77°/1.5 flashpoint: 93°C (199°F)	0.947	1.4213 ²⁵ 25g/\$88.00
$\begin{array}{c} \text{CH}_3 \\ \\ \text{N}\equiv\text{C}-\text{CHCH}_2\text{CH}_2 \\ \\ \text{Cl}-\text{Si}-\text{Cl} \\ \\ \text{Cl} \end{array}$	SIC2438.0 (3-CYANOBTYL)TRICHLOROSILANE C ₅ H ₈ Cl ₃ NSi [163155-56-4] HMIS: 3-2-1-X	216.57	61-3°/0.2	1.220	1.4690 ²⁵ 25g/\$39.00
$\begin{array}{c} \text{CH}_3 \\ \\ \text{N}\equiv\text{C}-\text{CHCH}_2\text{CH}_2 \\ \\ \text{H}_3\text{CO}-\text{Si}-\text{OCH}_3 \\ \\ \text{OCH}_3 \end{array}$	SIC2439.0 3-CYANOBTYLTRIETHOXYSILANE C ₁₁ H ₂₃ NO ₃ Si HMIS: 2-2-1-X	245.39			25g/\$62.00
$\begin{array}{c} \text{N}\equiv\text{C}-\text{CH}_2\text{CH}_2 \\ \\ \text{H}_3\text{C}-\text{Si}-\text{Cl} \\ \\ \text{Cl} \end{array}$	SIC2440.0 2-CYANOETHYLMETHYLDICHLOROSILANE C ₄ H ₇ Cl ₂ NSi monomer for polar silicones used in GC phases HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [1070-18-4] TSCA HMIS: 3-2-1-0	168.10	60-2°/4 flashpoint: 60°C (140°F)	1.2015	1.4550 ²⁵ 25g/\$123.00
$\text{N}\equiv\text{C}-\text{CH}_2\text{CH}_2\text{SiCl}_3$	SIC2442.0 2-CYANOETHYLTRICHLOROSILANE C ₃ H ₄ Cl ₃ NSi ΔHvap: 11.2 kcal/mole vapor pressure, 85°: 12mm HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [10731-22-3] TSCA HMIS: 3-2-1-0-X	188.52	84-6°/10 (32-3°)mp	1.356	1.4615 TOXICITY- oral rat, LD50: 2000mg/kg 10g/\$27.00







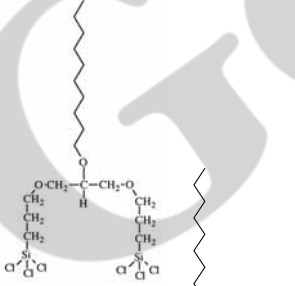

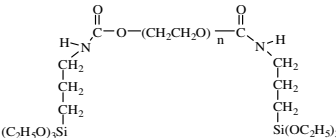

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
$\text{N}\equiv\text{C}-\text{CH}_2\text{CH}_2-\text{Si}(\text{OCH}_2\text{CH}_3)_3$	SIC2445.0 2-CYANOETHYLTRIETHOXYSILANE C ₉ H ₁₉ NO ₃ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [919-31-3] TSCA HMIS: 2-2-0-X	217.34	224-5° flashpoint: 86°C (186°F)	0.9792	1.4140
$\text{N}\equiv\text{C}-\text{CH}_2\text{CH}_2\text{Si}(\text{OCH}_3)_3$	SIC2446.0 2-CYANOETHYLTRIMETHOXYSILANE C ₆ H ₁₃ NO ₃ Si γc of treated surface: 34 dynes/cm crosslinker for moisture-cure silicone RTVs HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [2526-62-7] TSCA HMIS: 3-2-1-X	175.26	112°/15 flashpoint: 79°C (174°F)	1.079	1.4126
$\text{N}\equiv\text{C}-\text{CH}_2\text{CH}_2\text{CH}_2\text{Si}(\text{CH}(\text{CH}_3)_2)_2-\text{N}(\text{CH}_3)_2$	SIC2451.0 3-CYANOPROPYLDIISOPROPYLDIMETHYL-AMINOSILANE 4-(DIMETHYLAMINO)BIS(1-METHYLETHYL)SILYL)BUTANENITRILE C ₁₂ H ₂₆ N ₂ Si stable cyanofunctional bonded phase HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [163794-91-0] TSCA HMIS: 3-2-1-X	226.44	96-8°/0.2 flashpoint: 85°C (185°F)	0.89	
$\text{N}\equiv\text{C}-\text{CH}_2\text{CH}_2\text{CH}_2\text{Si}(\text{CH}_3)_2-\text{Cl}$	SIC2452.0 3-CYANOPROPYLDIMETHYLCHLOROSILANE 4-(CHLORODIMETHYLSILYL)BUTYRONITRILE C ₆ H ₁₂ ClNSi coupling agent for antibodies! 1. S. Falipou et al, Bioconjugate Chem., Am. Chem. Soc., 1989 HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [18156-15-5] TSCA HMIS: 3-2-1-X	161.71	108-9°/15 flashpoint: 85°C (185°F)	0.986	1.4460
$\text{N}\equiv\text{C}-\text{CH}_2\text{CH}_2\text{CH}_2\text{Si}(\text{Cl})_2-\text{CH}_3$	SIC2453.0 3-CYANOPROPYLMETHYLDICHLOROSILANE C ₅ H ₉ Cl ₂ NSi see also SIC2448.0 HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [1190-16-5] TSCA HMIS: 3-2-1-X	182.12	79-82°/1 flashpoint: 92°C (198°F)	1.145 ²⁵	1.4551 ²⁵
$\text{N}\equiv\text{C}-\text{CH}_2\text{CH}_2\text{CH}_2\text{Si}(\text{OCH}_3)_2-\text{CH}_3$	SIC2453.5 3-CYANOPROPYLMETHYLDIMETHOXYSILANE C ₇ H ₁₅ NO ₂ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture HMIS: 3-2-1-X	173.29	82-3°/3 flashpoint: 75°C (167°F)	0.9970	1.4235
$\text{N}\equiv\text{C}-\text{CH}_2\text{CH}_2\text{CH}_2\text{Si}(\text{Cl})_3$	SIC2454.0 3-CYANOPROPYLTRICHLOROSILANE C ₄ H ₆ Cl ₃ NSi see also SIC2449.0 HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [1071-22-3] TSCA HMIS: 3-2-1-X	202.54	93-4°/8 flashpoint: 75°C (167°F)	1.302	1.465
$\text{N}\equiv\text{C}-\text{CH}_2\text{CH}_2\text{CH}_2\text{Si}(\text{OC}_2\text{H}_5)_3$	SIC2455.0 3-CYANOPROPYLTTRIETHOXYSILANE C ₁₀ H ₂₁ NO ₃ Si viscosity: 2.3 cSt HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [1067-47-6] TSCA HMIS: 3-2-1-X	231.37	79-80°/0.6 flashpoint: 74°C (165°F)	0.961	1.4174
$\text{N}\equiv\text{C}-\text{CH}_2\text{CH}_2\text{CH}_2\text{Si}(\text{OCH}_3)_3$	SIC2456.0 3-CYANOPROPYLTRIMETHOXYSILANE C ₇ H ₁₅ NO ₃ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [55453-24-2] TSCA-L HMIS: 3-2-1-X	189.29	90-2°/7 flashpoint: 75°C (167°F)	1.026 ²⁵	1.4167
$\text{NC}(\text{CH}_2)_{11}\text{SiCl}_3$	SIC2456.3 11-CYANOUNDECYLTRICHLOROSILANE C ₁₂ H ₂₂ Cl ₃ NSi long-chain organofunctional silane HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [724460-16-6] HMIS: 3-2-1-X	314.76	162-4°/1 flashpoint: 75°C (167°F)	1.075	










Hydrophilic Silane Properties

Polar - Hydrogen Bonding



	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
$\begin{array}{c} \text{O} \\ \parallel \\ \text{CH}_3\text{CNCH}_2\text{CH}_2\text{CH}_2\text{Si} \\ \qquad \qquad \qquad \\ \text{H} \qquad \qquad \qquad \text{OCH}_3 \\ \qquad \qquad \qquad \\ \qquad \qquad \qquad \text{OCH}_3 \end{array}$	SIA0006.0 ACETAMIDOPROPYLTRIMETHOXYSILANE C ₈ H ₁₉ NO ₄ Si [57757-66-1] HMIS: 3-2-1-X	221.33	162-5°/2-3 10g/\$120.00		1.4410
$\begin{array}{c} \text{O} \\ \parallel \\ \text{CH}_3\text{COCH}_2\text{CH}_2\text{Si} \\ \qquad \qquad \qquad \\ \text{CH}_3 \qquad \qquad \qquad \text{CH}_3 \\ \qquad \qquad \qquad \\ \qquad \qquad \qquad \text{Cl} \end{array}$	SIA0010.0 ACETOXYETHYLDIMETHYLCHLOROSILANE C ₆ H ₁₃ ClO ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18306-45-1] HMIS: 3-2-1-X	180.71	108-9°/50 flashpoint: 63°C (145°F) 25g/\$61.00	1.031 ²⁵	1.4301 ²⁵
$\begin{array}{c} \text{O} \\ \parallel \\ \text{CH}_3\text{COCH}_2\text{CH}_2\text{Si} \\ \qquad \qquad \qquad \\ \text{Cl} \qquad \qquad \qquad \text{Cl} \\ \qquad \qquad \qquad \\ \qquad \qquad \qquad \text{CH}_3 \end{array}$	SIA0015.0 ACETOXYETHYLMETHYLDICHLOROSILANE C ₅ H ₁₀ Cl ₂ O ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18163-34-3] TSCA HMIS: 3-2-1-X	201.12	117°/62 flashpoint: 65°C (149°F) 25g/\$55.00	1.177 ²⁵	1.4390 ²⁵
$\begin{array}{c} \text{O} \\ \parallel \\ \text{CH}_3\text{COCH}_2\text{CH}_2\text{Si} \\ \qquad \qquad \qquad \\ \text{Cl} \qquad \qquad \qquad \text{Cl} \\ \qquad \qquad \qquad \\ \qquad \qquad \qquad \text{Cl} \end{array}$	SIA0020.0 ACETOXYETHYLTRICHLOROSILANE C ₄ H ₇ Cl ₃ O ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [18204-80-3] TSCA HMIS: 3-2-1-X	221.54	143°/70 flashpoint: 82°C (180°F) 25g/\$51.00	1.272 ²⁵	1.4427 ²⁵
$\begin{array}{c} \text{O} \\ \parallel \\ \text{CH}_3\text{COCH}_2\text{CH}_2\text{Si} \\ \qquad \qquad \qquad \\ \text{OC}_2\text{H}_5 \qquad \qquad \text{OC}_2\text{H}_5 \\ \qquad \qquad \qquad \\ \qquad \qquad \qquad \text{OC}_2\text{H}_5 \end{array}$	SIA0025.0 ACETOXYETHYLTRIETHOXYSILANE C ₁₀ H ₂₂ O ₅ Si >280° rearranges to acetoxyltriethoxysilane w/ extrusion of ethylene ¹ . 1. K. Ezbiansky et al, in "Chemical Process. of Dielectrics, Insulators & Electronic Ceramics MRS Proc. 2000." HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [22538-45-0] HMIS: 2-2-1-X	250.35	60°/0.2 25g/\$49.00	0.983	1.410
$\begin{array}{c} \text{O} \\ \parallel \\ \text{CH}_3\text{COCH}_2\text{CH}_2\text{Si} \\ \qquad \qquad \qquad \\ \text{OCH}_3 \qquad \qquad \text{OCH}_3 \\ \qquad \qquad \qquad \\ \qquad \qquad \qquad \text{OCH}_3 \end{array}$	SIA0030.0 ACETOXYETHYLTRIMETHOXYSILANE, 95% C ₇ H ₁₆ O ₅ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [72878-29-6] HMIS: 3-3-1-X	208.29	108-9°/27 25g/\$48.00	1.061	
$\begin{array}{c} \text{O} \qquad \qquad \text{CH}_3 \qquad \text{O} \\ \parallel \qquad \qquad \qquad \parallel \\ \text{CH}_3\text{COCH}_2\text{Si} \text{---} \text{OCCH}_3 \\ \qquad \qquad \qquad \\ \text{CH}_3 \qquad \qquad \qquad \text{CH}_3 \end{array}$	SIA0040.0 ACETOXYMETHYLDIMETHYLACETOXY- SILANE C ₇ H ₁₄ O ₄ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [5833-57-8] HMIS: 3-2-1-X	190.27	66-9°/7 flashpoint: 63°C (145°F) 25g/\$72.00	1.0420	1.4388
$\begin{array}{c} \text{O} \qquad \qquad \text{OC}_2\text{H}_5 \\ \parallel \qquad \qquad \\ \text{CH}_3\text{COCH}_2\text{Si} \text{---} \text{OC}_2\text{H}_5 \\ \qquad \qquad \qquad \\ \text{OC}_2\text{H}_5 \qquad \qquad \text{OC}_2\text{H}_5 \end{array}$	SIA0050.0 ACETOXYMETHYLTRIETHOXYSILANE C ₉ H ₂₀ O ₅ Si hydrolyzes to form stable silanol solutions in neutral water HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [5630-83-1] HMIS: 2-2-1-X	236.34	106°/15 25g/\$58.00	1.042 ²⁵	1.4092
$\begin{array}{c} \text{O} \qquad \qquad \text{OCH}_3 \\ \parallel \qquad \qquad \\ \text{CH}_3\text{COCH}_2\text{Si} \text{---} \text{OCH}_3 \\ \qquad \qquad \qquad \\ \text{OCH}_3 \qquad \qquad \text{OCH}_3 \end{array}$	SIA0055.0 ACETOXYMETHYLTRIMETHOXYSILANE, 95% C ₆ H ₁₄ O ₅ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [65625-39-0] TSCA-L HMIS: 3-3-1-X	194.26	190-1° flashpoint: 56°C (133°F) 10g/\$45.00	1.085	50g/\$180.00
$\begin{array}{c} \text{O} \qquad \qquad \text{OCH}_3 \\ \parallel \qquad \qquad \\ \text{CH}_3\text{CO}(\text{CH}_2\text{CH}_2\text{O})_{6-9}(\text{CH}_2)_3\text{Si} \text{---} \text{OCH}_3 \\ \qquad \qquad \qquad \\ \text{OCH}_3 \end{array}$	SIA0078.0 2-[ACETOXY(POLYETHYLENEOXY)- PROPYL]TRIETHOXYSILANE 95% HMIS: 2-1-1-X	500-700	25g/\$78.00	1.04	

PLEASE INQUIRE ABOUT BULK QUANTITIES

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SIA0090.0 ACETOXYPROPYLMETHYLDICHLORO-SILANE C ₆ H ₁₂ Cl ₂ O ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [5290-24-4] TSCA HMIS: 3-2-1-X	215.15	142°/73 flashpoint: 85°C (185°F)	1.151 ²⁵	1.4434 ²⁵
	SIA0100.0 ACETOXYPROPYLTRIMETHOXYSILANE C ₈ H ₁₈ O ₅ Si γc of treated surface: 37.5 dynes/cm HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [59004-18-1] HMIS: 3-1-1-X	222.31	92°/2 flashpoint: 93°C (200°F)	1.062	1.4146
	SIA0114.0 11-ACETOXYUNDECYLTRICHLOROSILANE C ₁₃ H ₂₅ Cl ₃ O ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents HMIS: 3-1-1-X	347.78	147-9°/1 flashpoint: >110°C (>230°F)	1.084	
	SIA0120.0 (N-ACETYLGLYCYL)-3-AMINOPROPYL-TRIMETHOXYSILANE C ₁₀ H ₂₁ N ₂ O ₆ Si amino acid-tipped silane HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture HMIS: 3-2-1-X	293.37			
	SIA0599.4 N-3-[(AMINO(POLYPROPYLENOXY)]AMINO-PROPYLTRIMETHOXYSILANE 60-65% 3-4 propyleneoxy units contains 30-35% amine terminated polypropylene oxide coupling agent with film-forming capability HMIS: 2-2-1-X	337-435		0.984	1.4508
	SIB0959.0 BENZOYLOXYPROPYLTRIMETHOXYSILANE C ₁₃ H ₂₀ O ₅ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [76241-02-6] TSCA-L HMIS: 3-2-1-X	284.38	145°/0.2	1.104	1.4806
	SIB1815.1 1,3-BIS(3-TRICHLOROSILYLPROPOXY)-2-DECYLOXYPROPANE C ₁₉ H ₃₈ O ₃ Cl ₆ Si ₂ dipodal C ₁₈ analog w/buried hydrophilicity HMIS: 3-1-1-X	583.40	190-200°/0.4	1.158	
	SIB1815.3 3,3-BIS(TRICHLOROSILYLPROPOXYMETHYL)-5-OXA-TRIDECAENE C ₂₀ H ₄₀ O ₃ Cl ₆ Si ₂ dipodal hydrophobic surface treatment with buried hydrophilicity for chromatography HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents HMIS: 3-1-1-X	597.42	220-2°/0.9	1.13	
	SIB1824.82 BIS[N,N'-(TRIETHOXYSILYLPROPYL)AMINO-CARBONYL]POLYETHYLENE OXIDE (10-15 EO) dipodal hydrophilic silane [178884-91-8] TSCA HMIS: 1-1-1-X	1000-1200		1.085	
	SIB1824.84 BIS(TRIETHOXYSILYLPROPYL)POLY-ETHYLENE OXIDE (25-30 EO) HMIS: 2-1-1-X	1400-1600			

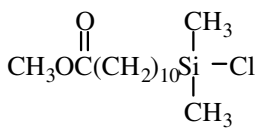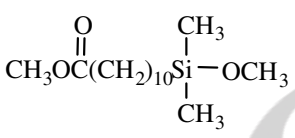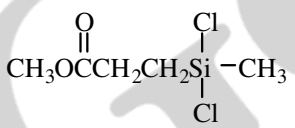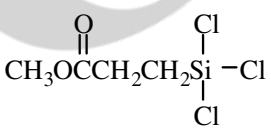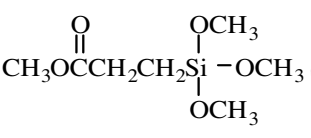	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SIB1827.0 BIS[3-(TRIETHOXY)SILYL]PROPYL]THIO-UREA tech -90 C ₁₉ H ₄₄ N ₂ O ₆ SSi ₂ forms films on electrodes for determination of mercury ¹ . 1. Y. Guo et al, J. Pharm. Biol. Anal., 19, 175, 1999 [69952-89-2] HMIS: 2-1-1-X	484.40			
			25g/\$134.00		
	SIB1828.0 BIS[3-(TRIETHOXY)SILYL]PROPYL]UREA, 60% in ethanol C ₁₉ H ₄₄ N ₂ O ₇ Si ₂ HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [69465-84-5] HMIS: 2-1-1-X	468.73	flashpoint: 24°C (75°F)	0.923	
			25g/\$34.00	100g/\$110.00	
	SIB1835.5 BIS(TRIMETHOXY)SILYL]PROPYL]UREA, 95% C ₁₃ H ₃₂ N ₂ O ₇ Si ₂ <i>amber liquid</i> [18418-53-6] TSCA HMIS: 3-2-1-X	384.58	flashpoint: >110°C (>230°F) viscosity: 100-250 cSt.	1.102	
			25g/\$20.00	100g/\$65.00	
	SIC2065.0 10-(CARBOMETHOXY)DECYLDIMETHYL-CHLOROSILANE C ₁₄ H ₂₉ ClO ₂ Si long-chain organofunctional silane HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [53749-38-5] HMIS: 3-1-1-X	292.92	133°/0.3 flashpoint: 105°C (221°F)	0.950	1.4483 ²⁵
			10g/\$42.00	50g/\$168.00	
	SIC2067.0 10-(CARBOMETHOXY)DECYLDIMETHYL-METHOXY-SILANE C ₁₅ H ₃₂ O ₃ Si long-chain organofunctional silane HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture HMIS: 2-1-1-X	288.50	130°/0.3	0.903	1.4394
			10g/\$51.00	50g/\$204.00	
	SIC2068.0 2-(CARBOMETHOXY)ETHYLMETHYL-DICHLOROSILANE, 95% C ₅ H ₁₀ Cl ₂ O ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [18163-42-3] TSCA HMIS: 3-2-1-X	201.12	98-9°/25 flashpoint: 52°C (126°F)	1.187 ²⁵	1.4439 ²⁵
			25g/\$80.00		
	SIC2070.0 2-(CARBOMETHOXY)ETHYLTRICHLORO-SILANE, 95% contains ~ 20% 1-(carbomethoxy)ethyltrichlorosilane isomer <i>METHYL(3-TRICHLOROSILYL)PROPIONATE</i> C ₄ H ₇ Cl ₃ O ₂ Si HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [18147-81-4] TSCA HMIS: 3-3-1-X	221.54	90-2°/25 flashpoint: > 43°C (>110°F)	1.325	1.448
			25g/\$36.00	100g/\$117.00	
	SIC2072.0 2-(CARBOMETHOXY)ETHYLTRIMETHOXY-SILANE, 95% contains ~ 20% 1-(carbomethoxy)ethyltrimethoxysilane isomer <i>METHYL(3-TRIMETHOXY)SILYL)PROPIONATE</i> C ₇ H ₁₆ O ₅ Si [76301-00-3] HMIS: 3-3-1-X	208.29	flashpoint: > 43°C (>110°F)	1.069	1.410
			10g/\$88.00		
	SID4465.0 N,N-DIOCTYL-N'-TRIETHOXY)SILYL]PROPYL]UREA C ₂₆ H ₅₆ N ₂ O ₄ Si forms hydrophobic phases with embedded hydrophilicity HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [259727-10-1] HMIS: 2-2-1-X	488.83		0.924 ²⁵	1.4521 ²⁵
			25g/\$82.00		

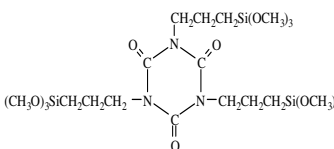PLEASE INQUIRE ABOUT BULK QUANTITIES

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
$\text{CH}_3\text{OCH}_2\text{CH}_2\text{O}(\text{CH}_2)_{11}\text{SiCl}_3$	SIM6491.5 METHOXYETHOXYUNDECYLTRICHLOROSILANE $\text{C}_{14}\text{H}_{29}\text{Cl}_3\text{O}_2\text{Si}$ forms self-assembled monolayers with "hydrophilic tips" HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents HMIS: 3-2-1-X	363.83	145-9°/1.25	1.07	
$\text{CH}_3\text{O}-(\text{CH}_2\text{CH}_2\text{O})_{6-9}-(\text{CH}_2)_3\text{SiCl}_3$	SIM6492.66 2-[METHOXY(POLYETHYLENEOXY)PROPYL]- TRICHLOROSILANE, 90% $\text{CH}_3\text{O}(\text{C}_2\text{H}_4\text{O})_{6-9}\text{C}_3\text{H}_6\text{Cl}_3\text{Si}$ forms hydrophilic surfaces provides protein antifouling surface ¹ . 1. F. Cecchet et al., Langmuir, 22, 1173, 2006 HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture [36493-41-1] HMIS: 3-2-1-X	472-604		1.13	
$\text{CH}_3\text{O}-(\text{CH}_2\text{CH}_2\text{O})_{6-9}(\text{CH}_2)_3\text{Si}(\text{OCH}_3)_3$	SIM6492.7 2-[METHOXY(POLYETHYLENEOXY)PROPYL]- TRIMETHOXY-SILANE, 90% $\text{CH}_3(\text{OC}_2\text{H}_4)_{6-9}(\text{CH}_2)_3\text{OSi}(\text{OCH}_3)_3$ reduces non-specific binding of proteins HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [65994-07-2] TSCA HMIS: 2-2-1-X	460-590	(-8°)mp flashpoint: 88°C (190°F) viscosity: 29 cSt	1.076	1.403
$\text{CH}_3\text{O}-(\text{CH}_2\text{CH}_2\text{O})_{9-12}(\text{CH}_2)_3\text{Si}(\text{OCH}_3)_3$	SIM6492.72 2-[METHOXY(POLYETHYLENEOXY)PROPYL]- TRIMETHOXY-SILANE, 90% $\text{CH}_3(\text{OC}_2\text{H}_4)_{9-12}(\text{CH}_2)_3\text{Si}(\text{OCH}_3)_3$ [65994-07-2] TSCA HMIS: 2-2-1-X	596-725	flashpoint: 88°C(190°F)	1.09	
$\text{CH}_3\text{OCH}_2\text{CH}_2\text{CH}_2\text{Si}(\text{OCH}_3)_3$	SIM6493.0 3-METHOXYPROPYLTRIMETHOXY-SILANE $\text{C}_7\text{H}_{18}\text{O}_4\text{Si}$ HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [33580-59-5] HMIS: 3-2-1-X	194.30	98-9°/40 flashpoint: 53°C (127°F)	0.995	
$\text{CH}_3\text{O}-(\text{CH}_2\text{CH}_2\text{O})_3-(\text{CH}_2)_3\text{SiCl}_3$	SIM6493.2 METHOXYTRIETHYLENOXYPROPYLTRI- CHLOROSILANE $\text{C}_{10}\text{H}_{21}\text{Cl}_3\text{O}_4\text{Si}$ [228700-87-6] HMIS: 3-2-1-X	339.71	140°/0.2	1.163	
$\text{CH}_3\text{O}-(\text{CH}_2\text{CH}_2\text{O})_3-(\text{CH}_2)_3\text{Si}(\text{OCH}_3)_3$	SIM6493.4 METHOXYTRIETHYLENOXYPROPYLTRI- METHOXY-SILANE $\text{C}_{13}\text{H}_{30}\text{O}_7\text{Si}$ forms polymeric proton-conducting electrolytes ¹ . 1. J. Ritchie et al, Chem. Mater., 18, 504, 2006 [132388-45-5] HMIS: 3-2-1-X	326.46	148°/0.3	1.034	
	SIT8186.0 (2-TRIETHOXY-SILYLPROPOXY)ETHOXY- SULFOLANE, 95% $\text{C}_{15}\text{H}_{32}\text{O}_7\text{SSi}$ forms hydrophilic surfaces HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [502925-40-8] HMIS: 2-2-1-X	384.56	190-4°/0.4	1.122	
	SIT8717.0 TRIS(3-TRIMETHOXY-SILYLPROPYL)ISO CYANURATE, 95% $\text{C}_{21}\text{H}_{45}\text{N}_3\text{O}_{12}\text{Si}_3$ HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [26115-70-8] TSCA HMIS: 2-1-1-X	615.86	flashpoint: 102°C (216°F) viscosity: 325-350 cSt.	1.170	1.4610

Hydrophilic Silane Properties

Hydroxylic


	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰	
$\begin{array}{c} \text{HOCH}_2\text{CH}_2 \diagdown \\ \text{NCH}_2\text{CH}_2\text{CH}_2\text{Si}(\text{OEt})_3 \\ \text{HOCH}_2\text{CH}_2 \diagup \end{array}$	SIB1140.0 BIS(2-HYDROXYETHYL)-3-AMINOPROPYL- TRIETHOXYSILANE, 62% in ethanol C ₁₃ H ₃₁ NO ₅ Si contains 2-3% hydroxyethylaminopropyltriethoxysilane urethane polymer coupling agent employed in surface modification for preparation of oligonucleotide arrays ¹ . 1. G. McGall et al, Proc. Nat'l Acad. Sci., 93, 1355, 1996. HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [7538-44-5] TSCA HMIS: 3-4-0-X	309.48	flashpoint: 24°C (75°F) specific wetting surface: 252m ² /g	0.92	1.409 ²⁵	
$\begin{array}{c} (\text{CH}_3\text{O})_3\text{SiCH}_2\text{CH}_2\text{CH}_2 \\ \\ \text{NCH}_2\text{CH}_2\text{OH} \\ \\ \text{CH}_2 \\ \\ \text{CH}_2 \\ \\ \text{NCH}_2\text{CH}_2\text{OH} \\ \\ (\text{CH}_3\text{O})_3\text{SiCH}_2\text{CH}_2\text{CH}_2 \end{array}$	SIB1142.0 N,N'-BIS(HYDROXYETHYL)-N,N'-BIS- (TRIMETHOXYSILYLPROPYL)ETHYLENEDIAMINE C ₁₈ H ₄₄ N ₂ O ₈ Si ₂ [214362-07-9] HMIS: 3-4-1-X	472.73	66-68% in methanol flashpoint: 11°C(52°F) 25g/\$66.00	0.985		
$\begin{array}{c} \text{OH} \quad \quad \quad \text{OH} \\ \quad \quad \quad \\ \text{OCH}_2\text{CHCH}_2-\text{O}-(\text{CH}_2\text{CH}_2\text{O})_{5-10}-\text{CH}_2\text{CHCH}_2-\text{O} \\ \quad \quad \quad \\ \text{CH}_2 \quad \quad \quad \text{CH}_2 \\ \quad \quad \quad \\ (\text{C}_2\text{H}_5\text{O})_3\text{Si} \quad \quad \quad \text{Si}(\text{OC}_2\text{H}_5)_3 \end{array}$	SIB1824.2 BIS-[3-(TRIETHOXYSILYLPROPOXY)- 2-HYDROXYPROPOXY]POLYETHYLENE OXIDE 65% in methanol HMIS: 2-4-1-X	700-800	25g/\$74.00			
$\begin{array}{c} \text{CH}_2\text{OCH}_2\text{CH}_2\text{CH}_2\text{Si}(\text{OC}_2\text{H}_5)_3 \\ \\ \text{HOCH}_2\text{C}(\text{CH}_3)_2\text{CH}_3 \\ \\ \text{CH}_2\text{OCH}_2\text{CH}_2\text{CH}_2\text{Si}(\text{OC}_2\text{H}_5)_3 \end{array}$	SIB1824.4 2,2-BIS(3-TRIETHOXYSILYLPROPOXY- METHYL)BUTANOL, 50% in ethanol C ₂₄ H ₅₄ O ₉ Si ₂ for solid state synthesis of oligonucleotides for solid state synthesis of oligonucleotides HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture HMIS: 2-4-1-X	542.86	10g/\$136.00	0.899		
$\text{HO}-(\text{CH}_2\text{CH}_2\text{O})_{6-9}-(\text{CH}_2)_3\text{Si}(\text{OCH}_2\text{CH}_3)_3$	SIH6188.0 [HYDROXY(POLYETHYLENEOXY)PROPYL]- TRIETHOXYSILANE, (8-12 EO) 50% in ethanol HMIS: 2-4-1-X	500-550	25g/\$78.00	0.889	1.401	
$\begin{array}{c} \text{HOCH}_2\text{CH}_2 \diagdown \\ \text{NCH}_2\text{CH}_2\text{CH}_2\text{Si}(\text{OCH}_3)_3 \\ \text{H}_3\text{C} \diagup \end{array}$	SIH6172.0 N-(HYDROXYETHYL)-N-METHYLAMINO- PROPYLTRIMETHOXYSILANE, 75% in methanol C ₉ H ₂₃ NO ₄ Si HMIS: 3-4-1-X	237.37	100g/\$179.00	0.99	1.417	
$\begin{array}{c} \text{OC}_2\text{H}_5 \\ \\ \text{HO}-\text{CH}_2-\text{Si}-\text{OC}_2\text{H}_5 \\ \\ \text{OC}_2\text{H}_5 \\ + \\ \text{OC}_2\text{H}_5 \quad \quad \quad \text{OC}_2\text{H}_5 \\ \quad \quad \quad \\ \text{HO}-\text{CH}_2-\text{Si}-\text{O}-\text{CH}_2-\text{Si}-\text{OC}_2\text{H}_5 \\ \quad \quad \quad \\ \text{OC}_2\text{H}_5 \quad \quad \quad \text{OC}_2\text{H}_5 \end{array}$	SIH6175.0 HYDROXYMETHYLTRIETHOXYSILANE, 50% in ethanol TRIETHOXYSILYLMETHANOL C ₇ H ₁₈ O ₄ Si contains equilibrium condensation oligomers hydrolysis yields analogs of silica- hydroxymethylsilanetriol polymers ¹ . 1. B. Arkles, US Pat. 5,371,262, 1994. [162781-73-9] HMIS: 2-4-0-X	194.31	25g/\$96.00	0.866		
$\begin{array}{c} \text{O} \\ \\ \text{C}-\text{NH}(\text{CH}_2)_3\text{Si}(\text{OC}_2\text{H}_5)_3 \\ \\ \text{H} \\ \\ \text{HO}-\text{H} \\ \\ \text{H}-\text{OH} \\ \\ \text{H}-\text{OH} \\ \\ \text{H}-\text{OH} \\ \\ \text{CH}_2\text{OH} \end{array}$	SIT8189.0 N-(3-TRIETHOXYSILYLPROPYL)GLUCONAMIDE 50% in ethanol C ₁₅ H ₃₃ NO ₉ Si water soluble, hydrophilic silane [104275-58-3] HMIS: 2-4-1-X	399.51	25g/\$28.00	0.951		
$\text{HOCH}_2\text{CH}_2\text{CH}_2\text{C}(=\text{O})\text{NCH}_2\text{CH}_2\text{CH}_2\text{Si}(\text{OC}_2\text{H}_5)_3$	SIT8189.5 N-(3-TRIETHOXYSILYLPROPYL)-4-HYDROXY- BUTYRAMIDE C ₁₃ H ₂₉ NO ₅ Si anchoring reagent for light-directed synthesis of DNA on glass ¹ . 1. G. McGall et al, J. Am. Chem. Soc., 119, 5081, 1997. [186543-03-3] HMIS: 2-2-1-X	307.47	10g/\$31.00	1.02	1.4533	
$\begin{array}{c} (\text{C}_2\text{H}_5\text{O})_3\text{Si} \diagdown \\ \text{CH}_2 \\ \\ \text{H}(\text{OCH}_2\text{CH}_2)_{4,6}\text{OCNHC}(\text{O})\text{CH}_2\text{CH}_2 \end{array}$	SIT8192.0 N-(TRIETHOXYSILYLPROPYL)-O-POLY- ETHYLENE OXIDE URETHANE, 95% C ₁₀ H ₂₂ NO ₄ SiO(CH ₂ CH ₂ O) ₄₋₆ H contains some bis(urethane) analog hydrophilic surface modifier stabilizes Si ₃ N ₄ aqueous colloids ¹ . 1. J. Yanez et al, J. Eur. Ceram. Soc., 18, 1993, 1998 HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [74695-91-3] HMIS: 2-1-1-X	400-500	25g/\$16.00	100g/\$52.00	1.09	1.4540 ²⁵

COMMERCIAL


Hydrophilic Silane Properties

Ionic-Charge Inducible


HYDROXYLIC / HYDROPHILIC / IONIC HYDROPHILIC




name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
SIB0957.0 (2-N-BENZYLAMINOETHYL)-3-AMINOPROPYL-TRIMETHOXYSILANE, hydrochloride 50% in methanol C ₁₅ H ₂₈ N ₂ O ₃ Si.HCl [623938-90-9] TSCA HMIS: 3-3-1-X	348.25	amber liquid flashpoint: 9°C (48°F) 25g/\$16.00	0.942	1.4104



SIB1835.0 BIS(3-TRIMETHOXYSILYL)PROPYL-N-METHYLAMINE C ₁₃ H ₃₃ NO ₆ Si ₂ HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [31024-70-1] HMIS: 2-1-0-X	355.58	175°/10 flashpoint: 106°C (223°F) 25g/\$68.00	1.023	1.4300
---	--------	---	-------	--------



SIC2263.0 CARBOXYETHYLSILANETRIOL, SODIUM SALT, 25% in water C ₃ H ₆ O ₅ Na ₂ Si HYDROLYTIC SENSITIVITY: 0 forms stable aqueous solutions [18191-40-7] HMIS: 2-0-0-X	196.14	pH:12-12.5 25g/\$45.00	1.17 ²⁵	
--	--------	---------------------------	--------------------	--




SIC2415.0 2-(4-CHLOROSULFONYLPHENYL)ETHYLTRICHLOROSILANE, 50% in methylene chloride C ₈ H ₈ Cl ₄ O ₂ SSi contains 30% free sulfonic acid analog and small amounts of silylsulfonic acid condensation products employed in preparation of solid phase extraction columns HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [79793-00-3] TSCA HMIS: 4-2-2-X	338.11		1.37	
--	--------	--	------	--


Solid Phase Extraction (SPE) columns with benzenesulfonic acid functionalized silica are utilized to analyze urine samples for amino acids and drugs of abuse.




SIC2415.4 2-(4-CHLOROSULFONYLPHENYL)ETHYLTRICHLOROSILANE, 50% in toluene C ₈ H ₈ Cl ₄ O ₂ SSi contains 30% free sulfonic acid analog and small amounts of silylsulfonic acid condensation products HYDROLYTIC SENSITIVITY: 8 reacts rapidly with water/moisture, protic solvents [79793-00-3] TSCA HMIS: 4-4-2-X	338.11		1.08	
---	--------	--	------	--










SIC2417.0 2-(4-CHLOROSULFONYLPHENYL)ETHYLTRIMETHOXYSILANE, 50% in methylene chloride C ₁₁ H ₁₇ ClO ₅ SSi contains free sulfonic acid; amber color treated silica acts as etherification catalyst ¹ . treatment of surface oxidized PMDSO supports electroosmotic flow ² . 1. B. Sow et al, Microporous & Mesoporous Materials, 79, 129, 2005 2. B. Wang et al, Micro Total Analysis Systems 2004 Vol 2., Roy Soc. Chem., 297, p109 [126519-89-9] HMIS: 3-2-1-X	324.85		1.30 ²⁵	
---	--------	--	--------------------	--












SID3392.0 N,N-DIDECYL-N-METHYL-N-(3-TRIMETHOXYSILYL)PROPYL)AMMONIUM CHLORIDE, 42% in methanol C ₂₇ H ₆₀ ClNO ₃ Si contains 3-5% Cl(CH ₂) ₃ Si(OMe) ₃ HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [68959-20-6] TSCA HMIS: 3-4-0-X	510.32	flashpoint: 13°C (55°F) 25g/\$49.00	0.863	1.4085
--	--------	--	-------	--------




SID3395.4 DIETHYLAMINOMETHYLTRIETHOXYSILANE C ₁₁ H ₂₇ NO ₃ Si catalyst for neutral cure 1-part RTVs HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [15180-47-9] HMIS: 2-2-1-X	249.43	74-6°/3 25g/\$49.00	0.9336 ²⁵	1.4142 ²⁵
--	--------	------------------------	----------------------	----------------------

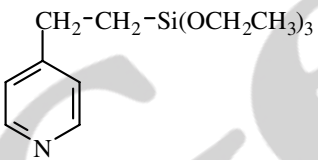	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SID3396.0 (N,N-DIETHYL-3-AMINOPROPYL)TRI-METHOXYSILANE C ₁₀ H ₂₅ NO ₃ Si HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [41051-80-3] TSCA HMIS: 2-2-1-X	235.40	120°/20 flashpoint: 100°C (212°F)	0.934	1.423
	COMMERCIAL SIO6620.0 OCTADECYLDIMETHYL(3-TRIMETHOXYSILYL-PROPYL)AMMONIUM CHLORIDE, 60% in methanol C ₂₆ H ₅₈ ClNO ₃ Si contains 3-5% Cl(CH ₂) ₃ Si(OMe) ₃ employed as lubricant/anti-static surface treatment orients liquid crystals dispersion/coupling agent for high density magnetic recording media ¹ . application as immobilizeable antimicrobial reported ² . 1. H. Vincent in "Chemically Modified Oxide Surfaces," ed. D. Leyden, Gordon & Breach, 1990, p. 305. 2. W. White et al in "Silanes, Surfaces & Interfaces" ed. D. Leyden, Gordon & Breach, 1986, p. 107. HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [27668-52-6] TSCA HMIS: 3-4-0-X	496.29	flashpoint: 15°C (59°F)	0.89	
	SIP6926.2 2-(2-PYRIDYLETHYL)THIOPROPYLTRI-METHOXYSILANE C ₁₃ H ₂₃ NO ₃ SSi chelates metal ions [29098-72-4] HMIS: 3-2-1-X	301.48	156-7°/0.25	1.089	1.498
	SIP6926.4 2-(4-PYRIDYLETHYL)THIOPROPYLTRI-METHOXYSILANE C ₁₃ H ₂₃ NO ₃ SSi immobilizeable ligand for immunoglobulin IgG separation using hydrophobic charge induction chromatography (HCIC) [198567-47-4] HMIS: 3-2-1-X	301.48	160-2°/0.2 pKa: 4.8	1.09	1.5037
	SIP6928.0 2-(4-PYRIDYLETHYL)TRIETHOXYSILANE C ₁₃ H ₂₃ NO ₃ Si see also SIT8396.0 HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture [98299-74-2] HMIS: 3-2-1-X	269.43	105°/0.9 amber liquid	1.00	1.4624 ²⁴
	SIT8157.0 2-[2-(TRICHLOROSILYL)ETHYL]PYRIDINE C ₇ H ₈ Cl ₃ NSi HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [17082-69-8] TSCA HMIS: 3-2-1-X	240.59	280°-decomposes (207°)mp fuming solid, moisture sensitive		
	SIT8158.0 4-[2-(TRICHLOROSILYL)ETHYL]-PYRIDINE, 15-20% in toluene C ₇ H ₈ Cl ₃ NSi see also SIT8396.0 2-(TRIMETHOXYSILYLETHYL)PYRIDINE employed in polypyridine self-assembled monolayers ¹ . 1. S. Paulson et al, J. Chem. Soc. Chem. Comm., 27, 1615, 1992. HYDROLYTIC SENSITIVITY: 8 reacts rapidly with moisture, water, protic solvents [17082-70-1] TSCA HMIS: 3-4-1-X	240.59	280°-decomposes (207°)mp hazy liquid; extremely moisture sensitive	0.93	

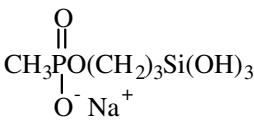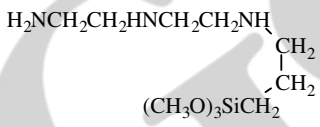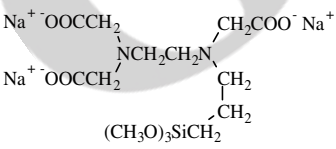
	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
	SIT8187.5 N-(3-TRIETHOXYSILYLPROPYL)- 4,5-DIHYDROIMIDAZOLE <i>3-(2-IMIDAZOLIN-1-YL)PROPYLTRIETHOXYSILANE</i> C ₁₂ H ₂₆ N ₂ O ₃ Si utilized in HPLC of metal chelates ¹ . forms proton vacancy conducting polymers w/sulfonamides by sol-gel ² . ligand for molecularly imprinting silica w/ chymotrypsin transition state analog ³ . 1. T. Suzuki et al, Chem. Lett, 881, 1994. 2. V. De Zea Bermudez et al, Sol-Gel Optics II, SPIE Proc. 1728, 180, 1992. 3. M. Markowitz et al, Langmuir, 1989. HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture	274.43	134°/2 flashpoint: >110°C (>230°F)	1.005	1.452
	[58068-97-6] TSCA HMIS: 2-1-1-X	25g/\$18.00	100g/\$62.00	2.0kg/\$680.00	
	SIT8378.3 3-(TRIHYDROXYSILYL)-1-PROPANE- SULFONIC ACID 30-35% in water C ₃ H ₁₀ O ₆ SSi HYDROLYTIC SENSITIVITY: 0 forms stable aqueous solutions	202.26	(-62°) pH: <1	1.12	
	[70942-24-4] TSCA HMIS: 3-0-0-X	25g/\$51.00	100g/\$ 166.00		
	SIT8378.5 3-TRIHYDROXYSILYLPROPYLMETHYL- PHOSPHONATE, SODIUM SALT, 42% in water C ₄ H ₁₂ NaO ₆ PSi contains 4-5% methanol, sodium methylphosphonate HYDROLYTIC SENSITIVITY: 0 forms stable aqueous solutions	238.18	flashpoint: 79°C (174°F)	1.25	
	[84962-98-1] TSCA HMIS: 1-2-0-X	100g/\$16.00	500g/\$64.00		
	SIT8395.0 N-(TRIMETHOXYSILYLETHYL)BENZYL-N,N,N- TRIMETHYLAMMONIUM CHLORIDE, 60% in methanol C ₁₅ H ₂₈ ClNO ₃ Si candidate for exchange resins and extraction phases HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture	333.93	flashpoint: 25°C (77°F)	0.966	
	HMIS: 3-3-1-X	25g/\$80.00			
	SIT8396.0 2-(TRIMETHOXYSILYLETHYL)PYRIDINE C ₁₀ H ₁₇ NO ₃ Si see also SIP6928.0 HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture	227.33	105°/0.3 flashpoint: >110°C (>230°F)	1.06	1.4755
	[27326-65-4] HMIS: 3-2-1-X	10g/\$41.00	50g/\$164.00		
	SIT8398.0 (3-TRIMETHOXYSILYLPROPYL)DIETHYLENE- TRIAMINE tech-95 C ₁₀ H ₂₇ N ₃ O ₃ Si HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture	265.43	114-8°/2 flashpoint: 137°C (279°F) Yc of treated surface: 37.5 dynes/cm	1.030	1.4590
	[35141-30-1] TSCA HMIS: 3-1-1-X	100g/\$20.00	2.0kg/\$248.00		
	SIT8402.0 N-(TRIMETHOXYSILYLPROPYL)ETHYLENE- DIAMINE TRIACETIC ACID, TRISODIUM SALT, 45% in water C ₁₄ H ₂₅ N ₂ Na ₃ O ₉ Si essentially silanetriol, contains NaCl chelates metal ions HYDROLYTIC SENSITIVITY: 0 forms stable aqueous solutions	462.42		1.26	
	[128850-89-5] TSCA HMIS: 2-0-0-X	25g/\$42.00	100g/\$137.00		
	SIT8405.0 N-(TRIMETHOXYSILYLPROPYL)ISOTHIO- URONIUM CHLORIDE, 50% in water C ₇ H ₁₉ ClN ₂ O ₃ SSi antimicrobial activity reported HYDROLYTIC SENSITIVITY: 0 forms stable aqueous solutions	274.84	essentially silanetriol TRIHYDROXYPROPYLCARBAMIDOTHIOIC ACID HYDROCHLORIDE pH: 6	1.190	1.441
	[84682-36-0] TSCA HMIS: 2-0-0-X	25g/\$45.00			
	SIT8412.0 N-TRIMETHOXYSILYLPROPYL-N,N,N-TRI- n-BUTYLAMMONIUM BROMIDE, 50% in methanol C ₁₈ H ₄₂ BrNO ₃ Si immobilizable phase transfer catalyst HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture	428.52	flashpoint: 11°C (52°F)	0.92	
	HMIS: 3-4-1-X	25g/\$89.00			

COMMERCIAL

COMMERCIAL



name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
SIT8414.0 N-TRIMETHOXYSILYLPROPYL-N,N,N-TRI- n-BUTYLAMMONIUM CHLORIDE, 50% in methanol C ₁₈ H ₄₂ ClNO ₃ Si flashpoint: 11°C (52°F) contains 3-5% chloropropyltrimethoxysilane and Bu ₃ NH ⁺ Cl ⁻ HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture HMIS: 3-4-1-X	384.08		0.88	
		25g/\$81.00		




COMMERCIAL

SIT8415.0 N-TRIMETHOXYSILYLPROPYL-N,N,N-TRI- METHYLAMMONIUM CHLORIDE, 50% in methanol N,N,N-TRIMETHYL-3-(TRIMETHOXYSILYL)-1-PROPANAMINIUM CHLORIDE C ₉ H ₂₄ ClNO ₃ Si flashpoint: 16°C (61°F) employed for bonded chromatographic phases anti-static agent used to treat glass substrates employed in electroblotting see also SIT8395.0 HYDROLYTIC SENSITIVITY: 7 reacts slowly with water/moisture [35141-36-7] TSCA HMIS: 2-4-1-X	257.83		0.927	1.3966
		25g/\$18.00		2.0kg/\$390.00


Polymeric Hydrophilic Silanes

Polymeric Amine



COMMERCIAL

name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
SSP-060 TRIMETHOXYSILYLPROPYL MODIFIED (POLYETHYLENIMINE) 50% in isopropanol visc: 125-175 cSt ~20% of nitrogens substituted employed as a coupling agent for polyamides ¹ . in combination with glutaraldehyde immobilizes enzymes ² . 1. B. Arkles et al, SPI 42nd Composite Inst. Proc., 21-C, 1987 2. S. Cramer et al, Biotech. & Bioeng., 33(3), 344, 1989.	1500-1800		0.92	
[136856-91-2] TSCA HMIS: 2-4-1-X		100g/\$28.00		2.0kg/\$364.00



SSP-065 DIMETHOXYMETHYLSILYLPROPYL MODIFIED (POLYETHYLENIMINE) 50% in isopropanol visc: 100-200 cSt ~20% of nitrogens substituted primer for brass	1500-1800		0.92	
[1255441-88-5] TSCA HMIS: 2-4-1-X		100g/\$38.00		2.0kg/\$494.00

Water-borne Aminoalkyl Silsesquioxane Oligomers

TSCA







Code	Functional Group	Mole %	Molecular Weight	Weight % in solution	Specific Gravity			pH	Price/100g	3kg
					Viscosity	Gravity	Gravity			
WSA-7011	Aminopropyl	65-75	250-500	25-28	1.10	5-15	10-10.5	\$29.00	\$435.00	
WSA-9911*	Aminopropyl	100	270-550	22-25	1.06	5-15	10-10.5	\$24.00	\$360.00	
WSA-7021	Aminoethylaminopropyl	65-75	370-650	25-28	1.10	5-10	10-11	\$29.00	\$435.00	
WSAV-6511**	Aminopropyl, vinyl	60-65	250-500	25-28	1.11	3-10	10-11	\$35.00	\$480.00	

*CAS [29159-37-3] **[207308-27-8]



Aqueous exposure of treated surfaces
converts Epoxy-Silanes to Hydrophilic-Diols

Epoxy Functional Silanes


Epoxy Functional Silanes - Trialkoxy

	SIE4668.0 2-(3,4-EPOXYCYCLOHEXYL)ETHYL- TRIETHOXYSILANE $C_{14}H_{28}O_4Si$ [10217-34-2] TSCA HMIS: 2-1-1-X	288.46	114-7°/0.4	1.015	1.4455	COMMERCIAL
	flashpoint: 104°C (220°F) 25g/\$14.00 100g/\$46.00 2.0kg/\$320.00					
	SIE4670.0 2-(3,4-EPOXYCYCLOHEXYL)ETHYL- TRIMETHOXYSILANE $C_{11}H_{22}O_4Si$ viscosity: 5.2 cSt coefficient of thermal expansion: 0.8×10^{-3} vapor pressure, 152°: 10mm ring epoxide more reactive than glycidoxypropyl systems. UV initiated polymerization of epoxy group with weak acid donors. forms UV-curable coating resins by controlled hydrolysis ¹ . 1. J. Crivello et al, Chem. Mater. 9, 1554, 1997.	246.38	95-7°/0.25	1.065	1.449	COMMERCIAL
	[3388-04-3] TSCA HMIS: 3-1-1-X 100g/\$24.00 2.0kg/\$270.00 18kg/\$1044.00					
	SIG5840.0 (3-GLYCIDOXYPROPYL)TRIMETHOXYSILANE 3-(2,3-EPOXYPROPOXY)PROPYLTRIMETHOXYSILANE $C_9H_{20}O_5Si$ coupling agent for epoxy composites employed in electronic "chip" encapsulation.	236.34	120°/2 (<-70°)mp	1.070	1.4290	COMMERCIAL
	[2530-83-8] TSCA HMIS: 3-1-1-X 100g/\$16.00 2.0kg/\$138.00 18kg/\$693.00					
	SIG5839.0 (3-GLYCIDOXYPROPYL)TRIETHOXYSILANE $C_{12}H_{26}O_5Si$ [2602-34-8] TSCA HMIS: 3-2-1-X	278.4	124°/3	1.00	1.425	DEVELOPMENTAL
	flashpoint: 144°C (291°F) 25g/\$38.00 100g/\$124.00 2.0kg/\$580.00					
	SIG5840.1 (3-GLYCIDOXYPROPYL)TRIMETHOXYSILANE 99+% 3-(2,3-EPOXYPROPOXY)PROPYLTRIMETHOXYSILANE $C_9H_{20}O_5Si$ [2530-83-8] TSCA HMIS: 3-1-1-X	236.34	120°/2 (<-70°)mp	1.070	1.4290	DEVELOPMENTAL
	TOXICITY- oral rat, LD50: 8,400 mg/kg 25g/\$180.00 in fluoropolymer bottle					
	SIE4675.0 5,6-EPOXYHEXYLTRIETHOXYSILANE $C_{12}H_{26}O_4Si$ [86138-01-4] HMIS: 3-2-1-X	262.42	115-9°/1.5	0.960 ²⁵	1.4254 ²⁵	DEVELOPMENTAL
	flashpoint: 99°C (210°F) 10g/\$89.00					

Epoxy Functional Silanes - Dialkoxy

	SIG5832.0 (3-GLYCIDOXYPROPYL)METHYLDIETHOXY- SILANE $C_{11}H_{24}O_4Si$ employed in scratch-resistant coatings for eyeglasses.	248.39	122-6°/5	0.978 ²⁵	1.431	COMMERCIAL
	[2897-60-1] TSCA HMIS: 2-1-1-X 25g/\$38.00 100g/\$124.00 2.0kg/\$580.00					
	SIG5836.0 (3-GLYCIDOXYPROPYL)METHYLDIMETHOXY- SILANE $C_9H_{20}O_4Si$ relative hydrolysis rate vs. SIG5840.0: 7.5:1	220.34	100°/4	1.02	1.431 ²⁵	DEVELOPMENTAL
	[65799-47-5] TSCA-L HMIS: 3-1-1-X 25g/\$50.00 100g/\$162.00					

Epoxy Functional Silanes - Monoalkoxy


	SIG5825.0 (3-GLYCIDOXYPROPYL)DIMETHYLETHOXY- SILANE $C_{10}H_{22}O_3Si$ [17963-04-1] TSCA HMIS: 3-2-1-X	218.37	100°/3	0.950	1.4337 ²⁵	DEVELOPMENTAL
	flashpoint: 87°C (189°F) 10g/\$40.00 50g/\$160.00					

Silyl Hydrides

Silyl Hydrides are a distinct class of silanes that behave and react very differently than conventional silane coupling agents. Their application is limited to deposition on metals (see discussion on p. 17). They liberate hydrogen on reaction and should be handled with appropriate caution.

	name	MW	bp/mm (mp)	D ₄ ²⁰	n _D ²⁰
$\begin{array}{c} \text{H} \\ \\ \text{CH}_3(\text{CH}_2)_{10}\text{CH}_2\text{Si} - \text{H} \\ \\ \text{H} \end{array}$	SID4629.6 DODECYLSILANE C ₁₂ H ₂₈ Si forms SAMS on gold surfaces	200.44	80°/7	0.7753	1.4380 ²⁵
	872-19-5 HMIS: 2-2-1-X		10g/\$78.00		
$\begin{array}{c} \text{H} \\ \\ \text{CH}_3(\text{CH}_2)_{16}\text{CH}_2 - \text{Si} - \text{H} \\ \\ \text{H} \end{array}$	SIO6635.0 n-OCTADECYLSILANE C ₁₈ H ₄₀ Si contains 4-6% C ₁₈ isomers forms self-assembled monolayers on titanium ¹ . 1. A. Fadeau et al, J. Am. Chem. Soc., 121, 12184, 1999	284.60	195°/15 (29°)mp flashpoint: >110°C (>230°F)	0.794	
	[18623-11-5] TSCA HMIS: 2-1-1-X	25g/\$46.00	100g/\$150.00		
$\begin{array}{c} \text{H} \\ \\ \text{CF}_3\text{CF}_2\text{CF}_2\text{CF}_2\text{CF}_2\text{CF}_2\text{CF}_2\text{CH}_2\text{CH}_2\text{Si} - \text{H} \\ \\ \text{H} \end{array}$	SIT8173.0 (TRIDecaFLUORO-1,1,2,2-TETRA- HYDROOCTYL)SILANE C ₈ H ₇ F ₁₃ Si provides vapor-phase hydrophobic surfaces on titanium, gold, silicon	378.22	75°/251.446	1.3184	
	[469904-32-3] HMIS: 3-3-1-X		10g/\$190.00		
$\begin{array}{c} \text{H} \\ \\ \text{H}_2\text{C}=\text{CH}(\text{CH}_2)_8\text{CH}_2\text{Si} - \text{H} \\ \\ \text{H} \end{array}$	SIU9048.0 10-UNDECENYLSILANE C ₁₁ H ₂₄ Si HMIS: 2-3-1-X	184.40		0.78	
			2.5g/\$180.00		

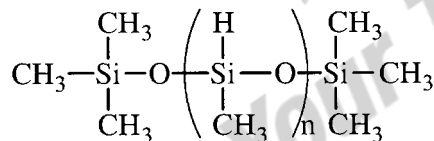MethylHydrosiloxane homopolymers are used as water-proofing agents, reducing agents and as components in some foamed silicone systems.



polyMethylHydrosiloxanes, Trimethylsiloxy terminated

Tg: -119° V.T.C: 0.50

CAS: [63148-57-2] TSCA

COMMERCIAL

Code	Viscosity	Molecular Weight	Mole % (MeHSiO)	Equivalent Weight	Specific Gravity	Refractive Index	Price/100g	Price/3 kg
HMS-991	15-25	1400-1800	100	67	0.98	1.395	\$14.00	\$96.00
HMS-992	25-35	1800-2100	100	65	0.99	1.396	\$19.00	\$134.00
HMS-993	35-45	2100-2400	100	64	0.99	1.396	\$24.00	\$168.00

Surface Modification with Silanes: What’s not covered in “Hydrophobicity, Hydrophilicity and Silane Surface Modification”?

Silanes which are expected to form covalent bonds after deposition onto surfaces are discussed in the Gelest brochure entitled “**Silane Coupling Agents: Connecting Across Boundaries**” Aminosilanes which are important in some hydrophilic surface treatments are covered in detail.

Further Reading

Silane Coupling Agents - General References and Proceedings

1. B. Arkles, Tailoring Surfaces with Silanes, CHEMTECH, 7, 766-778, 1977.
2. E. Plueddemann, “Silane Coupling Agents,” Plenum, 1982.
3. K. Mittal, “Silanes and Other Coupling Agents,” VSP, 1992.
4. D. Leyden and W. Collins, “Silylated Surfaces,” Gordon & Breach, 1980.
5. D. E. Leyden, “Silanes, Surfaces and Interfaces,” Gordon & Breach 1985.
6. J. Steinmetz and H. Mottola, “Chemically Modified Surfaces,” Elsevier, 1992.
7. J. Blitz and C. Little, “Fundamental & Applied Aspects of Chemically Modified Surfaces,” Royal Society of Chemistry, 1999.

Substrate Chemistry - General References and Proceedings

8. R. Iler, “The Chemistry of Silica,” Wiley, 1979.
9. S. Pantelides, G. Lucovsky, “SiO₂ and Its Interfaces,” MRS Proc. 105, 1988.

Hydrophobicity & Hydrophilicity

10. C. Tanford, “The Hydrophobic Effect” Wiley, 1973.
11. H. Butt, K. Graf, M. Kappl, “Physics and Chemistry of Interfaces,” Wiley, 2003.
12. A. Adamson, “Physical Chemistry of Surfaces”. Wiley, 1976.
13. F. Fowkes, “Contact Angle, Wettability and Adhesion,” American Chemical Society, 1964.
14. D. Quere “Non-sticking Drops” Rep. Prog. Phys. 68, 2495, 2005.
15. McCarthy, T. A Perfectly Hydrophobic Surface, J. Am. Chem. Soc., 2006, 128, 9052.


Product Code		Product Name		Molecular Weight	Boiling Point/mm (Melting Point)	Refractive Index	Specific Gravity	Other Physical Properties
SIA0588.0		(AMINOETHYLAMINOMETHYL)PHENETHYL-TRIMETHOXYSILANE, 90% mixed m,p isomers		298.46	126-30°/0.2 flashpoint: > 110°C (>230°F)	1.5083	1.02	
[74113-77-2]		TSCA HMIS: 3-1-1-X			25g/\$82.00		100g/\$266.00	
CAS#		Indicates Product listed in TSCA Inventory (L = Low Volume Exemption; S = Significant New Use Restriction)		Hazardous Rating Information (Health-Flammability-Reactivity)		References		

C₁₄H₂₆N₂O₃Si
coupling agent for polyimides photochemically sensitive (194nm)¹ self-assembled monolayers².

1. W. Dressick et al, Thin Solid Films, 284, 568, 1996.
2. C Harnett et al, Appl. Phys. Lett., 76, 2466, 2000.

HYDROLYTIC SENSITIVITY: 7 Si-OR reacts slowly with water/moisture

Cover
background photo:
*Fluoroalkylsilane treated
multi-color red granite is both
hydrophobic and
oleophobic.*



*The Stenocara beetle,
an African desert species,
harvests water that adsorbs on
superhydrophilic bumps on its back,
then transfers droplets into
superhydrophobic channels
that lead to its mouth.*

Gelest

Gelest Inc.
11 East Steel Road
Morrisville, PA 19067
Phone (215) 547-1015
Fax: (215) 547-2484
www.gelest.com